

## MIT Open Access Articles

*Spectroscopic perspective on the interplay between electronic and magnetic properties of magnetically doped topological insulators*

The MIT Faculty has made this article openly available. **Please share** how this access benefits you. Your story matters.

**Citation:** Krieger, J. A., et al. "Spectroscopic Perspective on the Interplay between Electronic and Magnetic Properties of Magnetically Doped Topological Insulators." *Physical Review B*, vol. 96, no. 18, Nov. 2017. © 2017 American Physical Society

**As Published:** <http://dx.doi.org/10.1103/PhysRevB.96.184402>

**Publisher:** American Physical Society

**Persistent URL:** <http://hdl.handle.net/1721.1/117039>

**Version:** Final published version: final published article, as it appeared in a journal, conference proceedings, or other formally published context

**Terms of Use:** Article is made available in accordance with the publisher's policy and may be subject to US copyright law. Please refer to the publisher's site for terms of use.





# Spectroscopic perspective on the interplay between electronic and magnetic properties of magnetically doped topological insulators

J. A. Krieger,<sup>1,2</sup> Cui-Zu Chang,<sup>3,4</sup> M.-A. Husanu,<sup>5,6</sup> D. Sostina,<sup>5</sup> A. Ernst,<sup>7,8</sup> M. M. Otrokov,<sup>9,10</sup> T. Prokscha,<sup>1</sup> T. Schmitt,<sup>5</sup> A. Suter,<sup>1</sup> M. G. Vergniory,<sup>11,12</sup> E. V. Chulkov,<sup>9,11,13</sup> J. S. Moodera,<sup>3,14</sup> V. N. Strocov,<sup>5</sup> and Z. Salman<sup>1,\*</sup>

<sup>1</sup>Laboratory for Muon Spin Spectroscopy, Paul Scherrer Institute, CH-5232 Villigen PSI, Switzerland

<sup>2</sup>Laboratorium für Festkörperphysik, ETH-Hönggerberg, CH-8093 Zürich, Switzerland

<sup>3</sup>Francis Bitter Magnet Lab, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, USA

<sup>4</sup>Department of Physics, The Penn State University, University Park, Pennsylvania 16802, USA

<sup>5</sup>Swiss Light Source, Paul Scherrer Institute, CH-5232 Villigen PSI, Switzerland

<sup>6</sup>National Institute of Materials Physics, Atomistilor 405A, 077125 Magurele, Romania

<sup>7</sup>Institut für Theoretische Physik, Johannes Kepler Universität, A 4040 Linz, Austria

<sup>8</sup>Max-Planck-Institut für Mikrostrukturphysik, Weinberg 2, 06120 Halle, Germany

<sup>9</sup>Departamento de Física de Materiales UPV/EHU, Centro de Física de Materiales CFM - MPC and Centro Mixto CSIC-UPV/EHU, 20080 San Sebastián/Donostia, Spain

<sup>10</sup>Tomsk State University, pr. Lenina 36, 634050 Tomsk, Russia

<sup>11</sup>Donostia International Physics Center, P. Manuel de Lardizabal 4, San Sebastián, 20018 Basque Country, Spain

<sup>12</sup>Department of Applied Physics II, Faculty of Science and Technology, University of the Basque Country UPV/EHU, Apdo. 644, 48080 Bilbao, Spain

<sup>13</sup>Saint Petersburg State University, 198504 Saint Petersburg, Russia

<sup>14</sup>Department of Physics, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, USA

(Received 8 August 2017; published 2 November 2017)

We combine low energy muon spin rotation (LE- $\mu$ SR) and soft-x-ray angle-resolved photoemission spectroscopy (SX-ARPES) to study the magnetic and electronic properties of magnetically doped topological insulators, (Bi,Sb)<sub>2</sub>Te<sub>3</sub>. We find that one achieves a full magnetic volume fraction in samples of (V/Cr)<sub>x</sub>(Bi,Sb)<sub>2-x</sub>Te<sub>3</sub> at doping levels  $x \gtrsim 0.16$ . The observed magnetic transition is not sharp in temperature indicating a gradual magnetic ordering. We find that the evolution of magnetic ordering is consistent with formation of ferromagnetic islands which increase in number and/or volume with decreasing temperature. Resonant ARPES at the V  $L_3$  edge reveals a nondispersing impurity band close to the Fermi level as well as V weight integrated into the host band structure. Calculations within the coherent potential approximation of the V contribution to the spectral function confirm that this impurity band is caused by V in substitutional sites. The implications of our results on the observation of the quantum anomalous Hall effect at mK temperatures are discussed.

DOI: [10.1103/PhysRevB.96.184402](https://doi.org/10.1103/PhysRevB.96.184402)

## I. INTRODUCTION

A topological insulator (TI) is a bulk insulator exhibiting an inverted band structure [1]. This, together with time reversal symmetry (TRS), leads to the presence of a spin-polarized Dirac cone in the surface states which is topologically protected against small, TRS invariant perturbations. However, TRS breaking in this system, e.g., by introducing long range ferromagnetism, opens an energy gap at the Dirac point. Such a gapped TI has been proposed to exhibit various new quantum states of matter including the quantum anomalous Hall (QAH) effect [2,3], charge induced magnetic mirror monopoles [4], and Majorana excitations when in proximity to an  $s$ -wave superconductor [5].

Recently the QAH effect has been experimentally observed in Cr and V doped (Bi,Sb)<sub>2</sub>Te<sub>3</sub> [6,7]. This has been possible only at an ultralow temperature (tens of mK), which was attributed to the presence of bulk valence bands at the binding energy of the Dirac point [8]. In addition, it has been pointed out that increasing the homogeneity of the ferromagnetic order might be crucial to elevate the temperature at which the QAH

effect can be observed [9]. Understanding the origin of the magnetism and the resulting splitting of the topological surface states in magnetically doped TIs is a prerequisite to tuning and controlling it. Nevertheless, this issue remains under intense discussion, particularly due to the lack of suitable methods to directly probe the magnetic properties of thin films and determine the nature of magnetism in these systems [10–14].

Theoretically, it was predicted that exchange coupling between the magnetic dopants and the Dirac electrons supports a strong out-of-plane single ion anisotropy [3,15–17]. In contrast, in Cr doped Sb<sub>2</sub>Te<sub>3</sub> it was found that the magnetism at the surface is oriented in plane, which does not allow for the opening of a gap [18]. Moreover, in Mn doped Bi<sub>2</sub>Se<sub>3</sub> the doping induced gap in the surface state was shown to be independent of the magnetism in the sample [19].

In order to realize the QAH effect it is essential that the Fermi level ( $E_F$ ) is located within the exchange gap of the topological surface states. In principle, this excludes any type of free carrier (at  $E_F$ ) mediated coupling between the dopants at low temperature. Instead, it has been proposed that the band inversion in a TI leads to an unusually high spin susceptibility of the parent compound which allows mediating a ferromagnetic coupling between the dopants (so called van Vleck ferromagnetism) [3]. Indeed, a temperature dependent

\*Corresponding author: [zaher.salman@psi.ch](mailto:zaher.salman@psi.ch)

shift of the V  $L_2$  and  $L_3$  edges has been measured with electron energy loss spectroscopy and was attributed to a van Vleck contribution of the V core levels to the ferromagnetism [11].

More recently, transport and scanning nanoSQUID measurements have shown that the magnetism in magnetically doped TIs may be attributed to superparamagneticlike behavior [12,13]. In addition, a high V density of states near  $E_F$  has been found using resonant (angular integrated) photoemission spectroscopy (AIPES) at the V  $L_3$  edge and scanning tunneling spectroscopy [20,21]. This is in agreement with theoretically predicted nonzero V partial density of states (V-DOS) at  $E_F$  [3,22].

Several of the above effects potentially hinder the observation of the QAH effect at higher temperature [8,9,12,13,19–21] and a deeper understanding of the interplay between the electronic and magnetic degrees of freedom in these materials is necessary in order to increase this temperature.

Here we investigate the local magnetic and electronic properties of thin films of V and Cr doped (Bi,Sb) $_2$ Te $_3$  using low energy muon spin rotation (LE- $\mu$ SR) and soft-x-ray angle-resolved photoemission spectroscopy (ARPES). We show that the ferromagnetic transition is gradual and strongly depends on the doping level. The evolution of the magnetic ordering is consistent with magnetic clusters formed at the transition temperature within a predominantly paramagnetic sample. The volume fraction of these clusters increases gradually with decreasing temperature. Our results show that samples of V $_x$ (Bi,Sb) $_{2-x}$ Te $_3$  with doping levels  $x \gtrsim 0.16$  become fully magnetic, while at a lower doping part of the sample does not exhibit magnetic ordering. By using resonant soft-x-ray ARPES at the V  $L_3$  edge we confirm the presence of a nondispersing V impurity band at  $E_F$  as well as spectral weight of V integrated in the host band structure at lower binding energies ( $E_b$ ). We show that the former is reproduced by density functional theory (DFT) in the coherent potential approximation (CPA) assuming substitutional V. In contrast, if the V is placed in the van der Waals (vdW) gap, no such impurity band is formed. The obtained LE- $\mu$ SR and ARPES results are used to understand the correlation between the electronic and magnetic properties of the magnetically doped TIs.

## II. EXPERIMENT

Films of magnetically doped (Bi,Sb) $_2$ Te $_3$  were grown using molecular beam epitaxy on sapphire (0001) substrates. The magnetic dopants were introduced via coevaporation as described in Refs. [23,24] to produce magnetic M $_x$ (Bi $_{1-y}$ Sb $_y$ ) $_{2-x}$ Te $_3$ , where M is either V or Cr. Hereafter we refer to the composition of the magnetic TI layer by M $_x$ . The samples investigated by  $\mu$ SR or ARPES were 20 or 10 quintuple layers (QL) thick, respectively. Before taking the samples out of the growth chamber they were capped with a 3- or 5-nm-thick Te protective layer [25]. A list of all the studied samples with relevant details is given in Table I. Note that similarly prepared films exhibit the QAH effect [6,7].

LE- $\mu$ SR experiments were performed at the  $\mu$ E4 beamline of the Paul Scherrer Institute [26]. The samples were glued using silver paint onto Ni-coated sample plates and mounted on the cold finger of a helium flow cryostat. In these experiments, fully spin-polarized muons with initial polarization chosen to

TABLE I. List of all the samples and the experimental technique which has been used to study them.

| Label       | Cap     | Topological insulator |  | Technique    |
|-------------|---------|-----------------------|--|--------------|
|             | 5 nm Te | 20 QL                 | Sb $_2$ Te $_3$  | LE- $\mu$ SR |
| V $_{0.13}$ | 5 nm Te | 20 QL                 | V $_{0.13}$ Sb $_{1.87}$ Te $_3$                           | LE- $\mu$ SR |
| Cr $_{0.2}$ | 5 nm Te | 20 QL                 | Cr $_{0.2}$ Sb $_{1.8}$ Te $_3$                            | LE- $\mu$ SR |
| V $_{0.08}$ | 3 nm Te | 20 QL                 | V $_{0.08}$ (Bi $_{0.32}$ Sb $_{0.68}$ ) $_{1.92}$ Te $_3$ | LE- $\mu$ SR |
| V $_{0.16}$ | 3 nm Te | 20 QL                 | V $_{0.16}$ (Bi $_{0.32}$ Sb $_{0.68}$ ) $_{1.84}$ Te $_3$ | LE- $\mu$ SR |
| V $_{0.19}$ | 3 nm Te | 20 QL                 | V $_{0.19}$ (Bi $_{0.33}$ Sb $_{0.67}$ ) $_{1.81}$ Te $_3$ | LE- $\mu$ SR |
| V $_{0.23}$ | 3 nm Te | 20 QL                 | V $_{0.23}$ (Bi $_{0.32}$ Sb $_{0.68}$ ) $_{1.77}$ Te $_3$ | LE- $\mu$ SR |
|             | 3 nm Te | 10 QL                 | (Bi $_{0.31}$ Sb $_{0.79}$ ) $_2$ Te $_3$                  | SXARPES      |
| V $_{0.06}$ | 3 nm Te | 10 QL                 | V $_{0.06}$ (Bi $_{0.33}$ Sb $_{0.67}$ ) $_{1.94}$ Te $_3$ | SXARPES      |
| V $_{0.12}$ | 3 nm Te | 10 QL                 | V $_{0.12}$ (Bi $_{0.33}$ Sb $_{0.67}$ ) $_{1.88}$ Te $_3$ | SXARPES      |

be parallel to the surface of the sample, were implanted at a tunable energy in the range of  $E = 1$  to 12 keV, corresponding to mean implantation depths of 10 to 70 nm. This is a key feature which makes LE- $\mu$ SR suited for studying thin film samples. In contrast, the implantation depth of surface muons (conventional  $\mu$ SR) or muons from decay channels (measurements under high pressure) is on the order of several hundreds of micrometers to centimeters, respectively [27,28], and therefore cannot be used to investigate thin samples.

The implanted muon decays (lifetime  $\tau_\mu = 2.2 \mu$ s) by emitting a positron preferentially along the muon spin direction. Therefore, the time evolution of the ensemble average of the muon spin polarization can be reconstructed by measuring the spatial distribution of emitted positrons using four detectors around the sample [28]. The asymmetry in positron counts between opposite detectors  $A(t)$  is proportional to the muon spin polarization along this direction, and reflects the temporal and spatial distribution of the magnetic fields at the muon stopping site. Weak transverse field  $\mu$ SR (wTF- $\mu$ SR) measurements as a function of temperature have been performed by field cooling in an applied field of 5 mT perpendicular to the surface of the sample and the initial muon spin polarization. The schematic experimental setup is shown in Fig. 1(a).

Soft-x-ray ARPES measurements were conducted at the ADDRESS beamline of the Swiss Light Source at the Paul Scherrer Institute [29] using circularly polarized photons in the energy range of 320 to 950 eV with a total energy resolution ranging from 40 to 160 meV. At energies corresponding to resonant photoemission at the V  $L_3$  edge the combined beamline and analyzer resolution was 60 meV. The experimental geometry provides a grazing incidence of the x rays on the sample as described in Ref. [30]. The measurements were carried out at 12 K to quench the thermal effects reducing the coherent  $\mathbf{k}$ -resolved spectral component at high photoelectron energies [31]. During the experiment the pressure was kept below  $10^{-10}$  mbar. In order to correct the angular dependence of the analyzer transmission, all spectra have been normalized to the diffuse intensity measured above  $E_F$ . X-ray absorption spectroscopy (XAS) measurements were also performed on the same beamline by measuring the total electron yield (TEY) via the sample drain current normalized by the incoming photon intensity.

For the ARPES measurements, the Te capping was first partially removed by sputtering the sample in  $5 \times 10^{-6}$  mbar

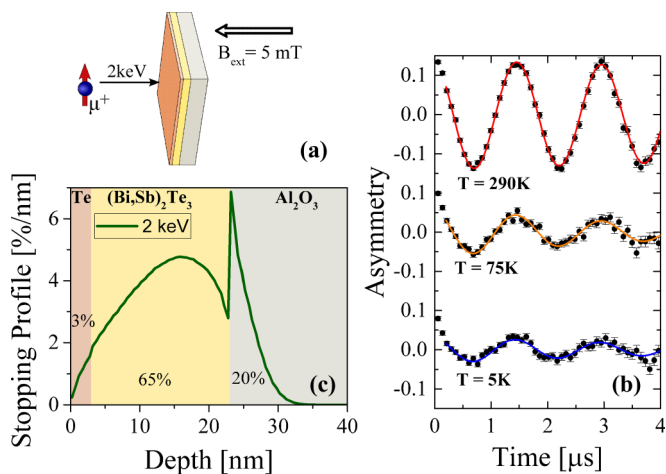


FIG. 1. (a) Schematic of the experimental configuration, where spin-polarized muons impinge on the sample with an implantation energy  $E$ . An external magnetic field of 5 mT is applied perpendicular to the initial muon spin and the sample surface. (b) Asymmetry spectra measured in the  $V_{0.19}$  sample with an implantation energy of  $E = 2$  keV, at different temperatures. The solid lines are fits to Eq. (1). (c) Simulated stopping profile of the implanted muons as a function of depth at  $E = 2$  keV, where almost 65% of all incoming muons stop in the TI layer.

Ar at 0.25 keV for 20 min. The remaining cap layer was evaporated by quickly heating the sample up to 340 °C where it was kept for 10 min. Then it was cooled down to 300 °C where it was kept for 20 min to prevent reabsorption of the evaporated Te, before cooling it to cryogenic temperatures and performing the ARPES measurements. During this process, the temperature of the samples was monitored using an optical pyrometer and the pressure in the preparation chamber was kept below  $10^{-7}$  mbar.

### III. RESULTS

#### A. Low energy muon spin rotation

Representative wTF- $\mu$ SR asymmetry spectra, measured at 2 keV implantation energy and different temperatures, are presented in Fig. 1(b). At high temperatures an almost undamped, large amplitude precession signal was observed. In contrast, a much smaller amplitude with a larger damping rate was measured at low temperatures, where a considerable part of the asymmetry decayed at very early times. At the implantation energy used in these measurements, most of the muons stop inside the TI layer, while less than 3% stop inside the Te capping and less than 20% in the sapphire substrate. Figure 1(c) shows the simulated stopping distribution profile of the muons at the corresponding implantation energy, which was calculated using the TRIM.SP Monte Carlo code [32]. Measurements as a function of implantation energy confirmed the validity of this simulation, see Fig. 1 in the Supplemental Material (SM) [33].

In a transverse field measurement, where the applied field  $B_0$  is much larger than the internal static fields sensed by the muons, one expects to measure an asymmetry oscillating at the Larmor frequency  $\omega_L = \gamma_\mu B_0$ , where  $\gamma_\mu = 2\pi \times 135.5$  MHz/T is the muon gyromagnetic ratio. However,

when the internal static field is much larger than the applied field, as is typically the case below a magnetic transition, the oscillating asymmetry becomes heavily damped. Due to the finite temporal resolution of the  $\mu$ SR technique, this can lead to an effective loss of initial asymmetry. Therefore, muons stopping in a magnetically ordered part of the sample or in the nickel sample holder [34] experience a larger static magnetic field and appear as a missing fraction in the asymmetry spectra. On the other hand, muons stopping in a paramagnetic region of the sample will precess at  $\sim \omega_L$ . Hence, considering only the oscillating signal after 0.2  $\mu$ s allows us to estimate the paramagnetic volume fraction of the sample, while the missing asymmetry at early times corresponds to the magnetic volume fraction.

Following this logic, we used the *Musrfit* software [35] to fit the measured  $\mu$ SR spectra between 0.2 and 8  $\mu$ s to an exponentially damped oscillating function,

$$A(t) = A_0 e^{-\lambda t} \cos(\gamma_\mu B t + \varphi), \quad (1)$$

where  $A_0$  is the extrapolated initial amplitude of the oscillating asymmetry at  $t = 0$   $\mu$ s,  $B$  is the mean field at the muons' stopping sites, and  $\lambda$  is the damping rate, which corresponds primarily to the width of the static local field distribution. The phase  $\varphi$  is determined by the initial muon spin direction and the geometry of the detectors. The temperature dependence of  $A_0$  (normalized to its value in the paramagnetic phase at 290 K),  $B$ , and  $\lambda$  obtained from the fits of all studied samples are shown in Fig. 2.

Note that the undoped sample exhibits an almost temperature independent  $A_0$  and  $\lambda$ , as expected for a nonmagnetic sample. In contrast, we observe a drop in  $A_0$  upon cooling the doped samples, which we associate with the appearance of strong static fields in portions of the sample. This drop can be attributed to a magnetic ordering at a transition temperature  $T_c$ . Clearly  $T_c$  and the relative size of drop in  $A_0$  depends strongly on the dopant and doping level in the sample. We also note that the drop in  $A_0$  is accompanied by an increase in  $\lambda$  and a decrease in  $B$ .

For comparison, measurements in zero field (ZF) on the  $V_{0.19}$  sample are shown in Fig. 3. At high temperature, the asymmetry follows an exponential-like behavior with a damping rate which increases sharply below  $T_c$ . We also note a change of the relaxation from a single exponential-like behavior to a biexponential relaxation below  $T_c$ , as is typical for systems undergoing magnetic ordering [28]. Therefore, we fit the data to the sum of two exponentials,

$$A(t) = A_0 \left( \frac{1}{3} e^{-\lambda_1 t} + \frac{2}{3} e^{-\lambda_2 t} \right). \quad (2)$$

This simplified model assumes that below the magnetic transition the implanted muons experience a Lorentzian distribution of randomly oriented static fields with an additional small and fluctuating component. In this case, an ensemble average of one third of the initial muon spin polarization is aligned parallel to the randomly oriented static local field, while two thirds are perpendicular to it. The 1/3 component can relax only due to fluctuations in the magnetic field, and hence is referred to as a dynamic component. On the other hand, the damping of the 2/3 component is due to incoherent precession and depolarization which is determined by the width of the static field distribution and is referred to as a static component [28].

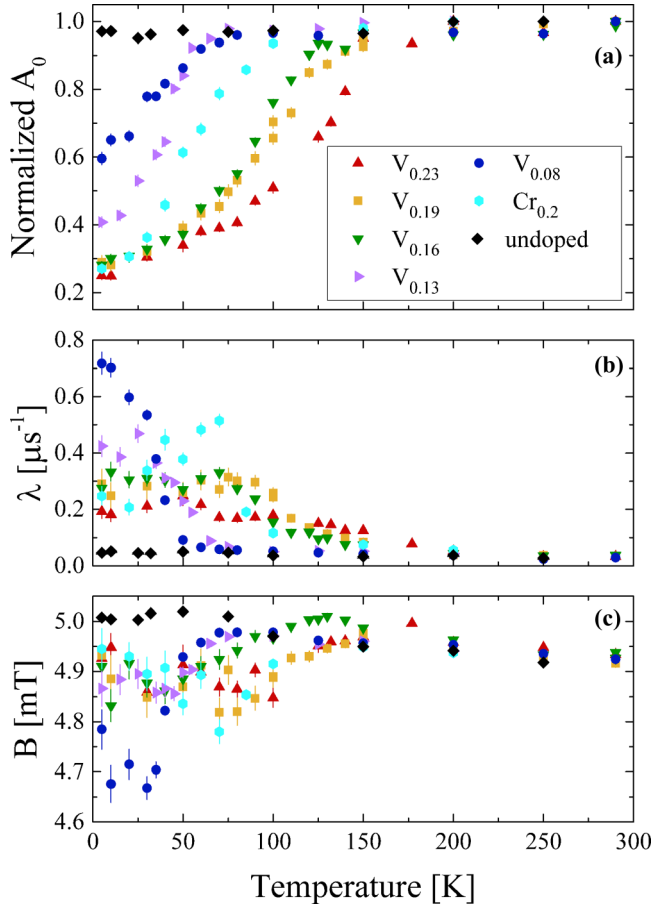


FIG. 2. Temperature dependence of (a) the normalized  $A_0$ , (b)  $\lambda$ , and (c)  $B$  obtained from the fits for the different  $M_x(\text{Bi}_{1-y}\text{Sb}_y)_{2-x}\text{Te}_3$  samples which are denoted by  $M_x$ .

Note that the direction of the local field at the muon stopping position strongly depends on the relative (random) location of the nearest dopant atom. Therefore, the random orientation of the local dipolar field does not necessarily imply randomly oriented magnetic moments.

Despite ignoring the presumably different contributions from various layers of the sample and substrate, the ZF measurements fit very well to Eq. (2), confirming the observed magnetic ordering from TF measurements and allowing a qualitative understanding of the behavior of the sample. In particular it shows that the damping rates above  $T_c$  are equal and almost temperature independent, reflecting the dynamic nature of the muon spin relaxation. Below  $T_c$  we observe a strong increase of the depolarization of the 2/3 component which is associated with the appearance of static magnetic fields in the sample due to the magnetic ordering.

### B. Soft-x-ray ARPES

The experimental band structure of the  $V_{0.06}$  sample measured at photon energy  $h\nu = 355$  eV is shown in Fig. 4. The constant  $E_b$  cuts as a function of the  $(k_x, k_y)$  coordinates [Fig. 4(b)] exhibit a pointlike feature at  $E_F$ , which can be associated with the topological surface state, and the hexagonally symmetric, flower-shaped bulk valence band below. This is

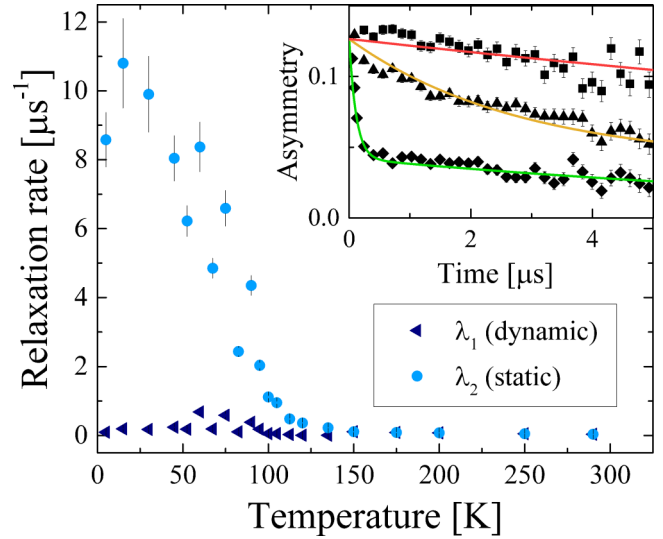


FIG. 3. Dynamic ( $\lambda_1$ ) and static ( $\lambda_2$ ) zero field relaxation rate as a function of temperature in the  $V_{0.19}$  sample. The inset shows typical asymmetry spectra at temperatures of 290, 120, and 5 K (from top to bottom). The solid lines are fits to Eq. (2).

similar to what is seen in ultraviolet ARPES, cf. [8]. We note that the dispersions are less sharp than in ultraviolet ARPES measurements on similar samples [8,36]. This worsens with increasing  $h\nu$ , cf. the measurement at 510 eV in Fig. 8(a). We attribute this effect to the doping induced distortions of the crystal lattice, which can be considered as “frozen phonons” affecting the coherent ARPES intensity similarly to the thermal effects which occur at high photon energies [31].

In Fig. 4(c) the measurement as a function of  $h\nu$  reveals that the surface state exhibits intensity modulations without dispersing as a function of  $k_z$ . To compensate for the effect of the decrease in the photoemission cross section with increasing  $h\nu$  in Fig. 4(c), each measurement was normalized to the total AIPES intensity outside the  $\Gamma$  point, within  $\pm 0.1$  eV around  $E_F$ .

Figure 5 shows the XAS across the V  $L_2$  and  $L_3$  edges. The deviation from the theoretical branching ratio of 2:1 and satellites to the peaks have been reported previously in similar samples and were attributed to final state effects ([20] and references therein). The peak positions are consistent with the literature values, however the peak width is larger than what is usually observed in these samples [20,21]. As we will discuss later, this could be caused by different chemical environments of the V atoms.

In Fig. 6 we plot the raw AIPES intensity of the  $V_{0.06}$  sample as a function of  $E_b$  and  $h\nu$  where the latter is scanned across the V  $L_3$  edge. The spectra were integrated along the  $\Gamma$ - $M$  direction. There is a clear intensity increase at the V  $L_3$  resonance around  $h\nu \approx 515.7$  eV, at  $E_b \approx -1.2$  eV. A careful analysis of constant  $E_b$  cuts, shown in Fig. 6(b), reveals that at  $h\nu \approx 514.2$  eV there is another resonance close to  $E_F$ . Note that there is no intensity drop at low  $h\nu$  like it is sometimes observed for Fano resonances. The two resonances can be distinguished more clearly by looking at the energy distribution curves (EDC) in Fig. 6(c) from which

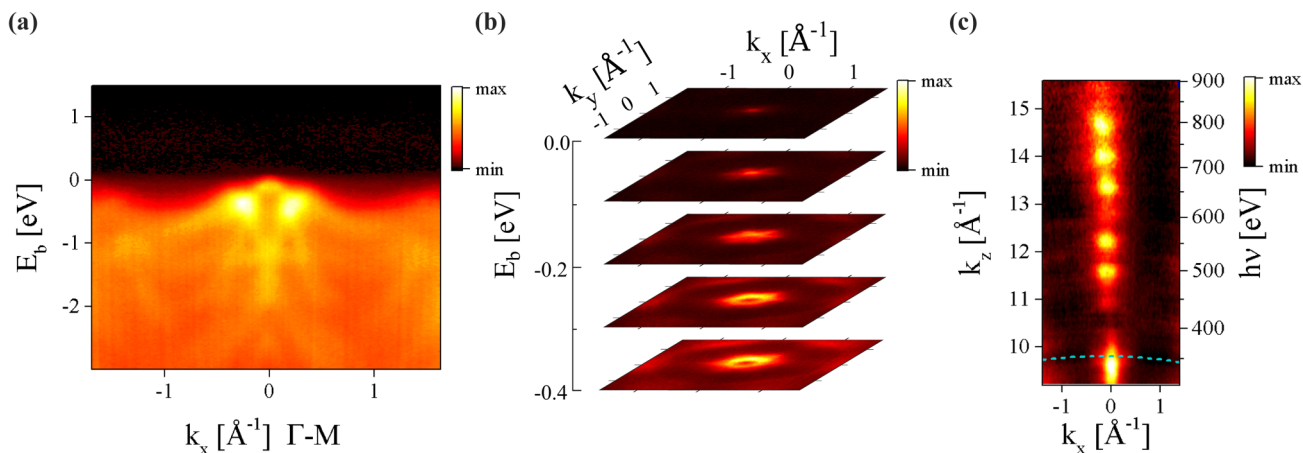


FIG. 4. (a) Band structure at 355 eV of the  $V_{0.06}$  sample measured along the  $\Gamma$ - $M$  direction. (b) Constant energy cut maps measured at  $h\nu = 355$  eV. (c) Fermi surface map along  $(k_x, k_z)$ . The  $h\nu$  values at  $k_x = 0$  are shown in the right axis. The dashed line indicates the position of the cut shown in (a) and (b).

the off-resonance contribution measured at 510 eV has been subtracted.

Resonant ARPES measurements have been performed by tuning the photon energy to the V  $L_3$  peak measured in XAS (514.7 eV) as indicated in Fig. 5. Off-resonance reference measurements were performed at  $h\nu = 510$  eV. The corresponding AIPES at different doping levels are compared in Fig. 7. Although the spectral shape of the undoped sample might have been affected by its incomplete decapping, it does not show any resonance at the V  $L_3$  edge either in XAS or in resonant AIPES. The difference of the AIPES measured on and off resonance, which reflects the V-DOS [37,38], is shown in Fig. 7(b). In the doped samples the two peaks are located at similar  $E_b$ , suggesting that the behavior observed in Fig. 6 is independent of the doping level. Note that we cannot resolve a shift of the DOS on the order of 20 meV at different doping levels due to a change in host carrier density that has been previously reported in Cr-doped  $(\text{Bi,Sb})_2\text{Te}_3$  [14].

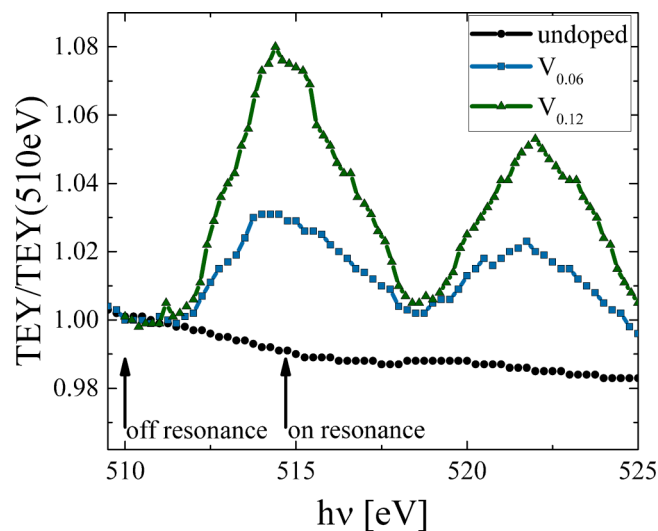


FIG. 5. Normalized TEY at the V  $L_2$  and  $L_3$  edges for different dopings. The arrows indicate the energies where the on and off resonant ARPES spectra were measured.

The EDCs measured on and off resonance [corresponding to the AIPES in Fig. 7(a)] on the  $V_{0.06}$  sample are shown in Fig. 8(b). Subtracting them gives the angle-resolved difference plot in Fig. 8(c). It is important to point out that the resonant contribution close to  $E_F$  forms a nondispersive impurity band, whereas the one around  $-1.2$  eV seems to be dispersive and hybridized with the host band structure. We also note that the behavior of the  $V_{0.12}$  sample is similar, but more smeared due to the larger disorder.

### C. Theory

Electronic structure calculations were performed by employing density functional theory within the generalized gradient approximation [39]. We used a full potential relativistic spin-polarized Green function method [40], in which disorder effects were treated within the coherent potential approach (CPA) [41]. The angular momentum cutoff was set to  $l_{\max} = 3$ . We have used 32 Gaussian quadrature points to carry out a complex energy contour integration, while for the integration over the irreducible Brillouin zone we used a  $30 \times 30 \times 30$   $\mathbf{k}$  points mesh. The experimental lattice constants and atomic coordinates of  $(\text{Bi,Sb})_2\text{Te}_3$  were adopted for the calculations [42]. According to the available experimental data [43–56], 3d transition metal impurities in tetradymitelike chalcogenides substitute typically cation atoms (Bi and Sb). However, STM studies also reveal van der Waals positions [50,54] of Fe atoms in the bulk  $\text{Bi}_2\text{Se}_3$ . Based on these data, we considered that V may occupy the substitutional position in the (Bi,Sb) sublattice and the octahedral interstitial site in the vdW gap.

To extract the V contribution to the Bloch spectral function (BSF), we calculated the Fourier transformed site and angular momentum projected Green function including non-site-diagonal terms within a coherent potential approximation. In this approach a direct extraction of the V contribution is not possible because of the non-site-diagonal terms. However, since in these systems only V atoms have  $d$  electrons, the Bloch spectral function projected into the angular momentum channel  $l = 2$  can be associated with the V contribution to the BSF. The result for  $V_{0.06}(\text{Bi}_{0.33}\text{Sb}_{0.67})_{1.94}\text{Te}_3$  considering

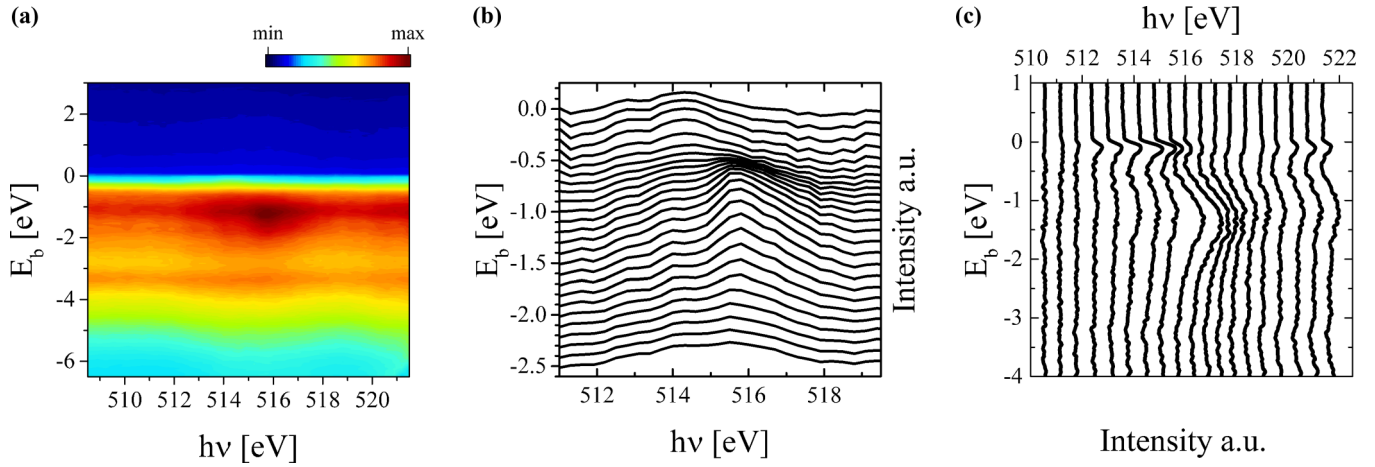


FIG. 6. (a) Raw AIPES of the  $V_{0.06}$  sample as a function of  $h\nu$  across the  $L_3$  edge of V. (b) Angle integrated constant  $E_b$  cuts. (c) The difference between AIPES measured at  $h\nu$  and off resonance (i.e., at 510 eV).

only V in substitutional positions is shown in Fig. 8(d). A second calculation including additional V in the vdW gap of  $V_{0.06+0.03}(Bi_{0.33}Sb_{0.67})_{1.94}Te_3$  is shown in Fig. 9.

#### IV. DISCUSSION

##### A. Muon spin rotation

The strong increase of the static ZF relaxation rate below  $T_c$  confirms the magnetic origin of the features we observe in wTF- $\mu$ SR measurements below the same temperature. The magnetic moments of the dopant atoms, which give only a small, motionally narrowed relaxation rate above the transition, slow down with decreasing temperature and

produce a broad, static field distribution below  $T_c$ . In the ZF measurements, a small increase of the dynamic relaxation is also observed below the transition, probably due to the slowing down of magnetic field fluctuations from the dopant moments. We also point out that the rate of the static depolarization at low temperature decreases with increasing doping level (not shown). This indicates a broader field distribution in the lower doping samples (as expected) and is generally consistent with the corresponding decrease in the wTF depolarization rates [Fig. 2(b)].

The onset of the magnetic transition at  $T_c$ , which coincides with the drop in  $A_0$ , increases with doping level. We also note that the transition temperature is generally higher for the V doped samples than for the Cr doped sample, even at lower doping levels. This is in agreement with the ferromagnetism that is commonly observed in these materials [6,7,14,43,45,46,48]. As mentioned earlier, the gradual decrease of the wTF initial asymmetry below  $T_c$  indicates the gradual formation of ferromagnetic regions, in an otherwise paramagnetic sample. At  $T_c$ , ferromagnetism is established in small islands which increase in number and/or size as the temperature is decreased. One important aspect of the results in Fig. 2 is the fact that in the samples with dopant concentrations  $x \gtrsim 0.16$  the initial asymmetry seems to decrease to the same value at the lowest temperature,  $\sim 5$  K. Given the similar geometry of the measured samples, this is a clear indication that at this temperature the TI layer is fully magnetic and that the remaining asymmetry is due to muons stopping in the Te capping layer, the sapphire substrate, or background contribution from muons landing outside the sample. From these measurements we can evaluate the magnetic volume fraction of the doped TI layer by considering the contribution of muons stopping in each layer to the measured asymmetry, normalized by the full asymmetry above  $T_c$ . Here we assume that muons landing in the nonmagnetic Te capping maintain their full polarization, while those stopping in the Ni backing depolarize immediately and do not contribute to the measured asymmetry. Furthermore we assume (based on measurements on the bare substrate) that muons in sapphire maintain only 42(7)% of their polarization due to muonium formation. The full details of these estimates and the reference measurements

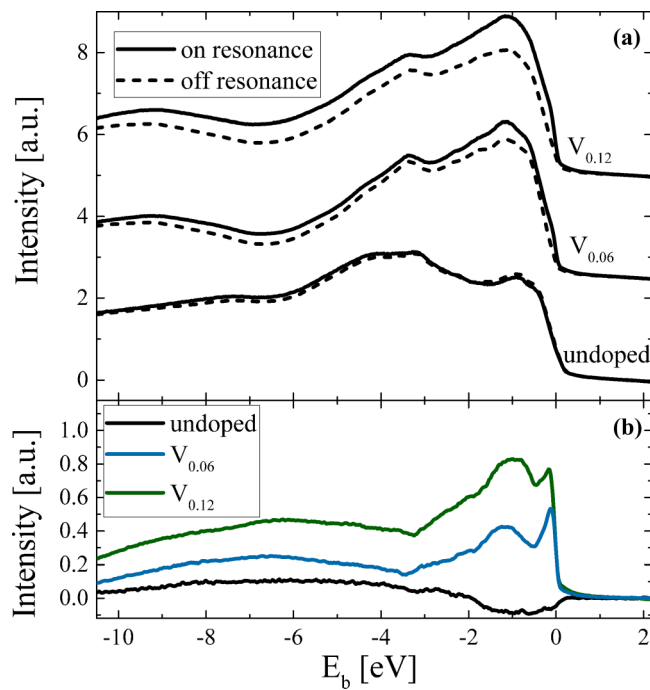


FIG. 7. (a) Resonant AIPES at different doping levels. (b) Intensity difference between the on and off resonance measurements shown in (a).

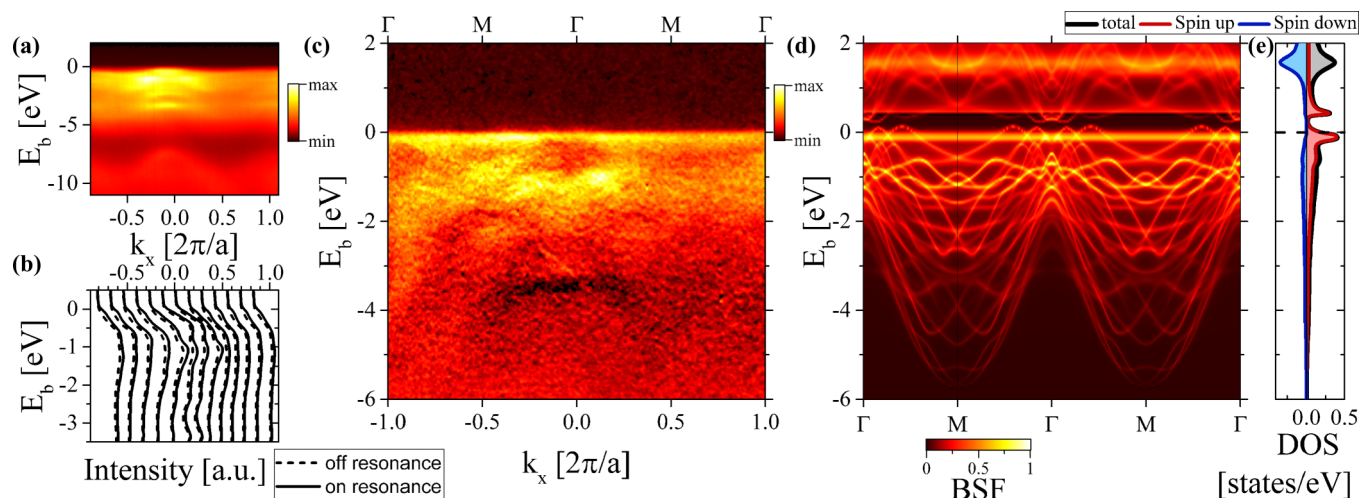


FIG. 8. (a) Off resonance ARPES spectrum measured at  $h\nu = 510$  eV. (b) Energy dependent cuts of the on and off resonant spectra which were used to calculate (c). (c) Intensity difference of the spectra measured on and off resonance for the  $V_{0.06}$  sample. (d) Calculated V contribution to the BSF of  $V_{0.06}(\text{Bi}_{0.33}\text{Sb}_{0.67})_{1.94}\text{Te}_3$ , assuming that V only occupies substitutional positions. (e) The corresponding spin-resolved V-DOS.

are given in the SM [33]. The resulting volume fraction as a function of temperature is shown in Fig. 10.

These results clearly show that the volume fraction at low temperature increases with increasing doping level saturating at a doping of  $x \approx 0.16$ , as shown in Fig. 11. Note that this saturation value of the magnetic volume fraction is consistent with a full volume fraction considering the systematic uncertainty in estimating the probability of muonium

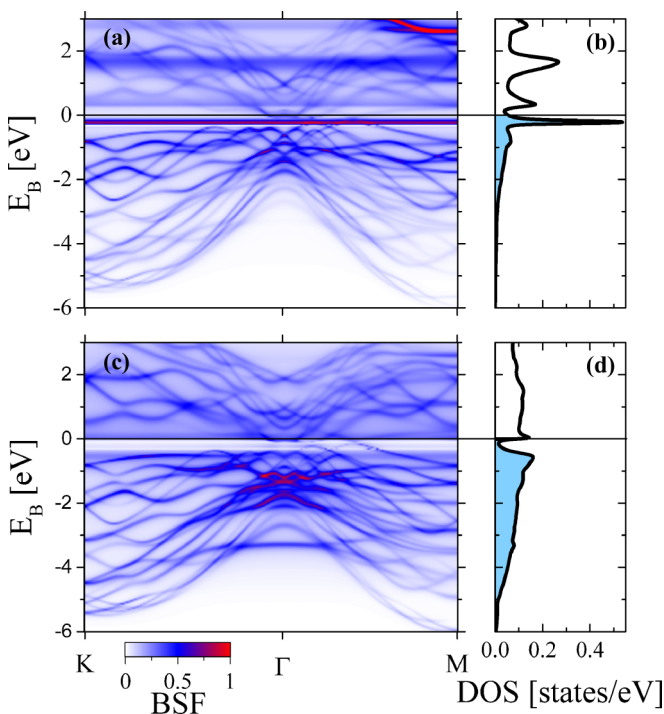


FIG. 9. Calculation on  $V_{0.06+0.03}(\text{Bi}_{0.33}\text{Sb}_{0.67})_{1.94}\text{Te}_3$  with V occupying both substitutional and vdW gap positions. The contribution of substitutional V (a) and V in the vdW gap (c) to the BSF, with the corresponding V-DOS in (b) and (d), respectively.

formation in the sapphire substrate (see full details in the SM [33]). The samples with V doping levels of  $x = 0.13$  and  $x = 0.08$  do not reach a full magnetic volume fraction at the lowest measured temperature (5 K), even when extrapolated to  $T \rightarrow 0$  K. This is one of the important aspects of our results, since such samples, seemingly with only partial magnetic volume fraction, have been shown to exhibit the QAH at very low (mK) temperature [7,12]. Remember, the QAH effect can occur only if the topological surface states are gapped, e.g., by a static magnetic field perpendicular to the surface of the sample. A possible explanation for the source of this static field throughout the sample may be drawn from our measurements. The negative shift of  $B$  [Fig. 2(c)] implies that even in the paramagnetic regions of the sample there is on average a net static field perpendicular to the surface. At low enough temperatures these fields may be sufficient to open the

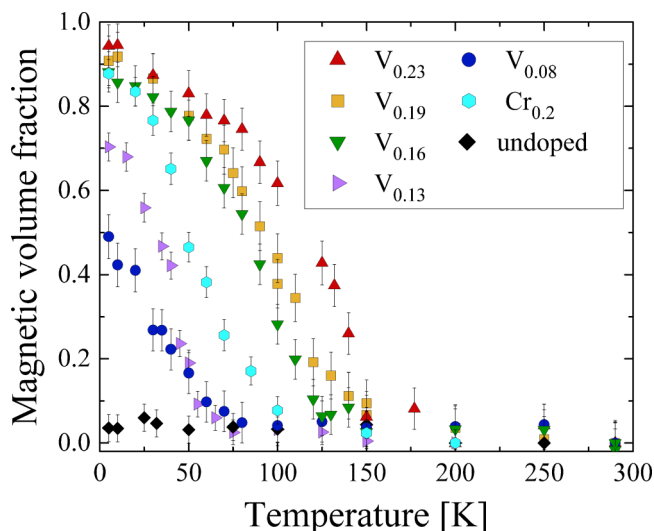


FIG. 10. Magnetic volume fraction as a function of temperature, measured in the samples listed in Table I.



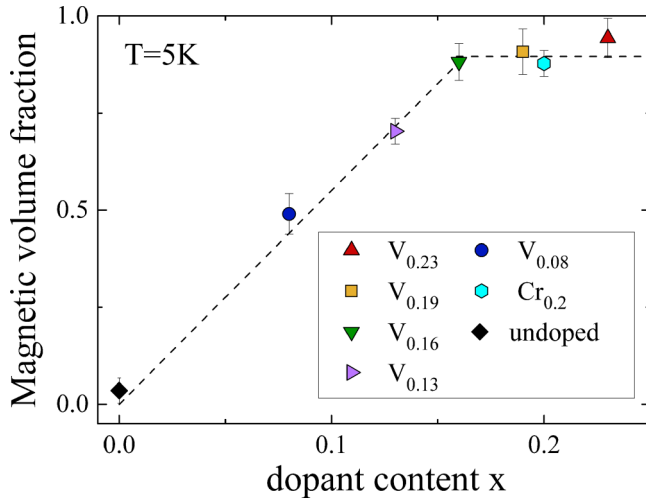


FIG. 11. Magnetic volume fraction at the lowest temperature of 5 K as a function of the dopant concentration  $x$ . The dashed line is a guide to the eye, showing that the volume fraction increases almost linearly with  $x$  until it saturates at  $x \approx 0.16$ .

required gap in the surface states which is necessary for the observation of the QAH effect.

The drop in  $A_0$  is consistent with both, partial volume ferromagnetism and superparamagnetism as has been reported on similar samples [12,13]. However, clues concerning the nature of the magnetic ordering in these systems can be obtained from a careful inspection of the temperature and field dependence of  $B$  [Fig. 2(c)]. In the undoped  $Sb_2Te_3$  we observe an increase of  $B$  with decreasing temperature, up to 2% of its value at room temperature (RT). The exact source of this shift is unknown, but it is most probably of hyperfine origin. A similar shift in  $B$  is observed above  $T_c$  in the magnetically doped samples. However, below  $T_c$  we detect a negative shift in  $B$ , which reaches 5% of the RT value. This surprising effect is most pronounced in the lowest doping sample. Such large (and negative) field shifts have been reported in other materials, e.g., in the diluted magnetic semiconductor  $Cd_{1-x}Mn_xTe$  [57,58] and in  $MnSi$  [59,60]. These were attributed to a large hyperfine interaction of the muon with the screening electrons, which results in a shift proportional to the applied field [28,57–60]. However, in the  $V_{0.08}$  sample we detect a shift which is not proportional to the applied field (Fig. 2 in the SM [33]). In addition field cooled and zero-field cooled measurements yield significantly different shifts (Fig. 3 in the SM [33]). These observations exclude a shift due to hyperfine interaction and support a scenario where the shift is due to dipolar fields from ferromagnetic islands acting as superparamagnets.

To understand this effect it is important to note that the measured precessing signal, and thereby the observed field shift, originate from parts of the sample which are not magnetically ordered. The ferromagnetic islands in the sample produce a dipolar field in these paramagnetic regions. If we assume that the magnetic moment of the islands are randomly oriented, then their dipolar contributions average to zero [sketched in Fig. 12(a)]. In such a case we would expect only an increase in the width of field distribution sensed by the muons. Therefore, the shift in the magnetic field

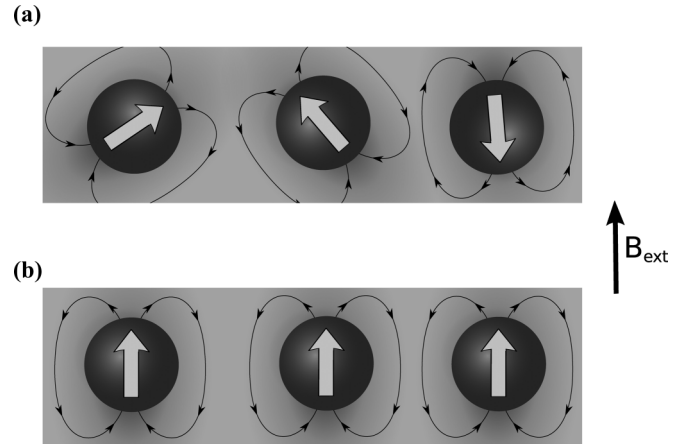


FIG. 12. Representation of the magnetic islands in the sample and their dipolar fields. (a) Randomly oriented islands: The dipolar fields average out to zero over the whole sample. (b) Islands aligned with the applied field: There is a net field opposite to the external field in the paramagnetic regions.

below  $T_c$  provides a strong evidence that the ferromagnetic domains align with the applied field, producing an average dipolar field in the opposite direction in the paramagnetic regions [Fig. 12(b)]. This is consistent with the reduction of the field shift upon zero-field cooling. Furthermore, it agrees with the superparamagnetism, i.e., weakly coupled magnetically ordered clusters embedded in a paramagnetic matrix, that has been reported in Refs. [12,13]. Both of these experiments were performed at temperatures below 300 mK on samples with dopant concentrations of  $x = 0.11$  or  $x = 0.1$  of V or Cr, respectively. Based on our results, these samples are not expected to be fully magnetic. As the field shift and the paramagnetic volume fraction decreases with increasing doping level, it may be possible to suppress this superparamagnetic behavior by increasing the doping level of the samples.

## B. ARPES and theory

We observe two peaks in the difference between resonant and off resonant AIPES. The one close to  $E_F$  is in agreement with Ref. [20], while the second one has not been reported before. The additional increase of intensity at  $E_b$  below  $-4$  eV [Fig. 7(b)] has previously been attributed to a contribution of a direct Auger decay [20]. Here it is less pronounced than in Ref. [20], possibly due to the lower dopant concentration in our sample. The different  $h\nu$  values of the two resonances in the AIPES scan (Fig. 6) point to the presence of two chemically different V species in the sample. This interpretation is consistent with the broader XAS peak that we observed.

The calculations show that there is a peak in the V-DOS of substitutional V around  $E_b = -0.1$  to  $-0.2$  eV, independent of the presence of additional V in the vdW gap [Figs. 8(e) and 9(b)]. Therefore, we attribute the first peak at  $E_b = -0.1$  eV in resonant AIPES to substitutional V. In addition, this peak corresponds to a nondispersing impurity band in the resonant ARPES measurement, which is also reproduced by

the calculation for substitutional V but absent for V in the vdW gap, cf. Fig. 9(c), confirming our conclusion regarding its origin.

In contrast, the second resonance at higher  $h\nu$  and lower binding energy does not agree with the peaks in our calculations of the V-DOS. The difference spectra in Fig. 8(c) features a general intensity increase around  $E_b = -1.2$  eV and some additional dispersing features around  $\Gamma$  at the same binding energy. The latter seem to be hybridized with the host band structure and are likely to be caused by V in the vdW gap as they agree with the calculated  $\mathbf{k}$ -resolved BSF in Fig. 9(c). The origin of the former is unclear, but we suspect it to be from V that segregated to the surface of the sample or oxidized during the sample preparation. In particular, some V oxides are expected to exhibit V derived states at this binding energy [61].

### C. Magnetic coupling mechanism

Both calculations and resonant ARPES measurements reveal a finite V-DOS at  $E_F$  and therefore also at  $E_b$  corresponding to the Dirac point, which is expected to be slightly below  $E_F$  [8,23]. Bulk states at this binding energy are expected to destroy any quantized transport signatures, as they open additional conduction channels alongside the QAH states at the surface [8,62]. However, they may be essential to mediate the magnetic coupling at higher temperatures. Carrier free magnetism has been proposed to either occur via van Vleck ferromagnetism or ferromagnetic superexchange [3,20]. The latter is usually short ranged and requires a high enough dopant concentration to produce long range order. The site percolation thresholds have been calculated to be 26.23(2)% in a triangular stack lattice and 69.71(4)% for a honeycomb lattice [63]. These values are much higher than the magnetic dopant concentration in our samples, where we find a full volume fraction already at 8% substitution of (Bi,Sb). This implies that a ferromagnetic superexchange alone is not sufficient to explain the long range magnetic coupling. Note that this does not exclude the presence of superexchange to trigger nucleation but requires other longer range interactions for the whole sample to become ferromagnetic.

The gradual evolution of the magnetic ordering which we see with  $\mu$ SR is another clear indication that there is a broad range of magnetic interactions involved. This hints at a scenario where charge carrier mediated interactions dominate. It would also agree with the finite V-DOS that we observe at  $E_F$  and with the magnetic moments on the Sb and Te sites that have been reported by x-ray magnetic circular dichroism [14]. In addition, DFT calculations on  $\text{Bi}_2\text{Te}_3$  and  $\text{Sb}_2\text{Te}_3$  predict the coupling to be caused mainly by RKKY interactions within the (Bi,Sb) layer and a double exchange via Te between adjacent layers [10]. Both of these mechanisms rely upon charge carriers at  $E_F$  [64]. Together these findings favor a scenario where the magnetic interactions are carrier mediated, thus giving a possible explanation for the observation of the QAH effect only at dilution refrigerator temperatures. It is likely that at these low temperatures other effects (like disorder induced localization of the impurity band together with gating) allow to fully gap the system without affecting the ferromagnetism in the sample.

## V. CONCLUSION

Our  $\mu$ SR measurements on low doping samples indicate a partial volume fraction of magnetic regions embedded in a paramagnetic environment. They exhibit no long range magnetic order even at temperatures down to 5 K. For higher doped samples ( $x \gtrsim 0.16$ ) we show that the samples become fully magnetic at low temperatures. Our findings are consistent with a scenario where weakly coupled ferromagnetic islands behave as superparamagnetic clusters which can be aligned with fields as low as 5 mT. Using resonant SX-ARPES we detect a nondispersing impurity band close to  $E_F$  which is doping level independent. By comparing it with calculations for two different V sites (V substituting Bi/Sb and in the vdW gap) we find that this impurity band originates from substitutional V. In addition, the calculations for both sites and the resonant ARPES measurements exhibit a finite V-DOS at  $E_F$ . This implies that the magnetic coupling at high temperature is predominantly carrier mediated. Along with the partial magnetic volume fraction, the additional conduction channels introduced by the impurity band could be another factor limiting the observation of the QAH effect at elevated temperature.

In this study we combine both LE- $\mu$ SR and SX-ARPES to investigate the same system. These two unique experimental techniques offer a complementary understanding of the electronic and magnetic state of the studied materials. This method of investigation is generally applicable to any magnetically doped system, including but not limited to dilute magnetic semiconductors, transition metal oxides, spin glasses, etc. and presents a powerful tool to tune and optimize such materials. Furthermore, this approach can be extended to magnetic heterostructure and buried interfaces, given that the top layer is thin enough ( $\lesssim 3$  nm) in order to allow the escape of the SX-ARPES photoelectrons.

## ACKNOWLEDGMENTS

We thank J. Mesot for fruitful discussions, support, and valuable suggestions. We are also grateful to Juraj Krempasky for his advice on sample preparation for the ARPES measurements. The work at PSI was supported by the Swiss National Science Foundation (SNF-Grant No. 200021\_165910). We acknowledge support from DFG through priority program SPP1666 (Topological Insulators), University of the Basque Country (Grants No. GIC07IT36607 and No. IT-756-13), Spanish Ministry of Science and Innovation (Grants No. FIS2013-48286-C02-02-P, No. FIS2013-48286-C02-01-P, and No. FIS2016-75862-P) and Tomsk State University competitiveness improvement programme (Project No. 8.1.01.2017). Partial support by the Saint Petersburg State University Project No. 15.61.202.2015 is also acknowledged. At MIT, C.Z.C. and J.S.M. acknowledge support from the STC Center for Integrated Quantum Materials under NSF grant DMR-1231319 as well as grants NSF (DMR-1207469, DMR-1700137), ONR (N00014-13-1-0301 and N00014-16-1-2657). C.Z.C. also acknowledges the support from the startup grant provided by Penn State University.

- [1] X.-L. Qi and S.-C. Zhang, *Rev. Mod. Phys.* **83**, 1057 (2011).
- [2] X.-L. Qi, Y.-S. Wu, and S.-C. Zhang, *Phys. Rev. B* **74**, 085308 (2006).
- [3] R. Yu, W. Zhang, H.-J. Zhang, S.-C. Zhang, X. Dai, and Z. Fang, *Science* **329**, 61 (2010).
- [4] X.-L. Qi, R. Li, J. Zang, and S.-C. Zhang, *Science* **323**, 1184 (2009).
- [5] X.-L. Qi, T. L. Hughes, and S.-C. Zhang, *Phys. Rev. B* **82**, 184516 (2010).
- [6] C.-Z. Chang, J. Zhang, X. Feng, J. Shen, Z. Zhang, M. Guo, K. Li, Y. Ou, P. Wei, L.-L. Wang *et al.*, *Science* **340**, 167 (2013).
- [7] C.-Z. Chang, W. Zhao, D. Y. Kim, H. Zhang, B. A. Assaf, D. Heiman, S.-C. Zhang, C. Liu, M. H. W. Chan, and J. S. Moodera, *Nat. Mater.* **14**, 473 (2015).
- [8] W. Li, M. Claassen, C.-Z. Chang, B. Moritz, T. Jia, C. Zhang, S. Rebec, J. J. Lee, M. Hashimoto, D.-H. Lu *et al.*, *Sci. Rep.* **6**, 32732 (2016).
- [9] X. Feng, Y. Feng, J. Wang, Y. Ou, Z. Hao, C. Liu, Z. Zhang, L. Zhang, C. Lin, J. Liao *et al.*, *Adv. Mater.* **28**, 6386 (2016).
- [10] M. G. Vergniory, M. M. Otrokov, D. Thonig, M. Hoffmann, I. V. Maznichenko, M. Geilhufe, X. Zubizarreta, S. Ostanin, A. Marmodoro, J. Henk *et al.*, *Phys. Rev. B* **89**, 165202 (2014).
- [11] M. Li, C.-Z. Chang, L. Wu, J. Tao, W. Zhao, M. H. W. Chan, J. S. Moodera, J. Li, and Y. Zhu, *Phys. Rev. Lett.* **114**, 146802 (2015).
- [12] S. Grauer, S. Schreyeck, M. Winnerlein, K. Brunner, C. Gould, and L. W. Molenkamp, *Phys. Rev. B* **92**, 201304 (2015).
- [13] E. O. Lachman, A. F. Young, A. Richardella, J. Cuppens, H. R. Naren, Y. Anahory, A. Y. Meltzer, A. Kandala, S. Kempinger, Y. Myasoedov *et al.*, *Sci. Adv.* **1**, e1500740 (2015).
- [14] M. Ye, W. Li, S. Zhu, Y. Takeda, Y. Saitoh, J. Wang, H. Pan, M. Nurmamat, K. Sumida, F. Ji *et al.*, *Nat. Commun.* **6**, 8913 (2015).
- [15] J. Henk, M. Flieger, I. V. Maznichenko, I. Mertig, A. Ernst, S. V. Ereameev, and E. V. Chulkov, *Phys. Rev. Lett.* **109**, 076801 (2012).
- [16] J. Henk, A. Ernst, S. V. Ereameev, E. V. Chulkov, I. V. Maznichenko, and I. Mertig, *Phys. Rev. Lett.* **108**, 206801 (2012).
- [17] A. S. Núñez and J. Fernández-Rossier, *Solid State Commun.* **152**, 403 (2012).
- [18] F. Yang, Y. R. Song, H. Li, K. F. Zhang, X. Yao, C. Liu, D. Qian, C. L. Gao, and J.-F. Jia, *Phys. Rev. Lett.* **111**, 176802 (2013).
- [19] J. Sánchez-Barriga, A. Varykhalov, G. Springholz, H. Steiner, R. Kirchschrager, G. Bauer, O. Caha, E. Schierle, E. Weschke, A. A. Ünal *et al.*, *Nat. Commun.* **7**, 10559 (2016).
- [20] T. R. F. Peixoto, H. Bentmann, S. Schreyeck, M. Winnerlein, C. Seibel, H. Maaß, M. Al-Baidhani, K. Treiber, S. Schatz, S. Grauer *et al.*, *Phys. Rev. B* **94**, 195140 (2016).
- [21] P. Sessi, R. R. Biswas, T. Bathon, O. Storz, S. Wilfert, A. Barla, K. A. Kokh, O. E. Tereshchenko, K. Fauth, M. Bode *et al.*, *Nat. Commun.* **7**, 12027 (2016).
- [22] P. Larson and W. R. L. Lambrecht, *Phys. Rev. B* **78**, 195207 (2008).
- [23] J. Zhang, C.-Z. Chang, Z. Zhang, J. Wen, X. Feng, K. Li, M. Liu, K. He, L. Wang, X. Chen *et al.*, *Nat. Commun.* **2**, 574 (2011).
- [24] C.-Z. Chang, J. Zhang, M. Liu, Z. Zhang, X. Feng, K. Li, L.-L. Wang, X. Chen, X. Dai, Z. Fang *et al.*, *Adv. Mater.* **25**, 1065 (2013).
- [25] K. Hofer, C. Becker, S. Wirth, and L. H. Tjeng, *AIP Adv.* **5**, 097139 (2015).
- [26] T. Prokscha, E. Morenzoni, K. Deiters, F. Foroughi, D. George, R. Kobler, A. Suter, and V. Vrankovic, *Nucl. Instrum. Methods Phys. Res. Sect. A* **595**, 317 (2008).
- [27] R. Khasanov, Z. Guguchia, A. Maisuradze, D. Andreica, M. Elender, A. Raselli, Z. Shermadini, T. Goko, F. Knecht, E. Morenzoni, and A. Amato, *High Press. Res.* **36**, 140 (2016).
- [28] A. Yaouanc and P. de Réotier, *Muon Spin Rotation, Relaxation, and Resonance: Applications to Condensed Matter*, International Series of Monographs on Physics (Oxford University Press, Oxford, 2011).
- [29] V. N. Strocov, T. Schmitt, U. Flechsig, T. Schmidt, A. Imhof, Q. Chen, J. Raabe, R. Betemps, D. Zimoch, J. Krempasky *et al.*, *J. Synchrotron Radiat.* **17**, 631 (2010).
- [30] V. N. Strocov, X. Wang, M. Shi, M. Kobayashi, J. Krempasky, C. Hess, T. Schmitt, and L. Patthey, *J. Synchrotron Radiat.* **21**, 32 (2014).
- [31] J. Braun, J. Minár, S. Mankovsky, V. N. Strocov, N. B. Brookes, L. Plucinski, C. M. Schneider, C. S. Fadley, and H. Ebert, *Phys. Rev. B* **88**, 205409 (2013).
- [32] E. Morenzoni, H. Glücker, T. Prokscha, R. Khasanov, H. Luetkens, M. Birke, E. M. Forgan, C. Niedermayer, and M. Pleines, *Nucl. Instrum. Methods Phys. Res. Sect. B* **192**, 254 (2005).
- [33] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevB.96.184402> for additional  $\mu$ SR measurements and details of the magnetic volume fraction calculations.
- [34] H. Saadaoui, Z. Salman, T. Prokscha, A. Suter, B. M. Wojek, and E. Morenzoni, *Phys. Proc.* **30**, 164 (2012).
- [35] A. Suter and B. M. Wojek, *Phys. Proc.* **30**, 69 (2012).
- [36] Y. L. Chen, J. G. Analytis, J.-H. Chu, Z. K. Liu, S.-K. Mo, X. L. Qi, H. J. Zhang, D. H. Lu, X. Dai, Z. Fang *et al.*, *Science* **325**, 178 (2009).
- [37] S. L. Molodtsov, M. Richter, S. Danzenbächer, S. Wieling, L. Steinbeck, and C. Laubschat, *Phys. Rev. Lett.* **78**, 142 (1997).
- [38] M. Kobayashi, I. Muneta, Y. Takeda, Y. Harada, A. Fujimori, J. Krempasky, T. Schmitt, S. Ohya, M. Tanaka, M. Oshima *et al.*, *Phys. Rev. B* **89**, 205204 (2014).
- [39] J. P. Perdew and Y. Wang, *Phys. Rev. B* **45**, 13244 (1992).
- [40] M. Geilhufe, S. Achilles, M. A. Köbis, M. Arnold, I. Mertig, W. Hergert, and A. Ernst, *J. Phys.: Condens. Matter* **27**, 435202 (2015).
- [41] B. L. Gyorffy, *Phys. Rev. B* **5**, 2382 (1972).
- [42] M. M. Stasova and N. K. Abrikosov, *Neorgan. Mater.* **6**, 1090 (1970).
- [43] J. S. Dyck, P. Hájek, P. Lošt'ák, and C. Uher, *Phys. Rev. B* **65**, 115212 (2002).
- [44] J. S. Dyck, P. Svanda, P. Lošt'ák, J. Horak, W. Chen, and C. Uher, *J. Appl. Phys.* **94**, 7631 (2003).
- [45] J. S. Dyck, C. Drašar, P. Lošt'ák, and C. Uher, *Phys. Rev. B* **71**, 115214 (2005).
- [46] V. A. Kulbachinskii, P. M. Tarasov, and E. Brück, *Phys. B: Condens. Matter* **368**, 32 (2005).
- [47] J. Choi, S. Choi, J. Choi, Y. Park, H.-M. Park, H.-W. Lee, B.-C. Woo, and S. Cho, *Phys. Status Solidi (b)* **241**, 1541 (2004).
- [48] Z. Zhou, Y.-J. Chien, and C. Uher, *Phys. Rev. B* **74**, 224418 (2006).

- [49] Y. S. Hor, P. Roushan, H. Beidenkopf, J. Seo, D. Qu, J. G. Checkelsky, L. A. Wray, D. Hsieh, Y. Xia, S.-Y. Xu *et al.*, *Phys. Rev. B* **81**, 195203 (2010).
- [50] C.-L. Song, Y.-P. Jiang, Y.-L. Wang, Z. Li, L. Wang, K. He, X. Chen, X.-C. Ma, and Q.-K. Xue, *Phys. Rev. B* **86**, 045441 (2012).
- [51] D. West, Y. Y. Sun, S. B. Zhang, T. Zhang, X. Ma, P. Cheng, Y. Y. Zhang, X. Chen, J. F. Jia, and Q. K. Xue, *Phys. Rev. B* **85**, 081305 (2012).
- [52] X. F. Kou, W. J. Jiang, M. R. Lang, F. X. Xiu, L. He, Y. Wang, Y. Wang, X. X. Yu, A. V. Fedorov, P. Zhang *et al.*, *J. Appl. Phys.* **112**, 063912 (2012).
- [53] T. Schlenk, M. Bianchi, M. Koleini, A. Eich, O. Pietzsch, T. O. Wehling, T. Frauenheim, A. Balatsky, J.-L. Mi, B. B. Iversen *et al.*, *Phys. Rev. Lett.* **110**, 126804 (2013).
- [54] M. M. Yee, Z.-H. Zhu, A. Soumyanarayanan, Y. He, C.-L. Song, E. Pomjakushina, Z. Salman, A. Kanigel, K. Segawa, Y. Ando *et al.*, *Phys. Rev. B* **91**, 161306 (2015).
- [55] A. Polyakov, H. L. Meyerheim, E. D. Crozier, R. A. Gordon, K. Mohseni, S. Roy, A. Ernst, M. G. Vergniory, X. Zubizarreta, M. M. Otrokov *et al.*, *Phys. Rev. B* **92**, 045423 (2015).
- [56] Z. Liu, X. Wei, J. Wang, H. Pan, F. Ji, M. Ye, Z. Yang, and S. Qiao, *Phys. Rev. B* **92**, 100101 (2015).
- [57] A. Golnik, E. Albert, M. Hamma, E. Westhauser, A. Weidinger, and E. Recknagel, *Hyperfine Interactions* **31**, 375 (1986).
- [58] E. J. Ansaldo, D. R. Noakes, J. H. Brewer, S. R. Kreitzman, and J. K. Furdyna, *Phys. Rev. B* **38**, 1183 (1988).
- [59] R. S. Hayano, Y. J. Uemura, J. Imazato, N. Nishida, K. Nagamine, T. Yamazaki, Y. Ishikawa, and H. Yasuoka, *J. Phys. Soc. Jpn.* **49**, 1773 (1980).
- [60] T. Lancaster, F. Xiao, Z. Salman, I. O. Thomas, S. J. Blundell, F. L. Pratt, S. J. Clark, T. Prokscha, A. Suter, S. L. Zhang *et al.*, *Phys. Rev. B* **93**, 140412 (2016).
- [61] R. Zimmermann, R. Claessen, F. Reinert, P. Steiner, and S. Hüfner, *J. Phys. Condens. Matter* **10**, 5697 (1998).
- [62] K. He, Y. Wang, and Q.-K. Xue, *Natl. Sci. Rev.* **1**, 38 (2014).
- [63] S. C. van der Marck, *Phys. Rev. E* **55**, 1514 (1997).
- [64] K. Sato, L. Bergqvist, J. Kudrnovský, P. H. Dederichs, O. Eriksson, I. Turek, B. Sanyal, G. Bouzerar, H. Katayama-Yoshida, V. A. Dinh *et al.*, *Rev. Mod. Phys.* **82**, 1633 (2010).