



MIT Open Access Articles

Proof of Tacticity of Stereoregular ROMP Polymers through Post Polymerization Modification

The MIT Faculty has made this article openly available. **Please share** how this access benefits you. Your story matters.

Citation	Hyvl, Jakub; Autenrieth, Benjamin and Schrock, Richard R. "Proof of Tacticity of Stereoregular ROMP Polymers through Post Polymerization Modification." <i>Macromolecules</i> 48, no. 9 (May 2015): 3148–3152. © 2015 American Chemical Society
As Published	http://pubs.acs.org/doi/abs/10.1021/acs.macromol.5b00477
Publisher	American Chemical Society (ACS)
Version	Author's final manuscript
Citable link	http://hdl.handle.net/1721.1/108291
Terms of Use	Article is made available in accordance with the publisher's policy and may be subject to US copyright law. Please refer to the publisher's site for terms of use.

Proof of Tacticity of Stereoregular ROMP Polymers Through Post Polymerization Modification

Jakub Hyvl, Benjamin Autenrieth, and Richard R. Schrock*

*Department of Chemistry 6-331, Massachusetts Institute of Technology, Cambridge,
Massachusetts 02139*

Abstract

Partial bromination or epoxidation has been used to prove the tacticities of several stereoregular polymers made through ROMP methods with well-defined Mo or W initiators. Tacticities were proven for *cis,isotactic* and *cis,syndiotactic* poly(norbornene), poly(3-methyl-3-phenylcyclopropene), and poly(*endo,anti*-tetracyclododecene). Various limitations can prevent application of these proofs in general to stereoregular polymers prepared through ROMP.

INTRODUCTION

Ring-opening metathesis polymerization (ROMP) is a powerful method for the synthesis of polymers.¹ It is most desirable that the structures so obtained be stereoregular, because desirable polymer properties (*e.g.*, crystallization) often then emerge. In the last several years we have been developing molybdenum and tungsten catalysts for stereospecific (*cis*) ROMP, *i.e.*, initiators that yield polymers with all *cis* C=C bonds and that have an *isotactic* or *syndiotactic* relationship between neighboring monomer units (dyads) in the polymer.² Tacticities can be determined readily if the polymers are made from an enantiomerically pure monomer, *e.g.*, enantiomerically pure dicarboalkoxynorbornadienes (2,3-(CO₂R*)₂-norbornadiene where R* = (1*R*, 2*S*, 5*R*)-(-)-menthyl or (R)-(-)-pantolactonyl) or disubstituted norbornenes (2,3-dicarbomethoxynorborn-5-ene, 2,3-dimethoxymethylnorborn-5-ene, and 5,6-dimethylnorborn-2-ene).^{3,4} A chiral element breaks the symmetry (a plane or a C₂-axis) that interconverts two backbone olefinic protons in a *cis, isotactic* or a *cis, syndiotactic* backbone structure and allows the two tacticities to be distinguished directly through homonuclear (proton/proton) correlation spectroscopy and decoupling experiments, as shown in Figure 1. This approach proves the structure of the chiral derivative (*e.g.*, carbomenthoxyl), but not necessarily an achiral analog (*e.g.*, carbomethoxyl).⁴

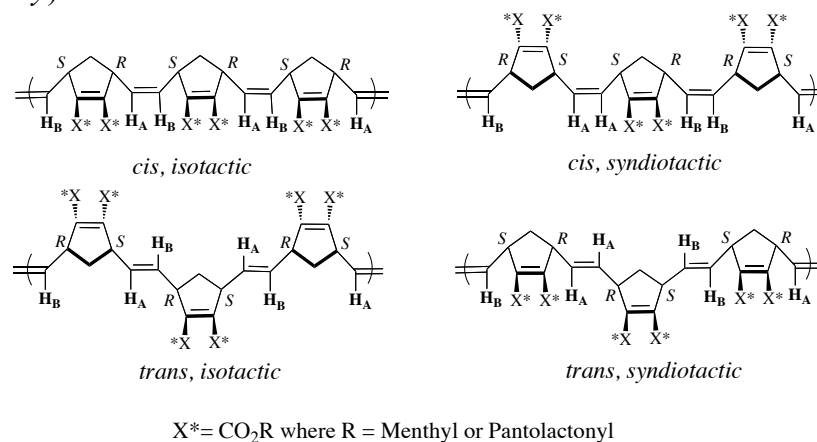


Figure 1. The four stereoregular structures of menthyl and pantolactonyl ester derivatives of polymers prepared through ROMP of 2,3-dicarboalkoxynorbornadienes.

Recently we evaluated a variety of well-defined Mo-based and W-based alkylidene initiators for the stereoselective polymerization of norbornene (NBE),⁵ *endo,anti*-tetracyclododecene (TCD),⁵ *endo*-dicyclopentadiene (DCPD),⁶ and enantiomerically pure methyl-N-(1-phenylethyl)-2-azabicyclo[2.2.1]hept-5-ene-3-carboxylate,⁷ to give *cis, isotactic* or

cis,syndiotactic structures. What are proposed to be *cis,isotactic* polymers made from achiral monomers (>98%) are prepared employing certain Mo and W imido alkylidene initiators that contain a chiral, racemic, C_2 -symmetric biphenolate ligand; an example is **1** in Figure 2. The chiral biphenolate ligand is proposed to force the monomer to add repeatedly to the same face of each M=C bond that is formed in the polymerization process (enantiomorphic site control). More recently, *cis,syndiotactic* polymers have been prepared from monoaryloxide pyrrolide initiators; an example is **2** in Figure 2. These initiators enforce *syndiotacticity* through "stereogenic metal control" as a consequence of the monomer adding *trans* to the pyrrolide and the chirality at the metal inverting with each addition of monomer. Under these circumstances the monomer adds alternately to one M=C face and then the other.^{2,8} The initiators in Figure 2 are examples from a much large selection of catalysts that were evaluated for the polymerization of NBE,⁵ TCD,⁵ and DCPD.⁶ Initiator **1** yielded *cis,isotactic* polymers from all three monomers (NBE,⁵ TCD,⁵ and DCPD⁶), while **2** yielded *cis,syndiotactic* polymers from all three monomers. It seems unlikely that many catalysts will be found that yield >98% *cis,syndiotactic* or >98% *cis,isotactic* polymers from a large and diverse collection of monomers, although that remains to be determined. Highly stereoregular polymers prepared from NBE, TCD, or DCPD have been hydrogenated to yield highly crystalline, relatively tactic saturated polymers.⁹

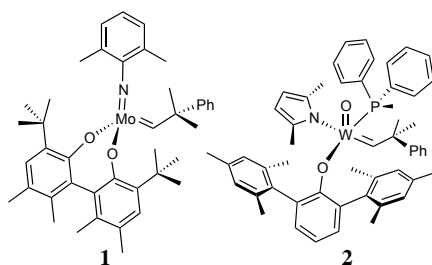


Figure 2. Examples of initiators for stereoselective ROMP reactions.


It occurred to us that post-polymerization modification (PPM) of backbone C=C bonds might be a valuable approach for identifying the tacticity of a stereoregular polymer prepared from an achiral monomer through ROMP methods. We devised two PPM approaches for proving the tacticity of stereoregular polymers prepared from NBE, TCD, and 3-methyl-3-phenylcyclopropene (MPCP). We found that the tacticities of all three polymers could be proven and are in agreement with predictions.

RESULTS AND DISCUSSION


The first two requirements for a tacticity proof employing a PPM method are that the polymer be essentially a single structure and that the PPM method be strictly stereospecific. Bromination and epoxidation are examples of stereospecific reactions at C=C bonds that proceed in strictly an *anti* and *syn* manner, respectively. Other requirements for a successful identification of tacticity of a stereoregular polymer include (i) modification of only a small percentage of C=C bonds in order that the resulting modified double bond remains in a homogeneous polymer environment; (ii) being able to observe (through proton NMR methods) the small percentage of protons in the modified polymer; (iii) compatibility of the PPM method with any functionality that is present; (iv) stability of the modified polymer; and (v) sufficient solubility of the polymer for NMR studies. Although failure of one or more of these five requirements has limited the generality of the PPM approach for determining the structure of *all* stereoregular polymers that we have tried, we have proven that both bromination and epoxidation are successful methods for a selected number of polymers. These methods therefore are *potentially* applicable to determination of tacticity in other stereoregular polymers prepared through ROMP.

Bromination of poly(norbornene)

Bromine addition to a C=C double bond proceeds in an *anti* fashion. All possible structures that can be made through bromine addition to *cis,tactic* and *trans,tactic* poly(NBE) (NBE = norbornene) are depicted in Schemes 1 and 2, respectively. Protons H_A and H_B in the resulting BrCHCHBr unit(s) are inequivalent and therefore distinguishable by ¹H NMR methods. Bromine addition to *cis,isotactic* poly(NBE) and *trans,syndiotactic*-poly(NBE) generates protons H(1',6')_A and H(1',6')_B, that are coupled to each other. If their chemical shifts are sufficiently different, it could be shown that they are correlated in a ¹H,¹H gCOSY experiment. Bromine addition to *cis,syndiotactic* poly(NBE) and *trans,isotactic* poly(NBE) generates protons H(1',6')_A and H(1',6')_B in different BrCHCHBr units that should not be correlated in a ¹H-¹H gCOSY experiment. Therefore, if the polymer is stereoregular and it can be determined whether it is all *cis* or all *trans* through IR studies, and the requirements stated in the above paragraph are all satisfied, then it may be possible to determine the tacticity through bromination. If two stereoregular polymers both have either a *cis* or *trans* stereochemistry it is necessary only to prove the tacticity of one in order to prove them both.

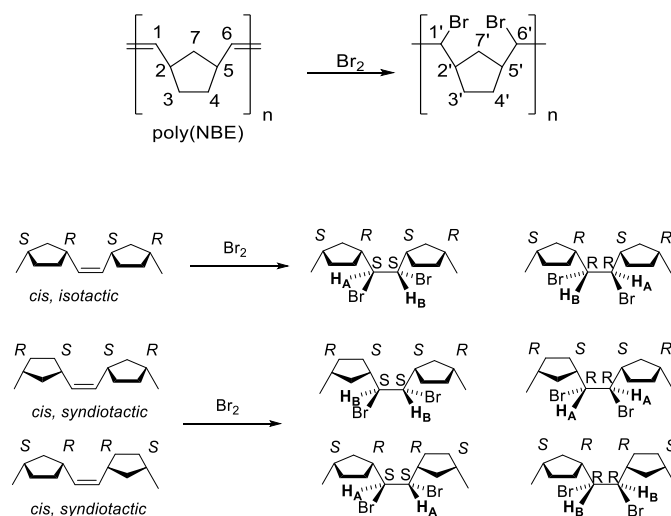

Scheme 1. Bromination of backbone double bonds in *cis, isotactic*-poly(NBE) and *cis, syndiotactic*-poly(NBE).

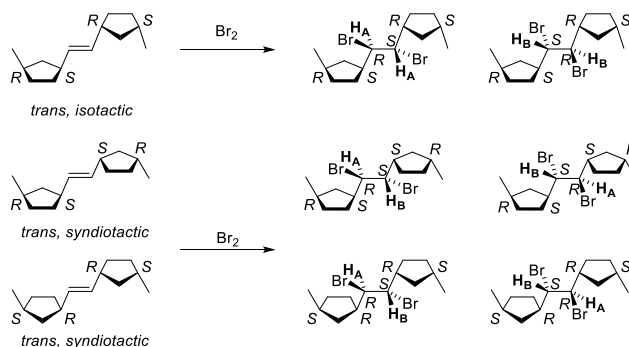

Scheme 2. Bromination of backbone double bonds in *trans, isotactic*-poly(NBE) and *trans, syndiotactic*-poly(NBE).

Only recently has it been shown that both *cis, syndiotactic*-poly(NBE) and *cis, isotactic*-poly(NBE) samples⁵ can be prepared and can be distinguished from one another through NMR methods. Samples of each polynorbornene were brominated to an extent of ~3% through dropwise addition of a solution of bromine in 0.5 mL of CDCl₃ to a stirred solution of polymer (20 mg, 0.212 mmol) in 0.8 mL of CDCl₃. Slow addition of bromine to a rapidly stirred solution produced polymers with the sharpest NMR spectra, probably because BrCHCHBr units are then essentially isolated throughout the stereoregular polymer. Proton NMR analyses of all samples were undertaken without further workup.

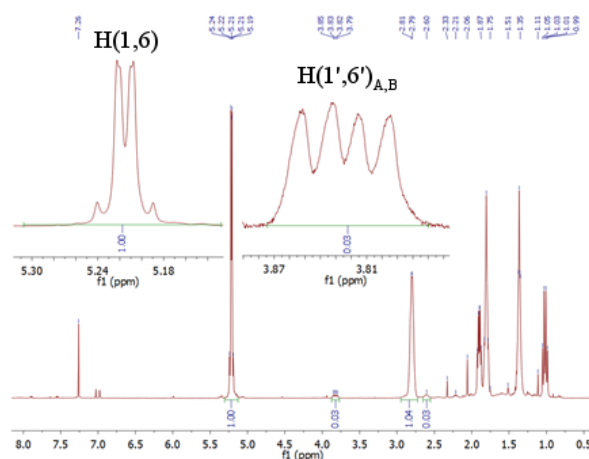


Figure 3. ^1H NMR spectrum of partially brominated (3 % conversion) *cis,syndiotactic* poly(NBE).

In the case of bromination of *cis,syndiotactic*-poly(NBE), doublets for $\text{H}(1',6')_{\text{A}}$ ($J_{1',2'} = 10.0$ Hz) at 3.84 ppm and $\text{H}(1',6')_{\text{B}}$ ($J_{1',2'} = 9.9$ Hz) at 3.81 ppm were found in the area typical for α -hydrogens in bromoalkanes (near 3.83 ppm, Figure 3). The resonance at 2.60 ppm is assigned to the methine protons $\text{H}(2',5')$ in the brominated double bonds. When the resonance for protons $\text{H}(2',5')$ was irradiated, singlets were observed for $\text{H}(1',6')_{\text{A}}$ at 3.84 ppm and $\text{H}(1',6')_{\text{B}}$ at 3.81 ppm (Figure 4). The $^1\text{H}, ^1\text{H}$ gCOSY showed that $\text{H}(1',6')_{\text{A}}$ and $\text{H}(1',6')_{\text{B}}$ are not coupled (Figures S1-S2). Therefore, these experiments prove that the structure prior to bromination is *cis,syndiotactic* (Scheme 1), as proposed.

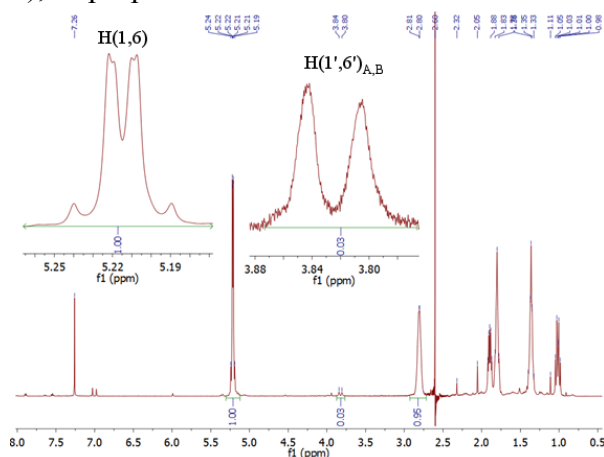


Figure 4. ^1H NMR spectrum of partially brominated (3 % conversion) *cis,syndiotactic* poly(NBE) with decoupling of the methine protons $\text{H}(2',5')$ at 2.60 ppm.


The proton NMR spectrum of partially brominated *cis,isotactic*-poly(NBE) revealed a broad doublet corresponding to the $\text{H}(1',6')_{\text{A}}$ and $\text{H}(1',6')_{\text{B}}$ protons at 3.83 ppm. Selective

decoupling of the methine protons H(2',5') at 2.60 ppm did not yield a significantly more resolved spectrum (see the SI, Figures S3 and S4), nor did spectra at several other temperatures. Therefore, this bromination is inconclusive. However, a proof of the *cis, isotactic* structure would be redundant since the *cis, syndiotactic* structure has been proven.

Epoxidation of poly(3-methyl-3-phenylcyclopropene) (MPCP)

3-Methyl-3-phenylcyclopropene (MPCP) has been polymerized with initiators of the type Mo(NAd)(CHCMe₂Ph)(pyrrolide)(OHIPT) (Ad = 1-adamantyl, OHIPT = 2,6-Mesityl₂C₆H₃) to give what was proposed to be *cis, syndiotactic*-poly(MPCP),^{8d} while what has been proposed to be *cis, isotactic*-poly(MPCP)¹⁰ has been prepared with initiators of the type Mo(NAr)(CHCMe₂Ph)(biphenolate) (Ar = 2,6-*i*-Pr₂C₆H₃). On the basis of an absence of a relatively intense IR peak in the region 970-980 cm⁻¹ a *cis* configuration was assigned to these two stereoregular polymers.^{8d}

All possible structures of partially epoxidized *cis, tactic*-poly(MPCP) (MPCP = methylphenylcyclopropene) are shown in Scheme 3. Epoxidation of *cis, syndiotactic*-poly(MPCP) should generate an epoxide with two inequivalent protons, H(1',10')_A and H(1',10')_B, that are coupled to each other, while epoxidation of *cis, isotactic*-poly(MPCP) should generate protons, H(1',10')_A and H(1',10')_B, that are in different epoxides. Because the two C=C faces are different in *cis, isotactic*-poly(MPCP), the two inequivalent protons are not likely to be found in a ratio of 1:1.

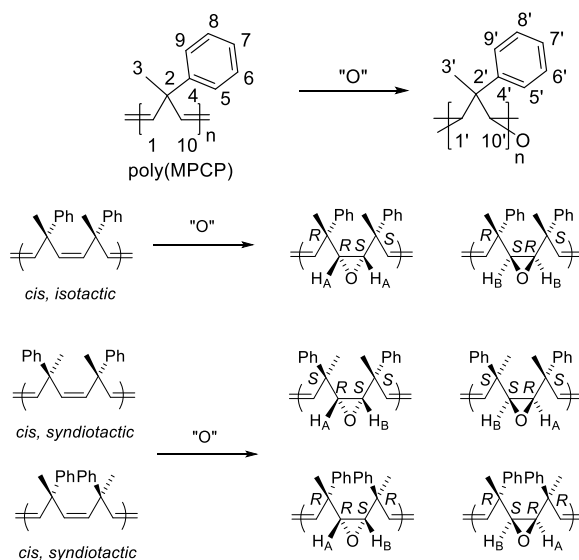

Scheme 3. Epoxidation of the backbone double bonds in *cis, isotactic* and *cis, syndiotactic* poly(MPCP).

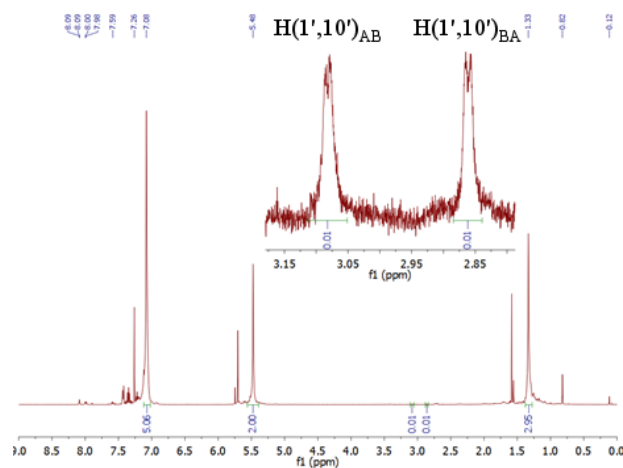


Figure 5. ^1H NMR spectrum of lightly epoxidized ($\sim 1\%$) *cis,syndiotactic*-poly(MPCP).

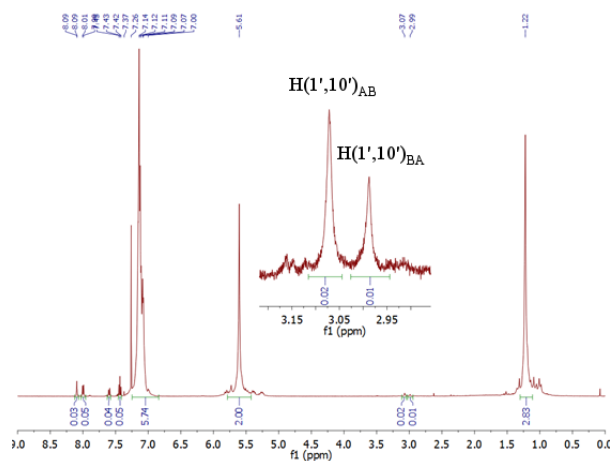


Figure 6. ^1H NMR spectrum of lightly epoxidized ($\sim 1.5\%$) *cis,isotactic*-poly(MPCP).

Stereoregular *cis*-poly(MPCP) samples were epoxidized to the extent of $\sim 1\%$ through addition of *m*-CPBA (*m*-chloroperoxybenzoic acid) to the solution of polymer (10 mg, 0.077 mmol) in 1.0 mL of CDCl_3 . Resolution of the epoxide protons in ^1H NMR spectra was less satisfactory in samples with $>1\%$ epoxidation. All samples were stirred for fourteen hours and examined without further workup. In the proton NMR spectrum of the epoxidized *cis,syndiotactic*-poly(MPCP) doublets were observed for $\text{H}(1',10')_{\text{A}}$ ($J_{\text{AB}} = 4.0$ Hz) at 3.09 ppm and $\text{H}(1',10')_{\text{B}}$ ($J_{\text{AB}} = 4.0$ Hz) at 2.86 ppm, the region typical for α -hydrogens in epoxides (Figure 5); the two protons are coupled by 4.0 Hz, as confirmed in a $^1\text{H},^1\text{H}$ gCOSY spectrum (Figures S5 and S6 in SI). These results prove that the polymer is *cis,syndiotactic*-poly(MPCP), as proposed.

In the proton NMR spectrum of $\sim 1.5\%$ epoxidized *cis,isotactic*-poly(MPCP) two singlets,


$H(1',10')_A$ at 3.09 ppm and $H(1',10')_B$ at 2.86 ppm in a ratio of approximately 2:1, were found in the region typical for α -hydrogens of the epoxide ring (Figure 6). A $^1H,^1H$ gCOSY spectrum showed that these two protons are not coupled (Figures S7 and S8 in SI). These results prove that the sample is *cis, isotactic*-poly(MPCP), as proposed. Being able to prove both the *cis, syndiotactic* and *cis, isotactic* structures of poly(MPCP) is satisfying, although a proof of both is again redundant.


Epoxidation of poly(*endo, anti*-tetracyclododecene)

Like norbornene, *endo, anti*-tetracyclododecene (TCD) has been polymerized stereoselectively to give what are proposed to be *cis, syndiotactic*-poly(TCD) and *cis, isotactic*-poly(TCD).⁵ All possible structures of epoxidized C=C bonds of *cis, tactic*-poly(TCD) are shown in Scheme 4. Epoxidation of *cis, syndiotactic*-poly(TCD) generates an epoxide with two inequivalent protons, $H(1',6')_A$ and $H(1',6')_B$, that are coupled to each other, while epoxidation of *cis, isotactic*-poly(TCD) generates different epoxides with equivalent protons, $H(1',6')_A$ and $H(1',6')_B$. The epoxidation reactions were performed in a manner analogous to the epoxidation of poly(MPCP) (*vide supra*).

Evaluation of proton NMR spectra of the lightly epoxidized samples of poly(TCD) is complicated by significant overlap of the proton resonances of interest ($H(1',6')$) in the epoxide with protons $H(2,5)$ (at 2.95 ppm, Figure 7). Although the analysis consequently is not as convincing as that for the partially epoxidized poly(MPCP) above, the data for poly(MPCP) helps convince us that the analysis for poly(TCD) is correct. Overlap of resonances is one typical complication in the use of PPM as a general method for analyzing tacticity of ROMP polymers.

The proton NMR sample of partially epoxidized *cis, syndiotactic*-poly(TCD) (7%) revealed two multiplets, $H(1',6')_A$ at 3.05 ppm and $H(1',6')_B$ at 3.00 ppm in the region typical for α -hydrogen chemical shifts of epoxide protons (Figure 7). Selective decoupling of the methine protons $H(2',5')$ at 1.90 ppm afforded two broad multiplets for $H(1',6')_A$ and $H(1',6')_B$ (Figure 8);

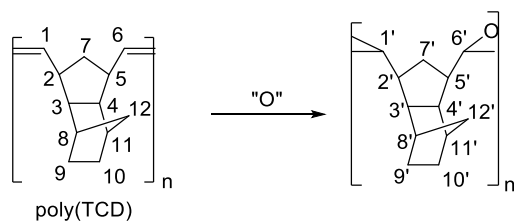

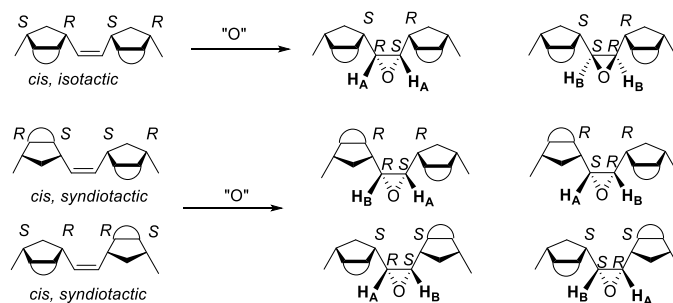

Scheme 4. Epoxidation of backbone double bonds in *cis, isotactic* and *cis, syndiotactic* poly(TCD).

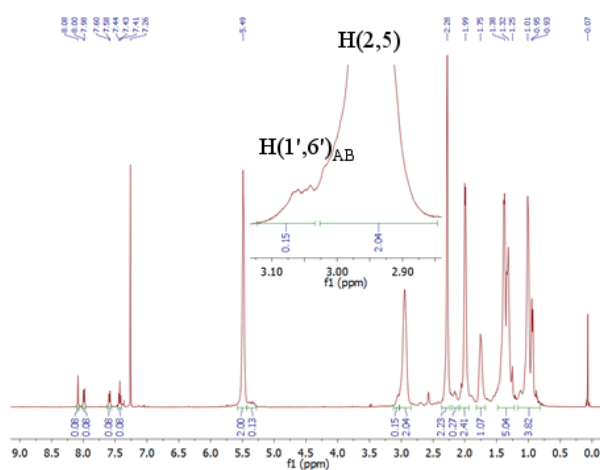


Figure 7. The ¹H NMR spectrum of epoxidized (7%) *cis,syndiotactic*-poly(TCD).

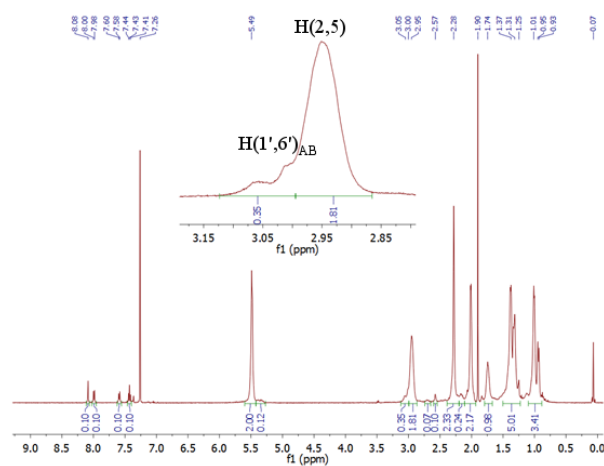


Figure 8. The ¹H NMR spectrum of epoxidized (7%) *cis,syndiotactic*-poly(TCD) with selective decoupling of the methine protons at 1.90 ppm.

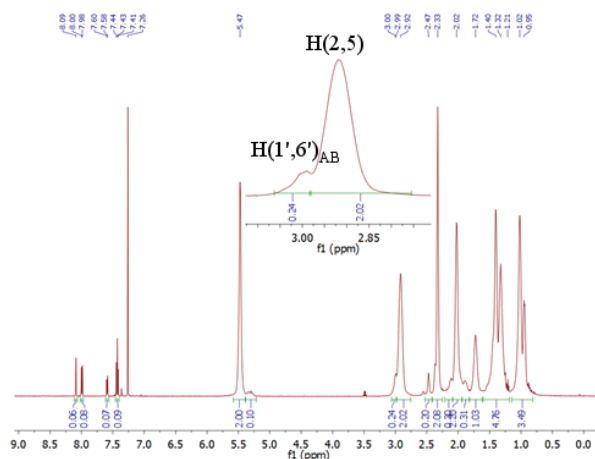


Figure 9. ^1H NMR spectrum of epoxidized (11%) *cis, isotactic*-poly(TCD).

a $^1\text{H}, ^1\text{H}$ gCOSY spectrum showed them to be coupled (Figures S9 and S10 in SI). Therefore, the structure of *cis, syndiotactic*-poly(TCD) is proven.

The proton NMR sample of partially epoxidized *cis, isotactic*-poly(TCD) (11%) revealed two multiplets, $\text{H}(1',6')\text{A}$ at 3.04 ppm and $\text{H}(1',6')\text{B}$ at 3.00 ppm, which are in the region typical for α -protons in epoxides (Figure 9). Selective decoupling of the methine protons $\text{H}(2',5')$ at 1.89 ppm led to two broad multiplets for $\text{H}(1',6')\text{A}$ and $\text{H}(1',6')\text{B}$ (Figure 10); a $1\text{H}, 1\text{H}$ gCOSY spectrum showed that protons A and B were not coupled to each other (Figures S11 and S12 in SI). Therefore, the structure of *cis, isotactic*-poly(TCD) is proven.

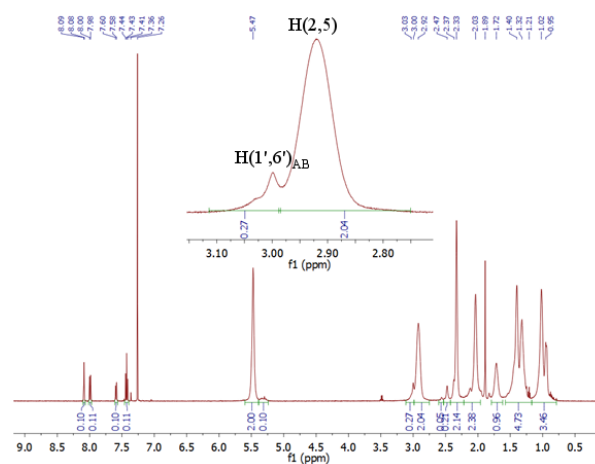


Figure 10. ^1H NMR spectrum of epoxidized (11%) *cis, isotactic*-poly(TCD) with selective decoupling of methine proton $\text{H}(2',5')$ at 1.89 ppm.

CONCLUSIONS

The tacticities of three *cis*, tactic polymers made with well-defined initiators (**1** and **2**) that have been proposed to give *cis, isotactic* and *cis, syndiotactic* polymers from achiral monomers have been proven through post polymerization modification. The two methods, bromination and epoxidation, are complementary. Although we have found that each method has its limitations, depending upon circumstances, as outlined in the beginning of this paper, each should prove useful as a means of determining tacticities of some stereoregular *cis* polymers prepared through ROMP. These methods should also allow the tacticities of *trans*, highly tactic polymers, to be determined, although pure *trans*, tactic polymers currently cannot be prepared through reliable methods.²

Acknowledgments. We are grateful to the Department of Energy (DE-FG02-86ER13564) for research support. J. H. thanks the Experientia Foundation for a one year postdoctoral fellowship.

Supporting Information Available. Experimental details for the synthesis of various polymers and NMR spectra of all polymers. This material is available free of charge via the Internet at <http://pubs.acs.org>.

References

¹ (a) Ivin, K. J.; Mol, J. C. *Olefin Metathesis and Metathesis Polymerization*; Academic Press: San Diego, 1997. (b) Ivin, K. J. *Olefin Metathesis*; Academic Press: San Diego, 1983. (c) Buchmeiser, M. R. *Chem. Rev.* **2000**, *100*, 1565. (d) Bielawski, C. W.; Grubbs, R. H. *Prog. Poly. Sci.* **2007**, *32*, 1. (e) Smith, E.; Pentzer, E. B.; Nguyen, S. T. *Polym. Rev.* **2007**, *47*, 419. (f) Buchmeiser, M. R. *Chem. Rev.* **2009**, *109*, 303. (g) Grubbs, R. H., Ed., *Handbook of Metathesis*; Wiley-VCH: Weinheim, 2003; Vols. 1 and 2.

² (a) Schrock, R. R. *Dalton Trans.* **2011**, *40*, 7484. (b) Schrock, R. R. *Acc. Chem. Res.* **2014**, *47*, 2457.

³ O'Dell, R.; McConville, D. H.; Hofmeister, G. E.; Schrock, R. R. *J. Am. Chem. Soc.*, **1994**, *116*, 3414.

⁴ Forrest, W. P.; Weis, J. G.; John, J. M.; Axtell, J. C.; Simpson, J. H.; Swager, T. M.; Schrock, R. R. *J. Am. Chem. Soc.* **2014**, *136*, 10910.

⁵ Autenrieth, B.; Schrock, R. R. *Macromolecules* **2015**, asap April 7, 10.1021/acs.macromol.5b00161.

⁶ Autenrieth, B.; Jeong, H.; Forrest, W. P.; Axtell, J. C.; Ota, A.; Lehr, T.; Buchmeiser, M. R.; Schrock, R. R. *Macromolecules* **2015**, in press.

⁷ Jeong, H.; Ng, V. W. L.; Börner, J.; Schrock, R. R. *Macromolecules* **2015**, asap March 17, DOI 10.1021/acs.macromol.5b00264.

⁸ (a) Flook, M. M.; Jiang, A. J.; Schrock, R. R.; Müller, P.; Hoveyda, A. H. *J. Am. Chem. Soc.* **2009**, *131*, 7962. (b) Jeong, H.; Kozera, D. J.; Schrock, R. R.; Smith, S. J.; Zhang, J.; Ren, N.; Hillmyer, M. A. *Organometallics* **2013**, *32*, 4843. (c) Flook, M. M.; Börner, J.; Kilyanek, S.; Gerber, L. C. H.; Schrock, R. R. *Organometallics* **2012**, *31*, 6231. (d) Flook, M. M.; Gerber, L. C. H.; Debelouchina, G. T.; Schrock, R. R. *Macromolecules* **2010**, *43*, 7515. (e) Flook, M. M.; Ng, V. W. L.; Schrock, R. R. *J. Am. Chem. Soc.* **2011**, *133*, 1784. (f) Forrest, W. P.; Axtell, J. C.; Schrock, R. R. *Organometallics* **2014**, *33*, 2313.

⁹ (a) Hayano, S.; Nakama, Y. *Macromolecules* **2014**, *47*, 7797. (b) Hayano, S.; Kurakata, H.; Tsunogae, Y.; Nakayama, Y.; Sato, Y.; Yasuda, H. *Macromolecules* **2003**, *36*, 7422.

¹⁰ Singh, R.; Schrock, R. R. *Macromolecules* **2008**, *41*, 2990.

TOC for

Proof of Tacticity of Stereoregular ROMP Polymers Through Post Polymerization Modification

Jakub Hyvl, Benjamin Autenrieth, and Richard R. Schrock*

