

MIT Open Access Articles

*Active Radiative Thermal Switching
with Graphene Plasmon Resonators*

The MIT Faculty has made this article openly available. *Please share*
how this access benefits you. Your story matters.

Citation: Ilic, Ognjen et al. "Active Radiative Thermal Switching with Graphene Plasmon Resonators." ACS Nano 12, 3 (March 2018): 2474–2481 © 2018 American Chemical Society

As Published: <http://dx.doi.org/10.1021/ACSNANO.7B08231>

Publisher: American Chemical Society (ACS)

Persistent URL: <https://hdl.handle.net/1721.1/121276>

Version: Author's final manuscript: final author's manuscript post peer review, without publisher's formatting or copy editing

Terms of Use: Article is made available in accordance with the publisher's policy and may be subject to US copyright law. Please refer to the publisher's site for terms of use.



Active Radiative Thermal Switching with Graphene Plasmon Resonators

Ognjen Ilic,¹ Nathan H. Thomas,² Thomas Christensen,³ Michelle C. Sherrott,¹ Marin Soljačić,³ Austin J. Minnich,² Owen D. Miller,⁴ and Harry A. Atwater¹

¹*Department of Applied Physics and Materials Science, California Institute of Technology, Pasadena, CA 91125, USA*

²*Division of Engineering and Applied Science, California Institute of Technology, Pasadena, CA 91125, USA*

³*Department of Physics, Massachusetts Institute of Technology, Cambridge, MA 02139, MA, USA*

⁴*Department of Applied Physics and Energy Sciences Institute, Yale University, New Haven, CT 06511, USA*

ABSTRACT

We theoretically demonstrate a near-field radiative thermal switch based on thermally excited surface plasmons in graphene resonators. The high tunability of graphene enables substantial modulation of near-field radiative heat transfer, which, when combined with the use of resonant structures, overcomes the intrinsically broadband nature of thermal radiation. In canonical geometries, we use nonlinear optimization to show that stacked graphene sheets offer improved heat conductance contrast between “ON” and “OFF” switching states, and that a >10x higher modulation is achieved between isolated graphene resonators than for parallel graphene sheets. In all cases, we find that carrier mobility is a crucial parameter for the performance of a radiative thermal switch. Furthermore, we derive shape-agnostic analytical approximations for the resonant heat transfer that provide general scaling laws and allow for direct comparison between different resonator geometries dominated by a single mode. The presented scheme is relevant for active thermal management and energy harvesting as well as probing excited-state dynamics at the nanoscale.

Keywords: graphene, thermal radiation, near-field radiative heat transfer, surface plasmon

Radiative heat transfer on the nanoscale holds promise for next-generation energy conversion technologies, including heat-to-electricity conversion platforms such as near-field thermophotovoltaics and near-field solid-state refrigeration. A key enabler is the idea that closely separated objects at different temperatures—*i.e.* objects at separation distances much smaller than the characteristic thermal wavelength—can exhibit order-of-magnitude increases in the radiatively exchanged power relative to the power that can be transferred in the far field. While the early work on near-field radiative heat transfer (NF-RHT) focused on the thermal energy exchange between conducting plates,^{1,2} the advancements in nanofabrication have led to experimental demonstrations of NF-RHT in a number of configurations.^{3–17} Among recent studies, radiative nanoscale energy transfer has been investigated in metasurfaces,¹⁸ non-

1
2
3 reciprocal systems and systems with gain,^{19,20} van der Waals stacks,²¹ and for concepts such as
4 luminescent refrigeration,²² thermal extraction,²³ thermal rectification and amplification,^{24–27} and radiative
5 heat transfer limits.^{28–30}
6

7 A key functionality central to the application of NF-RHT is a means of *active* heat transfer
8 control—a scheme whereby external parameters can dynamically modulate the radiative flux between
9 objects without necessitating a temperature change. The challenge of realizing such a thermal switch is
10 two-fold: (1) the broadband spectrum of thermal radiation makes it difficult to modulate the radiative heat
11 transfer to a significant degree, and (2) such a switch must comprise materials with tunable emissivity at a
12 fixed temperature. Here, we propose use of coupled graphene resonators as a means to overcome both
13 challenges; their highly tunable optical properties allow for constant-temperature operation, and provide a
14 means to dramatically modulate NF-RHT despite the broadband nature of thermal radiation. In contrast to
15 their bulk counterparts, low-dimensional plasmonic materials such as graphene exhibit highly tunable
16 optical properties when electrically biased. Moreover, graphene supports strongly confined surface
17 plasmons in the technologically important thermal IR spectral range. Finally, graphene combines a strong
18 optical response with low losses, endowing it with the largest optical response of known plasmonic
19 materials.³⁰ Jointly, these attributes have sparked a significant interest in the study of plasmon-mediated
20 NF-RHT in graphene.^{31–40}
21

22 In this work, we find that optimal combinations of resonator size and material properties,
23 specifically carrier concentration and relaxation rate, can enable large thermal switching ratios and high
24 levels of modulation sensitivity. The working principle behind thermal switching with plasmonic
25 graphene resonators is the ability to dynamically tune the modes of the resonances of the emitting and the
26 absorbing objects into and out of resonance. We illustrate the idea of a thermal switch in several relevant
27 configurations, including thermal switching between (a) graphene sheets, (b) multilayer graphene stacks,
28 (c) dipolar graphene resonators, and (d) hybrid resonator-multilayer structures (Fig. 1). In this radiative
29 heat transfer analysis with multiple configurations and inputs (*e.g.* temperature, distance, *etc.*), we
30 identify carrier mobility as a critical parameter in achieving a large contrast between the “ON” (maximal
31 heat transfer) and “OFF” (minimal heat transfer) states: higher mobility gives rise to sharper plasmonic
32 resonances that are more easily detuned. For each value of mobility, identifying the ON and OFF thermal
33 conductance states constitutes a nonlinear optimization problem over a parameter space of all allowable
34 gate voltages. We find that in all structures, ON states comprise similarly doped graphene structures—
35 where the individual plasmonic resonances of the two sides efficiently overlap—and where optimal Fermi
36 levels depend on carrier mobility and resonator size. For analyzed OFF states, we identify relevant
37 regimes that depend on carrier mobility. Finally, we derive analytical approximations that highlight the
38 relevant scaling laws and key parameters, and show that heat flux modulation is possible even with
39 graphene on infrared active substrates.
40
41
42
43
44
45
46
47
48
49
50

51 52 **RESULTS AND DISCUSSION**

53
54
55 The radiative energy flux exchanged between two structures of temperatures T_1 and T_2 is given by⁴¹
56
57
58
59
60

$$H_{1 \rightarrow 2} = \int_0^{\infty} d\omega [\theta(\omega, T_1) - \theta(\omega, T_2)] \Phi(\omega; T_1, T_2), \quad (1)$$

where $\theta(\omega, T) = \hbar\omega / [\exp(\hbar\omega/k_B T) - 1]$ is the mean energy of a photon, and Φ is the spectral transfer function which accounts for the geometry, shape, and (temperature-dependent) material properties of the two objects. In this work, we focus on the radiative thermal conductance (RTC) h between two structures, defined for a given temperature T as $h(T) = \lim_{T_1, T_2 \rightarrow T} H(T_1, T_2) / (T_1 - T_2) = \int_0^{\infty} d\omega \frac{\partial \theta}{\partial T}(\omega, T) \Phi(\omega, T)$. As a first step in our analysis, we examine the radiative heat transfer between two graphene sheets, as shown in Fig. 1a. For two parallel graphene sheets radiatively exchanging heat in the near field, and separated by a distance d , the spectral transfer function per unit area is^{33,34}

$$\Phi_{\text{sheets}}(\omega) = \frac{1}{\pi^2} \int_{\omega/c}^{\infty} dq q \frac{\text{Im}[r_1] \text{Im}[r_2]}{|1 - r_1 r_2 e^{2i\kappa d}|^2} e^{2i\kappa d}, \quad (2)$$

where q and κ are the in-plane and the perpendicular wave-vector, respectively ($\kappa = \sqrt{\omega^2/c^2 - q^2}$), and r_i is the reflection coefficient of the i -th sheet (related to the, generally nonlocal, graphene surface conductivity, see SI). In this configuration, the radiative thermal conductance h depends on several physical parameters: $h = h(E_i, \mu_i, T, d)$, where $E_i = (E_1, E_2)$ and $\mu_i = (\mu_1, \mu_2)$ denote the Fermi levels and carrier mobilities of the two sheets, respectively, T is the temperature, and d is the separation. Because both E_1, E_2 are actively tunable through electrostatic gating, our goal is to determine the optimal pairs $(E_1^{\text{on}}, E_2^{\text{on}})$ and $(E_1^{\text{off}}, E_2^{\text{off}})$ that correspond to the ON and OFF states, namely where $h_{\text{on}} \equiv h(E_1^{\text{on}}, E_2^{\text{on}})$ and $h_{\text{off}} \equiv h(E_1^{\text{off}}, E_2^{\text{off}})$. A thermal switch with excellent modulation ability will then have a high switching ratio $\eta = h_{\text{on}}/h_{\text{off}}$.

Figure 2a shows the maximum conductance h_{on} and the switching ratio η as a function of the carrier mobility. We assume equal mobilities $\mu_{1,2} = \mu$, and fix the temperature ($T = 300$ K) and the sheet separation ($d = 100$ nm). Carrier mobility quantifies the magnitude of optical losses in graphene and is related to the carrier relaxation time τ via the impurity-limited approximation $\tau = \mu E_F / e v_F^2$.⁴² For each value of mobility, we find the optimal $E_{1,2}^{\text{on}}$ and $E_{1,2}^{\text{off}}$ pairs in the allowable range $E_i \in [E_{\text{min}}, E_{\text{max}}]$. For the allowable range, we assume $E_{\text{min}} \sim k_B T$ and $E_{\text{max}} = 0.6$ eV, consistent with typical experimental gate voltages (we note that presented results are not sensitive to the choice of E_{min} , whether it is zero or $k_B T$). The $E_{1,2}^{\text{on}}$ and $E_{1,2}^{\text{off}}$ pairs are computed numerically using a (multi-start) local, derivative-free, optimization algorithm.⁴³⁻⁴⁵ For the case of two graphene sheets radiatively exchanging heat in Fig. 2a, we observe a peak in the maximum conductance h_{on} (solid black), implying the existence of an optimal optical loss rate which maximizes the heat transfer. The existence of *optimal loss* arises from the geometry of the problem. A parallel plate configuration, due to multiple reflections between the plates, does not achieve the optimal-absorber condition, exhibiting a heat transfer rate that is substantially weaker than the extended-structure limit.²⁹ Because of this, we do not expect the optical response and the heat transfer rate to monotonically increase with mobility (or, equivalently, decrease with mounting optical loss). For the parameters under analysis here, we find the optimal mobility for the case of two graphene sheets to be $\mu_{\text{opt}} \approx 1800$ cm²/Vs, and the corresponding radiative thermal conductance $h_{\text{on}}/h_{\text{bb}} \approx 340$ for $E_1^{\text{on}} =$

1
2
3 $E_2^{\text{on}} = 0.173$ eV. Here, the conductance is normalized to the far-field limit of radiatively coupled
4 blackbodies (with unity view factor) $h_{\text{bb}}(T) = \frac{d}{dT}(\sigma_{\text{SB}}T^4) = 4\sigma_{\text{SB}}T^3$, where σ_{SB} is the Stefan-Boltzmann
5 constant. We note that in all cases, the emitter–receiver symmetry ensures that the ON state comprises
6 equally doped graphene sheets ($E_1^{\text{on}} = E_2^{\text{on}}$), such that the resonances are aligned (Fig. 2c). For analyzed
7 OFF states, the carrier mobility is relevant. For low carrier mobility, maximal detuning of broad
8 plasmonic resonances is achieved at the extremes of the allowable range of Fermi levels. In contrast, for
9 higher carrier mobilities, once the plasmonic resonances are sufficiently detuned, the heat flux
10 suppression in the OFF state is reduced with further separation of the emitter/absorber Fermi levels due to
11 the onset of the interband transition in the lower-doped graphene structure (and the corresponding
12 additional contribution to the radiative heat transfer).
13
14
15
16

17 In contrast to the heat transfer rate, the switching ratio η monotonically increases with carrier
18 mobility (solid, red in Fig. 2a), which reduces the plasmonic linewidths and thus enables improved
19 detuning of resonances. We also observe (Fig. 2c) a cross-over value of mobility (~ 1300 cm²/Vs) that
20 separates the two regimes of η : for low mobility (*i.e.* broad resonances), the OFF state is achieved for the
21 end values of the range of allowable Fermi levels, namely $E_{1(2)}^{\text{off}} = E_{\text{min(max)}}$; in contrast, for higher
22 mobility $E_1^{\text{off}} > E_{\text{min}}$ and the switching ratio increases faster with increasing mobility. Despite the
23 multiple reflections in the parallel-plate geometry and the failure to achieve the optimal-absorber
24 condition, the switching ratio can be appreciable, reaching a value of $\eta \approx 8.5$ for $\mu = 10^3$ cm²/Vs (and
25 $\eta \approx 45$ for $\mu = 10^4$ cm²/Vs).
26
27
28
29

30 The concept of thermal switching using two graphene sheets can be further extended to parallel
31 graphene *stacks* (Fig. 1b). As an example, we focus on the near-field radiative heat transfer between a
32 single graphene sheet (object 1) and a stack comprising two graphene sheets in close proximity (object 2).
33 We fix the separation between the sheets in the second stack at $\delta = 10$ nm and object separation, as
34 before, at $d = 100$ nm. In this case, active modulation is achieved with parameters $E_i = (E_1, E_{21}, E_{22})$, as
35 sketched in Fig. 2a. Similar to the 2-sheet case, we also observe the existence of an optimal mobility that
36 maximizes the radiative thermal conductance (blue, dashed, in Fig. 2a). In addition, we note a slight
37 decrease ($\sim 20\%$) of h_{on} relative to the 2-sheet case, which can be attributed to the inability to achieve
38 perfectly resonant coupling in this asymmetric configuration. The condition for maximal RTC is reached
39 for a nearly-symmetric configuration $E_1 \sim E_{21}$ and $E_{22} \sim E_{\text{min}}$. Despite the optimal low carrier
40 concentration of the bottom sheet, its optical response is appreciable enough to detune the plasmonic
41 resonance, resulting in a decrease of h_{on} .
42
43
44
45
46

47 While the presence of the bottom sheet in the stack reduces the maximum heat transfer rate, it in
48 turn enables a noticeably larger switching ratio. The improved switching ratio arises from the h_{off}
49 suppression due to resonance blue-shift in the graphene stack. This effect is elucidated by examining the
50 local density of states (LDOS) above a layered stack. The LDOS at a point \mathbf{r} is proportional to the decay
51 rate of an (orientation-averaged) dipole at that point, given by⁴⁶ $\rho(\mathbf{r}, \omega) = (2\omega/\pi c^2)\text{Im}\{\text{Tr}[\vec{\mathbf{G}}(\mathbf{r}, \mathbf{r}, \omega)]\}$,
52 where $\vec{\mathbf{G}}$ is the dyadic Green function (SI). Fig. 3a shows the spectral LDOS above a graphene stack of N
53 identically doped sheets (of mutual, constant sheet-separation δ). For $N > 1$ the one-sheet plasmon
54
55
56
57
58
59
60

dispersion fractures into a set of N hybridized resonances, split into mutually bonding and anti-bonding modes, corresponding to low- and high-frequency branches. The principal LDOS contribution originates from the highest frequency branch. Normalizing the stack's LDOS to that of an individual sheet, we observe a substantially enhanced optical response at higher frequencies (Fig. 3b). Finally, Fig. 3c shows the (k, ω) dependence of the LDOS and the relevant higher order modes of the graphene stack. Together, these considerations further elucidate the previously noted blue shift of the two-sheet case with $E_{21,22}^{\text{off}} = E_{\text{max}}$ relative to the single sheet case with $E_2^{\text{off}} = E_{\text{max}}$. In summary, while the maximum thermal conductance h_{on} suffers from the introduction of the bottom sheet, the reduction is more than made up by the lower h_{off} , thus leading to an enhanced switching ratio η .

Moving beyond extended structures, we analyze radiative heat transfer between isolated graphene resonators, as shown in Fig. 1c. In the dipolar limit, the spectral transfer function for resonators 1 and 2 (normalized to resonator area A) can be expressed as $\Phi(\omega, d) = \frac{1}{8\pi^3} \frac{1}{d^6} \sum_{j \in \mathcal{F}} \lambda_j \text{Im}[\alpha_1^j] \text{Im}[\alpha_2^j] / A$ where d is the resonator separation distance, $\alpha_{1(2)}$ is the polarizability of resonator 1(2), and λ_j is a numerical pre-factor that depends on the relative orientation of the two resonators (SI). The polarizability connects the induced dipole moment $p(\omega) = \epsilon_0 \alpha(\omega) E_0$ with an external field E_0 , and can be expressed as the eigenmode sum⁴⁷

$$\alpha(\omega) = 2L^3 \sum_{\nu} \frac{\Delta_{\nu}}{\zeta_{\nu} - \zeta(\omega)}, \quad (3)$$

where the geometrical shape of a graphene resonator is captured by the normalized eigenfrequencies ζ_{ν} and the oscillator strengths Δ_{ν} . The size and the material-response dependence of the graphene resonator are embedded in the dispersive parameter $\zeta(\omega) = 2i\epsilon_0\epsilon\omega L/\sigma(\omega)$, where L is the characteristic length scale and $\sigma(\omega)$ is graphene's surface conductivity. For identical resonators ($\alpha_1 = \alpha_2$), assuming intraband (Drude) conductivity, we can approximate the ON state radiative thermal conductance (and the corresponding optimal Fermi levels) to emphasize the parameter dependencies as (SI)

$$h_{\text{ON}} \approx 116.23 \left(\frac{\epsilon_0 k_{\text{B}}^5 T^4}{2\pi \hbar^2 e^3 v_{\text{F}}^2} \right) \frac{1}{A} \frac{\lambda_{\text{S}}}{2} \mu \frac{L^7}{d^6} \frac{\Delta_1^2}{\zeta_1^3} \quad (4)$$

$$E_{\text{ON}} \approx 71.27 \left(\frac{\epsilon_0 \pi k_{\text{B}}^2 T^2}{e^2} \right) \frac{L}{\zeta_1}$$

which are valid assuming the optical response is dominated by a single (or a set of degenerate) mode(s) associated with ζ_1, Δ_1 from (3). Note, $\lambda_{\text{S}} \equiv \sum_{j \in \mathcal{F}} \lambda_j$ is the sum of all corresponding numerical pre-factors. For disk resonators of radius R , we associate $L \equiv \sqrt{A} = \sqrt{R^2 \pi}$, and give the relevant oscillator parameters in the SI. Figure 4 shows the normalized maximum thermal conductance $h_{\text{on}}/h_{\text{bb}}$ and the switching ratio η , for graphene disks of varying size (we assume disks are co-axial, hence $\lambda_{\text{S}} = 2$). We observe that the optimal doping ($E = E_{1,2}^{\text{on}}$) that maximizes the RTC is not particularly sensitive to mobility (Fig. 4b); instead, it is dependent on the resonator size, exhibiting a linear relationship with the disk radius R (in agreement with Eq. 4). The higher optimal doping would seem to imply weaker radiative conductance per unit area between larger disks at temperature T (due to a blue-shifted resonance frequency); nevertheless, the cubic dependence of polarizability on disk size leads to the overall increase of h_{on} with the disk size,

as shown in Fig. 4c. We make two remarks. First, while the RTC between identical disks of radius R is proportional to R^6 for *fixed* Fermi levels, the *optimal* conductance (*i.e.* the ON state) has a stronger (R^7) size dependence (Fig. S4b). Second, Eqs. (3) and (4) are shape-agnostic: they apply to graphene resonators other than disks, allowing for direct comparison between different resonator geometries. For example, using the values from Table S1 (SI), we can readily infer that square, triangular, or elliptical resonators would exhibit stronger on-resonance heat transfer than disks, for the same resonator area. For elliptical resonators, the enhancement arises from the fact that increasing the aspect ratio simultaneously increases the long-axis oscillator strength Δ_1 while reducing its eigenfrequency ζ_1 . For squares and triangles, the argument is more nuanced: both the polarizability and the eigenfrequency are lower relative to disks, but the latter has the stronger effect. Finally, sharp, geometry-dictated resonances lead to order-of-magnitude higher switching ratios relative to those in planar structures (Fig. 4d).

In addition to thermal switching in extended (sheets and multi-layer stacks) and dipolar (*e.g.* disks) structures, we also analyze a hybrid scenario that combines the two; for example a graphene disk above a single sheet (or a stack) as shown in Fig. 1d. The spectral transfer function of the configuration consisting of a dipolar nanostructure above a planar sheet can be expressed as

$$\Phi(\omega) = \frac{2\omega^2}{\pi c^2} \sum_{i=x,y,z} \text{Im}[\alpha_i(\omega)] \text{Im}[\vec{\mathbf{G}}(\omega, \mathbf{r}_0)]_{ii}, \quad (5)$$

where $\vec{\mathbf{G}}$ is the dyadic Green tensor of the planar interface (see SI). In the nonretarded limit ($q \gg k$) relevant to NF RHT, the expression for the spectral transfer function $\Phi(\omega)$ features terms proportional to $\text{Im}(\alpha)\text{Im}(r_p)$, where α is the resonator polarizability and r_p is the p-polarization (TM) reflection coefficient for the underlying sheet (SI). Fig. S3 shows the RTC enhancement and the switching ratio, assuming the polarizability of the disk is $\alpha = \sum_i \alpha_i \hat{n}_i = \alpha(1,1,0)^T$ where Eq. (3) applies for the scalar α . We observe that it is still possible to bring the disk and the sheet into resonance, as indicated by the very large possible switching ratios relative to the sheet/stack configuration of Fig. 2. In contrast to the latter, the inclusion of an additional layer in the stack does not appear to improve either the RHT enhancement or the switching ratio (Fig. S3, dashed). Attainable switching ratios would, in general, depend on the separation between graphene resonators. For the sheet-sheet configuration, Fig. S5 shows the switching ratio as a function of mobility, for different separations. We observe similar trends as before: namely, the switching ratio increases with mobility and that shorter separations are generally favorable due to the enhancement of the ON state conductance as sheets become closer. We note that for resonators in the dipolar limit both the ON and the OFF state energy fluxes scale in the same way with the separation d , making the switching ratio insensitive to separation.

Besides the heat transfer enhancement and the switching ratio, another relevant quantity for active modulation is the switching sensitivity. Here, we define the switching sensitivity as $\xi = k_B T / \min_i |E_i^{\text{on}} - E_i^{\text{on}/2}|$, a quantity that is proportional to the minimum change in any single Fermi level E_i that is needed to halve the maximum radiative conductance h_{on} . Figure 5 shows the sensitivity ξ for different values of mobility for the discussed configurations. In the disk-disk and the 2-sheet case, the ON state of the system is (due to symmetry) equally sensitive to changes in E_1 and E_2 . In the 3-sheet case (Fig

1
2
3 2., dashed), the most “sensitive” parameter is the doping of the top sheet (E_1); likewise, in the disk-sheet
4 case (Fig. S3, dashed) the doping of the disk (E_1) is the most sensitive. Similar to the switching ratio, the
5 sensitivity of switching increases with increasing graphene mobility, especially for the disk-disk heat
6 transfer characterized by sharp resonances.
7

8
9 Finally, we briefly characterize thermal switching with graphene sheets on substrates. The
10 simplest example comprises a sheet of graphene on a semi-infinite substrate of constant permittivity (*e.g.*
11 CVD diamond, $\epsilon \sim 5.8$). In that case, much of the analysis from Fig. 2 holds, with switching ratios
12 exhibiting similar mobility dependence, with generally lower magnitude due to stronger mode
13 confinement for $\epsilon > 1$. A more interesting extension includes the analysis of thermal switching in the
14 presence of IR active substrates (*i.e.* substrates that themselves support surface electromagnetic modes in
15 the mid-IR). For this case, we focus on SiO₂, SiC, and SiN_x, materials that exhibit surface phonon-
16 polaritons. As indicated in Fig. S6, these three materials can be characterized by both sharp and broad
17 resonances as well as by both low and high background permittivities. Figure 6 shows the switching ratio
18 η between two graphene sheets on substrates as a function of mobility. The substrates are identical and, as
19 before, we find optimal Fermi levels E_f that maximize/minimize the RTC. To emphasize the substrate
20 *versus* graphene contribution to RTC, we plot the switching ratio for different separation distances d .
21 From Fig. 6 we can draw several qualitative conclusions. As expected, for a given substrate, modulation
22 is generally stronger at smaller separations due to enhanced contribution of tightly-confined surface
23 modes in graphene. As a result, at smaller separations (where graphene response is more dominant)
24 higher mobility is still favored. In terms of the most suitable substrate material, silicon carbide appears to
25 provide the largest switching ratio of the analyzed substrates. We attribute this to its narrowest resonant
26 response (as indicated by its permittivity function, Fig. S6) that allows for stronger detuning of the heat
27 transfer in the presence of graphene.
28

29
30 At larger separations, where graphene response is less dominant, the effect of carrier mobility is
31 more nuanced. At a separation of $d = 400$ nm, we find graphene-on-SiO₂ to have the strongest switching
32 ratio. This is attributed to the (comparatively) low ϵ_{re} of SiO₂, giving rise to less strongly confined
33 surface modes that can more effectively modulate the RTC at such distances. This is the same reason why
34 SiO₂ outperforms SiN_x, and even optically inactive CVD diamond, as the substrate material. This implies
35 that, among polaritonic materials, SiO₂ may be a suitable substrate for RTC modulation at larger, more
36 experimentally accessible separations.
37
38
39
40
41
42
43
44
45
46

47 CONCLUSIONS

48
49
50 In this work, we proposed and demonstrated a radiative thermal switching scheme with graphene
51 plasmon nanoresonators in several relevant configurations. We showed that optimal combinations of
52 resonator size and carrier concentration give rise to strongly contrasting ON and OFF thermal
53 conductance states, and identified carrier mobility as a critical material parameter. In addition to
54 numerical optimizations, we derived analytical, shape-agnostic approximations that highlight parameter
55
56
57
58
59
60

1
2
3 dependence for resonant heat transfer and allow for direct comparison between different resonator
4 geometries. Finally, we characterized thermal switching and heat flux modulation of graphene on infrared
5 active substrates. Though the focus of this work is radiative flux modulation *via* the control of plasmonic
6 resonances in graphene, other reduced-dimensionality materials and other types of polaritons (phonon-
7 polariton, exciton-polariton, magnon, *etc.*) would exhibit similar radiative thermal emission
8 enhancements. In addition to electrostatic gating, other mechanisms, such as an imposed elastic strain,
9 offer another means for polariton resonance modulation. Because of its vanishing density of states at its
10 neutrality point, graphene exhibits exceptional tunability and is particularly suitable for radiative flux
11 modulation. The described active thermal switching may be relevant for applications that include near-
12 field thermophotovoltaic modulation, and cooling of electronic nano-devices. These results demonstrate
13 the potential of graphene-based plasmonic resonators for active thermal management on the nanoscale.
14
15
16
17
18
19
20

21 **COMPUTATIONAL METHODS**

22
23 Calculations in the present paper were performed by numerical evaluation of Equations (1-5). Unless
24 otherwise specified, optical conductivity of graphene is numerically obtained (for desired values of
25 frequency, Fermi energy, mobility, temperature) by summing the intraband and the interband
26 contributions (see, for example, Ref [47]). For optimizations, the Fermi energy pairs ($E_{1,2}^{\text{on}}$ and $E_{1,2}^{\text{off}}$) are
27 computed numerically using a (multi-start) local, derivative-free, optimization algorithms^{44,45}, accessed
28 *via* the NLOpt package.⁴³
29
30
31
32

33 **Acknowledgements**

34
35 O.I., N.H.T., M.C.S, A.J.M., and H.A.A. were supported as part of the DOE “Light-Material
36 Interactions in Energy Conversion” Energy Frontier Research Center funded by the US Department of
37 Energy, Office of Science, Office of Basic Energy Sciences under Award Number DE-SC0001293. O.I.,
38 M.C.S., and H.A.A. acknowledge support from the Northrop Grumman Corporation through NG Next.
39 M.C.S. acknowledges fellowship support from the Resnick Sustainability Institute. O.D.M. was supported
40 by the Air Force Office of Scientific Research under Award Number FA9550-17-1-0093. T.C. was
41 supported by the Danish Council for Independent Research (Grant DFFC6108-00667). M.S. was
42 supported as part of the Army Research Office through the Institute for Soldier Nanotechnologies under
43 contract no. W911NF-13-D-0001 (photon management for developing nuclear-TPV and fuel-TPV mm-
44 scale-systems). M.S. was also supported as part of the S3TEC, an Energy Frontier Research Center
45 funded by the US Department of Energy under grant no. DE-SC0001299 (for fundamental photon
46 transport related to solar TPVs and solar-TEs).
47
48
49
50

51 **Supporting Information**

52 The Supporting Information is available free of charge on the ACS Publications website at DOI: -----
53 Analysis beyond the local response approximation (LRA) conductivity; expressions for the
54 radiative heat transfer involving dipolar structures; polarizability model for graphene
55
56
57
58
59
60

resonators; first-order approximations to the radiative thermal conductance; separation distance; effect of substrate (PDF).

References

- (1) Hargreaves, C. M. Anomalous Radiative Transfer between Closely-Spaced Bodies. *Phys. Lett. A* **1969**, *30*, 491–492.
- (2) Polder, D.; Van Hove, M. Theory of Radiative Heat Transfer between Closely Spaced Bodies. *Phys. Rev. B* **1971**, *4*, 3303–3314.
- (3) Narayanaswamy, A.; Shen, S.; Chen, G. Near-Field Radiative Heat Transfer between a Sphere and a Substrate. *Phys. Rev. B* **2008**, *78*, 115303.
- (4) Shen, S.; Narayanaswamy, A.; Chen, G. Surface Phonon Polaritons Mediated Energy Transfer between Nanoscale Gaps. *Nano Lett.* **2009**, *9*, 2909–2913.
- (5) Rousseau, E.; Siria, A.; Jourdan, G.; Volz, S.; Comin, F.; Chevrier, J.; Greffet, J.-J. Radiative Heat Transfer at the Nanoscale. *Nat. Photonics* **2009**, *3*, 514–517.
- (6) Ottens, R. S.; Quetschke, V.; Wise, S.; Alemi, A. A.; Lundock, R.; Mueller, G.; Reitze, D. H.; Tanner, D. B.; Whiting, B. F. Near-Field Radiative Heat Transfer between Macroscopic Planar Surfaces. *Phys. Rev. Lett.* **2011**, *107*, 14301.
- (7) Guha, B.; Otey, C.; Poitras, C. B.; Fan, S.; Lipson, M. Near-Field Radiative Cooling of Nanostructures. *Nano Lett.* **2012**, *12*, 4546–4550.
- (8) van Zwol, P. J.; Thiele, S.; Berger, C.; de Heer, W. A.; Chevrier, J. Nanoscale Radiative Heat Flow due to Surface Plasmons in Graphene and Doped Silicon. *Phys. Rev. Lett.* **2012**, *109*, 264301.
- (9) St-Gelais, R.; Guha, B.; Zhu, L.; Fan, S.; Lipson, M. Demonstration of Strong Near-Field Radiative Heat Transfer between Integrated Nanostructures. *Nano Lett.* **2014**, *14*, 6971–6975.
- (10) Song, B.; Ganjeh, Y.; Sadat, S.; Thompson, D.; Fiorino, A.; Fernández-Hurtado, V.; Feist, J.; Garcia-Vidal, F. J.; Cuevas, J. C.; Reddy, P.; Meyhofer, E. Enhancement of Near-Field Radiative Heat Transfer Using Polar Dielectric Thin Films. *Nat. Nanotechnol.* **2015**, *10*, 253–258.
- (11) Kim, K.; Song, B.; Fernández-Hurtado, V.; Lee, W.; Jeong, W.; Cui, L.; Thompson, D.; Feist, J.; Reid, M. T. H.; Garcia-Vidal, F. J.; Cuevas, J. C.; Meyhofer, E.; Reddy, P. Radiative Heat Transfer in the Extreme Near Field. *Nature* **2015**, *528*, 387–391.
- (12) Ito, K.; Miura, A.; Iizuka, H.; Toshiyoshi, H. Parallel-Plate Submicron Gap Formed by Micromachined Low-Density Pillars for near-Field Radiative Heat Transfer. *Appl. Phys. Lett.* **2015**, *106*, 83504.
- (13) St-Gelais, R.; Zhu, L.; Fan, S.; Lipson, M. Near-Field Radiative Heat Transfer between Parallel Structures in the Deep Subwavelength Regime. *Nat. Nanotechnol.* **2016**, *11*, 515–519.
- (14) Bernardi, M. P.; Milovich, D.; Francoeur, M. Radiative Heat Transfer Exceeding the Blackbody Limit between Macroscale Planar Surfaces Separated by a Nanosize Vacuum Gap. *Nat. Commun.* **2016**, *7*, 12900.
- (15) Watjen, J. I.; Zhao, B.; Zhang, Z. M. Near-Field Radiative Heat Transfer between Doped-Si Parallel Plates Separated by a Spacing down to 200 nm. *Appl. Phys. Lett.* **2016**, *109*, 203112.
- (16) Kloppstech, K.; Köne, N.; Biehs, S.-A.; Rodriguez, A. W.; Worbes, L.; Hellmann, D.; Kittel, A. Giant Heat Transfer in the Crossover Regime between Conduction and Radiation. *Nat. Commun.* **2017**, *8*, 14475.
- (17) Cui, L.; Jeong, W.; Fernández-Hurtado, V.; Feist, J.; Garcia-Vidal, F. J.; Cuevas, J. C.; Meyhofer, E.; Reddy, P. Study of Radiative Heat Transfer in Ångström- and Nanometre-Sized Gaps. *Nat. Commun.* **2017**, *8*, 14479.

- 1
 - 2
 - 3
 - 4
 - 5
 - 6
 - 7
 - 8
 - 9
 - 10
 - 11
 - 12
 - 13
 - 14
 - 15
 - 16
 - 17
 - 18
 - 19
 - 20
 - 21
 - 22
 - 23
 - 24
 - 25
 - 26
 - 27
 - 28
 - 29
 - 30
 - 31
 - 32
 - 33
 - 34
 - 35
 - 36
 - 37
 - 38
 - 39
 - 40
 - 41
 - 42
 - 43
 - 44
 - 45
 - 46
 - 47
 - 48
 - 49
 - 50
 - 51
 - 52
 - 53
 - 54
 - 55
 - 56
 - 57
 - 58
 - 59
 - 60
- (18) Liu, X.; Zhang, Z. Near-Field Thermal Radiation between Metasurfaces. *ACS Photonics* **2015**, *2*, 1320–1326.
- (19) Zhu, L.; Fan, S. Persistent Directional Current at Equilibrium in Nonreciprocal Many-Body Near Field Electromagnetic Heat Transfer. *Phys. Rev. Lett.* **2016**, *117*, 134303.
- (20) Khandekar, C.; Jin, W.; Miller, O. D.; Pick, A.; Rodriguez, A. W. Giant Frequency-Selective Near-Field Energy Transfer in Active-Passive Structures. *Phys. Rev. B* **2016**, *94*, 115402.
- (21) Principi, A.; Lundeberg, M. B.; Hesp, N. C. H.; Tielrooij, K.-J.; Koppens, F. H. L.; Polini, M. Super-Planckian Electron Cooling in a van Der Waals Stack. *Phys. Rev. Lett.* **2017**, *118*, 126804.
- (22) Chen, K.; Santhanam, P.; Fan, S. Near-Field Enhanced Negative Luminescent Refrigeration. *Phys. Rev. Appl.* **2016**, *6*, 024014.
- (23) Ding, D.; Kim, T.; Minnich, A. J. Active Thermal Extraction of Near-Field Thermal Radiation. *Phys. Rev. B* **2016**, *93*, 081402.
- (24) Otey, C. R.; Lau, W. T.; Fan, S. Thermal Rectification through Vacuum. *Phys. Rev. Lett.* **2010**, *104*, 154301.
- (25) Iizuka, H.; Fan, S. Rectification of Evanescent Heat Transfer between Dielectric-Coated and Uncoated Silicon Carbide Plates. *J. Appl. Phys.* **2012**, *112*, 24304.
- (26) Zhu, L.; Otey, C. R.; Fan, S. Ultrahigh-Contrast and Large-Bandwidth Thermal Rectification in Near-Field Electromagnetic Thermal Transfer between Nanoparticles. *Phys. Rev. B* **2013**, *88*, 184301.
- (27) Ben-Abdallah, P.; Biehs, S.-A. Near-Field Thermal Transistor. *Phys. Rev. Lett.* **2014**, *112*, 044301.
- (28) Ben-Abdallah, P.; Joulain, K. Fundamental Limits for Noncontact Transfers between Two Bodies. *Phys. Rev. B* **2010**, *82*, 121419.
- (29) Miller, O. D.; Johnson, S. G.; Rodriguez, A. W. Shape-Independent Limits to Near-Field Radiative Heat Transfer. *Phys. Rev. Lett.* **2015**, *115*, 204302.
- (30) Miller, O. D.; Ilic, O.; Christensen, T.; Reid, M. T. H.; Atwater, H. A.; Joannopoulos, J. D.; Soljačić, M.; Johnson, S. G. Limits to the Optical Response of Graphene and Two-Dimensional Materials. *Nano Lett.* **2017**, *17*, 5408–5415.
- (31) Volokitin, A. I.; Persson, B. N. J. Near-Field Radiative Heat Transfer between Closely Spaced Graphene and Amorphous SiO₂. *Phys. Rev. B* **2011**, *83*, 241407.
- (32) Ilic, O.; Jablan, M.; Joannopoulos, J. D.; Celanovic, I.; Soljačić, M. Overcoming the Black Body Limit in Plasmonic and Graphene near-Field Thermophotovoltaic Systems. *Opt. Express* **2012**, *20*, A366.
- (33) Ilic, O.; Jablan, M.; Joannopoulos, J. D.; Celanovic, I.; Buljan, H.; Soljačić, M. Near-Field Thermal Radiation Transfer Controlled by Plasmons in Graphene. *Phys. Rev. B* **2012**, *85*, 155422.
- (34) Svetovoy, V. B.; van Zwol, P. J.; Chevrier, J. Plasmon Enhanced near-Field Radiative Heat Transfer for Graphene Covered Dielectrics. *Phys. Rev. B* **2012**, *85*, 155418.
- (35) Messina, R.; Hugonin, J.-P.; Greffet, J.-J.; Marquier, F.; De Wilde, Y.; Belarouci, A.; Frechette, L.; Cordier, Y.; Ben-Abdallah, P. Tuning the Electromagnetic Local Density of States in Graphene-Covered Systems via Strong Coupling with Graphene Plasmons. *Phys. Rev. B* **2013**, *87*, 085421.
- (36) Liu, X. L.; Zhang, Z. M. Graphene-Assisted Near-Field Radiative Heat Transfer between Corrugated Polar Materials. *Appl. Phys. Lett.* **2014**, *104*, 251911.
- (37) Ben-Abdallah, P.; Belarouci, A.; Frechette, L.; Biehs, S.-A. Heat Flux Splitter for near-Field Thermal Radiation. *Appl. Phys. Lett.* **2015**, *107*, 53109.
- (38) Yang, Y.; Wang, L. Electrically-Controlled Near-Field Radiative Thermal Modulator Made of Graphene-Coated Silicon Carbide Plates. *J. Quant. Spectrosc. Radiat. Transf.* **2017**, *197*, 68–75.
- (39) Yu, R.; Manjavacas, A.; de Abajo, F. J. Ultrafast Radiative Heat Transfer. *Nat. Commun.* **2017**, *8*, 2.
- (40) Ramirez, F. V.; Shen, S.; McGaughey, A. J. H. Near-Field Radiative Heat Transfer in Graphene Plasmonic Nanodisk Dimers. *Phys. Rev. B* **2017**, *96*, 165427.
- (41) Rodriguez, A. W.; Ilic, O.; Bermel, P.; Celanovic, I.; Joannopoulos, J. D.; Soljačić, M.; Johnson,

- 1
2
3 S. G. Frequency-Selective Near-Field Radiative Heat Transfer between Photonic Crystal Slabs: A
4 Computational Approach for Arbitrary Geometries and Materials. *Phys. Rev. Lett.* **2011**, *107*,
5 114302.
- 6 (42) Jablan, M.; Buljan, H.; Soljačić, M. Plasmonics in Graphene at Infrared Frequencies. *Phys. Rev. B*
7 **2009**, *80*, 245435.
- 8 (43) Johnson, S. G. The NLOpt nonlinear-optimization package <http://ab-initio.mit.edu/nlopt>.
- 9 (44) Rinnooy Kan, A. H. G.; Timmer, G. T. Stochastic Global Optimization Methods. *Math. Program.*
10 **1987**, *39*, 27–78.
- 11 (45) Powell, M. J. D. *The BOBYQA Algorithm for Bound Constrained Optimization without*
12 *Derivatives*; Cambridge NA Report NA2009/06, University of Cambridge, Cambridge. **2009**, 26-
13 46.
- 14 (46) Novotny, L.; Hecht, B. *Principles of Nano-Optics*; Cambridge University Press, **2006**.
- 15 (47) Christensen, T. From Classical to Quantum Plasmonics in Three and Two Dimensions, *PhD*
16 *Thesis*, Technical University of Denmark, **2015**.
- 17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

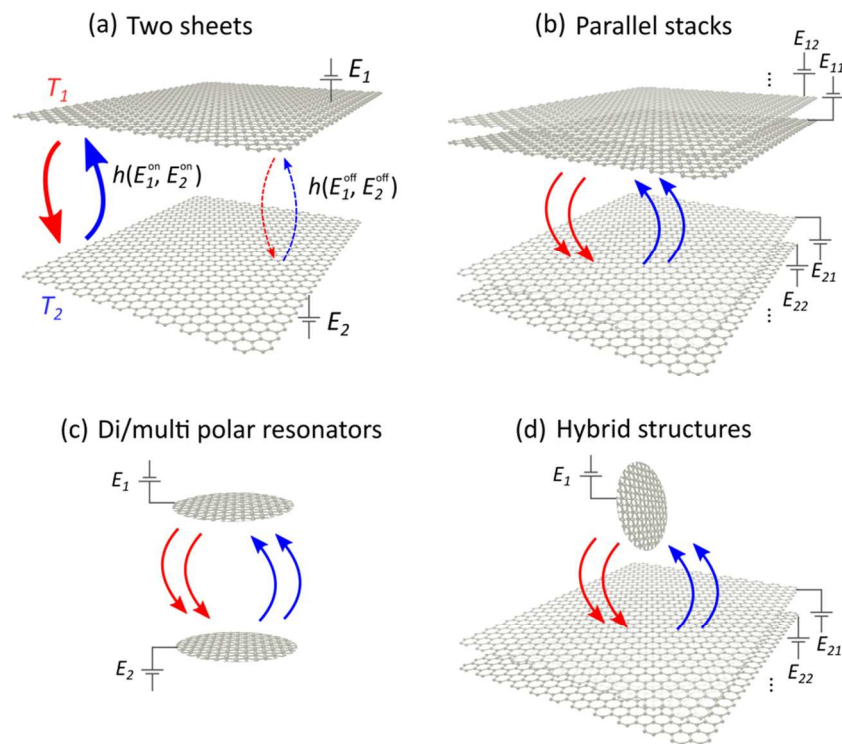


Fig 1. Operating principle for a radiative thermal switch using graphene plasmon nanoresonators in structures comprising (a, b) parallel (multi)layers, (c) di/multipolar resonators, and (d) hybrid configurations. External control of the relevant Fermi levels $E_i = (E_1, \dots)$ modulates the near-field heat transfer between the “OFF” state at minimal radiative thermal conductance $h_{\text{off}} = h(E_1^{\text{off}}, \dots)$, and the “ON” state at maximal conductance $h_{\text{on}} = h(E_1^{\text{on}}, \dots)$.

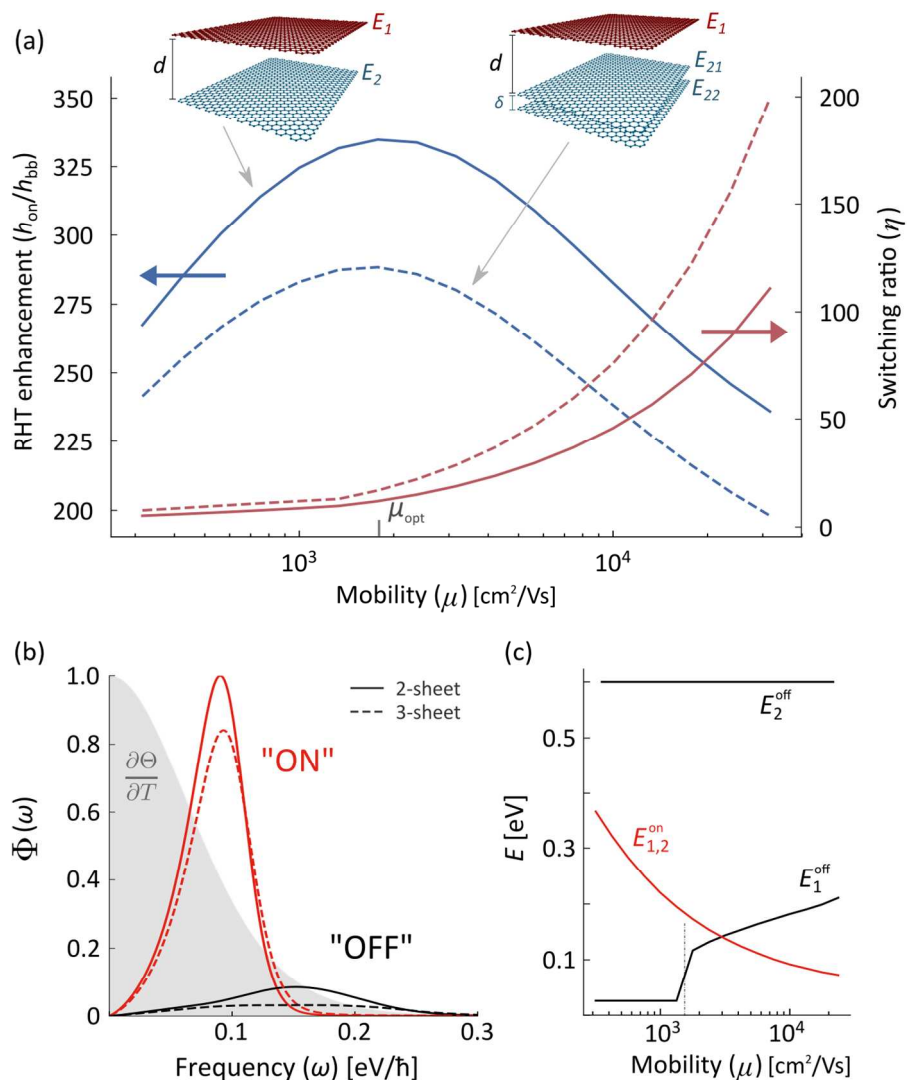


Fig 2. Thermal switching in parallel graphene stacks. (a) RHT enhancement $h_{\text{on}}/h_{\text{bb}}$ (left) and the switching ratio $\eta = h_{\text{on}}/h_{\text{off}}$ (right) for a 2-sheet (solid) and a 3-sheet (dashed) configuration, as a function of mobility $\mu_{1,2} = \mu$. (b) Spectral heat flux indicating the "ON" and the "OFF" states for mobility $\mu = \mu_{\text{opt}}$ from (a). Shaded region shows Planck's prefactor from (1). (c) Corresponding Fermi levels for the "ON" ($E_{1,2}^{\text{on}}$) and the "OFF" ($E_{1,2}^{\text{off}}$) states in the 2-sheet case. Here, $T = 300$ K, $d = 100$ nm, $\delta = 10$ nm.

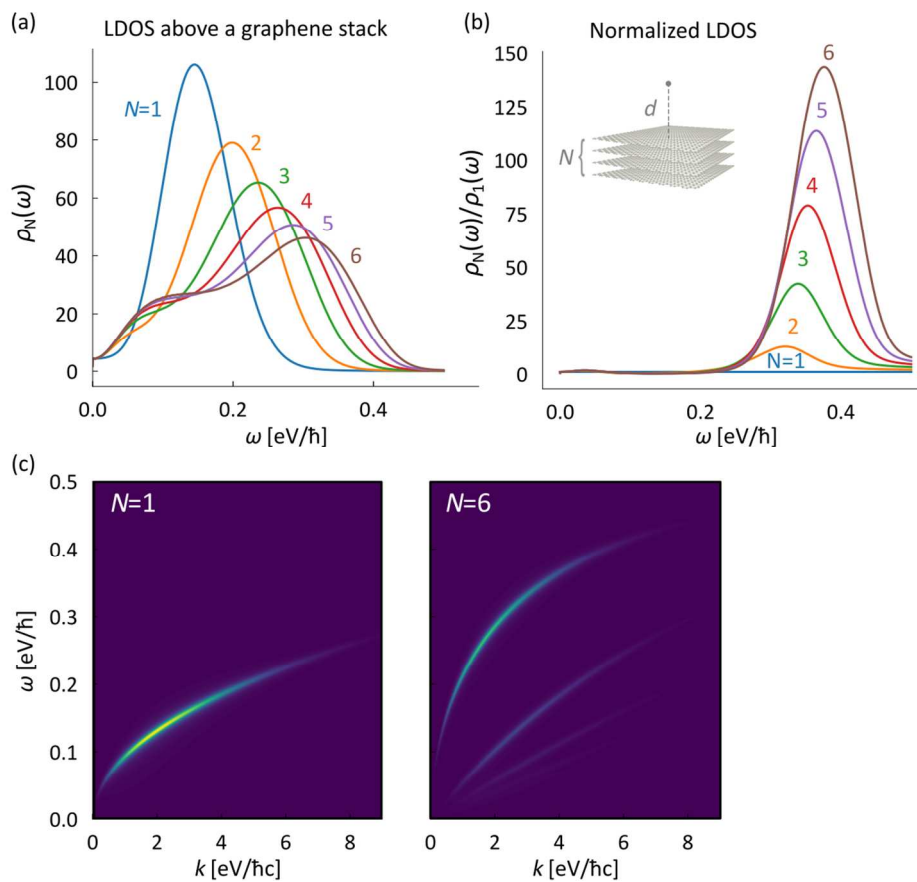


Fig 3. (a) Orientation-averaged local density of states (LDOS) ρ at a height d above a graphene stack of N identical sheets ($E_i=0.6$ eV), separated by δ (see inset in (b)). (b) LDOS for $N > 1$ normalized to that of $N = 1$. (c) Decomposed (k, ω) LDOS for $N = 1$ and $N = 6$. Here, $d = 100$ nm, $\delta = 10$ nm.

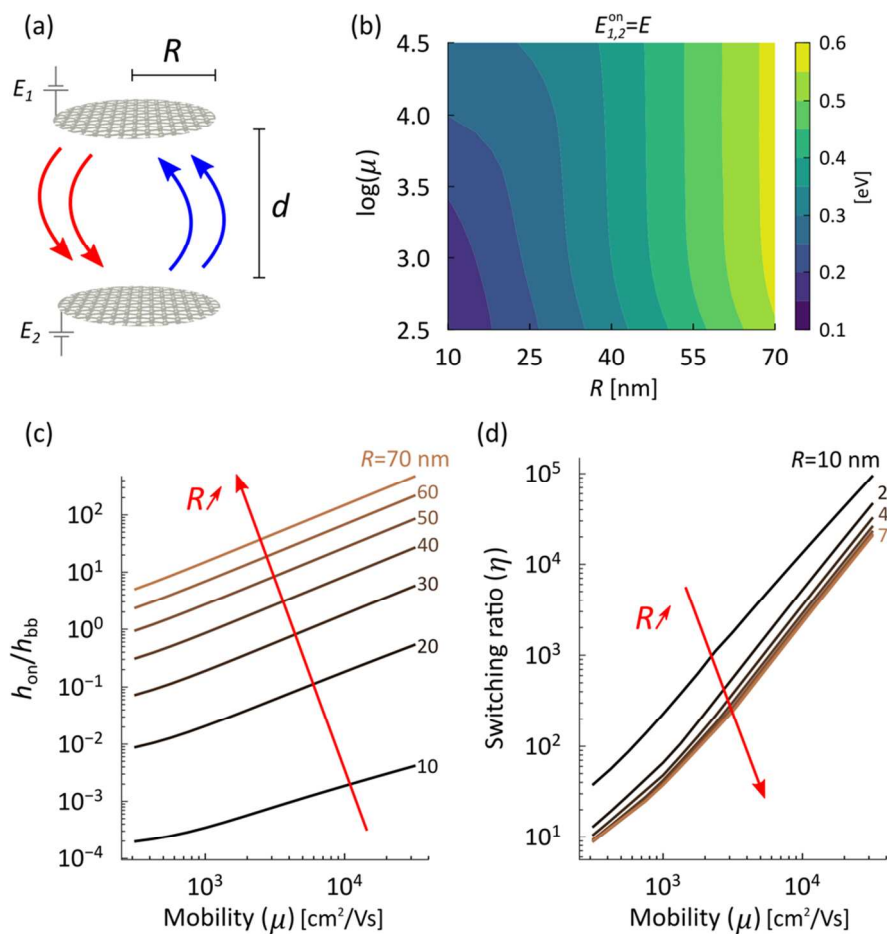


Fig 4. Radiative thermal switching between parallel graphene disks (a). Optimal carrier concentration levels $E_{1,2}^{on} = E$ for the “ON” state (b), RHT enhancement (c), and the switching ratio (d), as a function of mobility (μ) and disk radius (R). Here, $T = 300$ K, $d = 200$ nm.

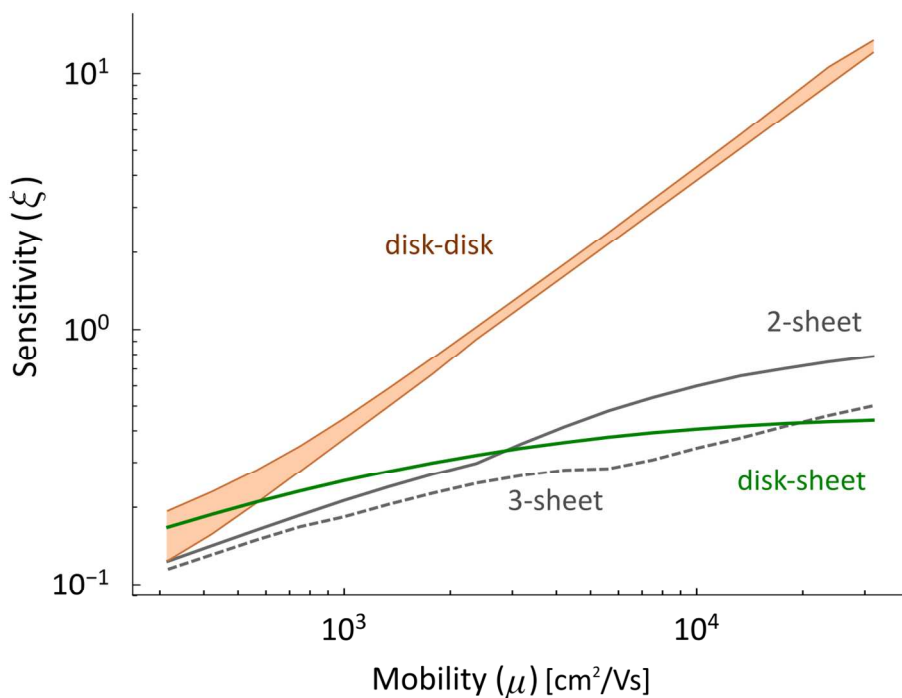


Fig 5. Sensitivity of thermal switching defined as $\xi = k_B T / \min_i |E_i^{\text{on}} - E_i^{\text{on}/2}|$ (*i.e.* inversely proportional to the smallest change in E_i needed to halve the “ON” state thermal conductance), for resonator configurations from Fig. 1. For parallel disks (Fig. 4), a range from $R = 10$ nm (most sensitive) to $R = 70$ nm (least sensitive) is shown.

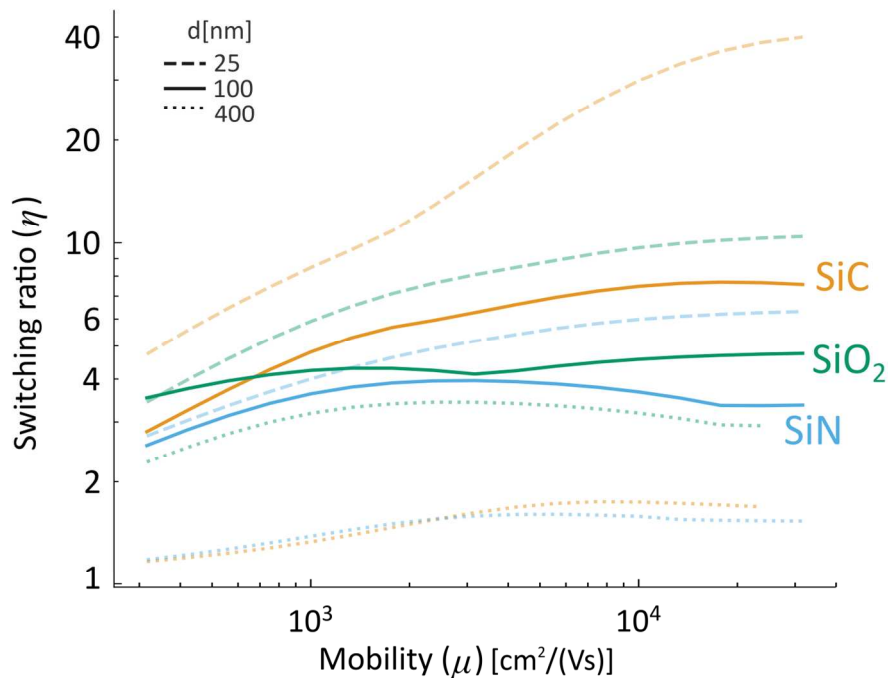


Fig 6. Thermal switching between parallel graphene sheets (Fig. 1a), now on identical substrates that support surface phonon-polaritons (SiC, SiN, or SiO₂). Different line styles indicate the switching ratio η for separation distance d of 25 nm (dashed), 100 nm (solid), and 400 nm (dotted) ($T=300$ K). As before, for each value of mobility, the respective Fermi levels for the ON ($E_{1,2}^{\text{on}}$) and the OFF ($E_{1,2}^{\text{off}}$) state are determined.