

MIT Open Access Articles

Programmable CRISPR-responsive smart materials

The MIT Faculty has made this article openly available. **Please share** how this access benefits you. Your story matters.

Citation: English, Max A. et al. " Programmable CRISPR-responsive smart materials." Science 365, 6455 (August 2019): 780-785 © 2017 The Authors

As Published: <http://dx.doi.org/10.1126/science.aaw5122>

Publisher: American Association for the Advancement of Science (AAAS)

Persistent URL: <https://hdl.handle.net/1721.1/125920>

Version: Author's final manuscript: final author's manuscript post peer review, without publisher's formatting or copy editing

Terms of use: Creative Commons Attribution-Noncommercial-Share Alike



Programmable CRISPR-Responsive Smart Materials

Max A. English^{1,2†}, Luis R. Soenksen^{2,3,4‡}, Raphael V. Gayet^{1,2,5†}, Helena de Puig^{2,4,6†}, Nicolaas M. Angenent-Mari^{1,2,4‡}, Angelo S. Mao^{4,6‡}, Peter Q. Nguyen^{4,6}, and James J. Collins^{1,2,4,6,7,8,9*}

5

Affiliations:

¹Department of Biological Engineering, Massachusetts Institute of Technology (MIT), Cambridge, MA 02139, USA.

²Institute for Medical Engineering and Science, MIT, Cambridge, MA 02139, USA.

10 ³Department of Mechanical Engineering, MIT, Cambridge, MA 02139, USA.

⁴Wyss Institute for Biologically Inspired Engineering, Harvard University, Boston, MA 02115, USA.

⁵Microbiology Graduate Program, MIT, Cambridge, MA 02139, USA.

15 ⁶School of Engineering and Applied Sciences, Harvard University, Cambridge, MA 02138, USA.

⁷Synthetic Biology Center, MIT, Cambridge, MA 02139, USA.

⁸Broad Institute of MIT and Harvard, Cambridge, MA 02142, USA.

⁹Harvard-MIT Program in Health Sciences and Technology, Cambridge, MA 02139, USA.

20 *Corresponding author. Email: jimjc@mit.edu (J.J.C.);

†, ‡ These authors contributed equally to this work.

25

Abstract: Stimuli-responsive materials activated by biological signals play an increasingly important role in biotechnology applications. We exploit the programmability of CRISPR-associated nucleases to actuate hydrogels containing DNA as a structural element or as an anchor for pendant groups. After activation by guide RNA-defined inputs, Cas12a cleaves DNA within the gels, thereby converting biological information into changes in material properties. We report four applications: (i) branched poly(ethylene glycol) hydrogels releasing DNA-anchored compounds; (ii) degradable polyacrylamide-DNA hydrogels encapsulating nanoparticles and live cells; (iii) conductive carbon black-DNA hydrogels acting as degradable electrical fuses; and (iv) a polyacrylamide-DNA hydrogel operating as a fluidic valve with an electrical readout for remote signaling. These materials allow for a range of in vitro applications in tissue engineering, bio-electronics, and diagnostics.

35

One Sentence Summary: The programmability of CRISPR-associated nucleases is used to precisely control multiscale properties of DNA-based materials.

40

Main Text:

Microbial clustered regularly interspaced short palindromic repeats (CRISPR) and CRISPR-associated (Cas) adaptive immune systems contain RNA-guided endonucleases capable of multiple-turnover nucleic acid hydrolysis (1, 2). Due to their specificity and programmability, CRISPR-Cas enzymes have been exploited as efficient genome editing tools (3) and in nucleic acid diagnostic applications such as SHERLOCK (4, 5) and DETECTR (2).

Biologically responsive materials are important for biotechnology applications, including the fabrication of scaffolds for tissue engineering (6), the actuation of microfluidic valves (7), and the detection of analytes in sensors (8, 9). DNA-responsive hydrogels are well suited to interface with synthetic DNA constructs or naturally occurring extracellular DNA (10). Current DNA-responsive hydrogels typically rely on strand-displacement or structural changes in DNA cross-linkers (11, 12), which require high concentrations of DNA triggers for actuation. Adapting such DNA-hydrogels for activation with new trigger sequences involves the modification of nucleic acid components which can conflict with the structural requirements (e.g., length, secondary structure) imposed by the material. This limits the programmability of these systems, and highlights the need for a strategy that uncouples structural and sensing constraints in DNA-based materials.

We use CRISPR-associated enzymes to control the properties of hydrogels with integrated DNA components at multiple scales and in a modular fashion and thereby eliminate the need to encode target sequence specificity into the gel structure. Our material platform is able to induce changes in hydrogels in response to user-defined target nucleic acid sequences by replacing a single component – a CRISPR guide RNA (gRNA) that governs sequence-specific Cas activation. We engineered different DNA-based materials to demonstrate a variety of nuclease-mediated responses including the release of small molecules, enzymes, nanoparticles (NPs) and live cells, as well as the modulation of bulk electrical and permeability properties of DNA-hydrogels for sensing and diagnostics (Fig. S1).

Cas12a has both targeted and collateral DNase activities

The Cas12a from *Lachnospiraceae* bacterium ND2006 (LbaCas12a) (1, 2) displays a specific cleavage activity towards double-stranded DNA (dsDNA) fragments matching the gRNA spacer sequence (targeted cleavage), and a subsequent indiscriminate single-stranded DNA (ssDNA) hydrolysis activity (collateral cleavage, Fig. S2). Once the Cas12a-gRNA complex binds and cleaves its dsDNA target, the collateral cleavage of nearby ssDNA by Cas12a is highly efficient (~1250 turnovers per second) (2). To demonstrate the target programmability of CRISPR-gels, we tested gRNAs to detect fragments of the *mecA* antibiotic-resistance gene of methicillin-resistant *Staphylococcus aureus* (MRSA). We selected MRSA as a clinically relevant model to demonstrate the target programmability of CRISPR-gels, given the high concentration of extracellular DNA in MRSA biofilms (13).

We first validated the collateral cleavage activity of Cas12a-gRNA in solution (14). Cleavage of a ssDNA reporter containing a quenched fluorophore by Cas12a in response to *mecA* dsDNA triggers confirmed the performance of the MRSA1 gRNA (Fig. S3). Cas12a programmed with this gRNA detected its cognate trigger down to ~16 pM in solution (Fig. S4) and was selected for

subsequent experiments. Sequence mismatches between the gRNA and trigger reduced the collateral cleavage rate, consistent with previously reported patterns (2, 15). Non-specific activation of Cas12a by a scrambled dsDNA sequence was over 100-fold lower than that by the *mecA* trigger (Fig. S4). Cas12a's high dsDNA target specificity and rapid nonspecific ssDNA collateral cleavage activity make it an ideal candidate for modulating a wide range of physical and mechanical hydrogel properties (Fig. S1).

Programmable materials capable of the controlled release of soluble compounds, as well as encapsulated cells, have broad utility in various therapeutic and research applications (16-19). Due to the diversity of DNA-based hydrogels in the literature (Table S1), we selected material formulations that span a wide range of physical properties to demonstrate that they could be actuated by Cas proteins (Table S2): (1) poly(ethylene glycol) (PEG) hydrogels with covalently bound nonstructural DNA pendants that are released by Cas12a nuclease activity without degrading the overall hydrogel structure; (2) acrylamide hydrogels with structural ssDNA cross-links that could be cleaved by Cas12a resulting in bulk gel degradation, as well as particle or cell release; and (3) conductive hydrogels loaded with carbon black that were cleaved from the surface of electrodes by Cas12a, thus behaving like an electronic fuse.

Collateral Cas12a activity releases ssDNA-anchored cargos from hydrogel matrices

The targeted dsDNA cleavage activity of Cas12a can be used to preferentially release anchored cargos with near-single turnover (Fig. S5), however we focused on the collateral ssDNase activity of the enzyme as it allows for the efficient transduction of external stimuli into changes in material properties through catalytic signal amplification. To illustrate the programmable actuation of materials using Cas12a, we covalently tethered a fluorophore (Cy3) into PEG hydrogels through a ssDNA linker (Fig. 1A) and monitored its release into solution (Fig. S6) upon Cas12a-induced cleavage. The Cas12a-gRNA complex was insufficient to catalyze cargo release, however introduction of the *mecA* dsDNA trigger initiated the hydrolysis of ssDNA anchors (Fig. 1B and Fig. S7). In contrast, a randomly permuted version of the *mecA* dsDNA (scrambled control) failed to do so. We then used horseradish peroxidase (HRP) enzyme as a model for larger biomolecule payloads, demonstrating that biological function was preserved after immobilization in hydrogels using ssDNA anchors and subsequent release by Cas12a (Fig. 1C). Within 10 minutes of exposure to a low-concentration (10 nM) dsDNA stimulus, we detected sufficient HRP activity in the supernatant for a visual readout (Fig. 1C, inset). Further incubation allowed us to routinely discriminate trigger and scrambled dsDNA down to 100 pM (Fig. S8). These experiments are consistent with the efficient ssDNase activity of activated Cas12a (2).

To demonstrate that changes to the gRNA were sufficient to entirely reprogram the target responsiveness of the material, we designed gRNAs to target a panel of genes involved in *S. aureus* antibiotic-resistance mechanisms (Fig. S9). These include the antibiotic resistance genes *ermA*, and *ermC* (20, 21), the virulence factor gene *spa* (22) and the vancomycin-resistance gene *vanA* (23). Out of 25 combinations of gRNAs and dsDNA, those where the sequence of the trigger matched the gRNA resulted in substantially higher fluorophore payload release from the hydrogel matrix (Fig. 1D). These results correlated to similar observations of the reactions performed in solution (Fig. S10), and suggest that different gRNA-trigger pairs activate Cas12a to different extents (2).

For many applications, the rate at which a molecule is delivered from a carrier conveys important biological information (16). The speed of CRISPR-mediated hydrogel actuation corresponds to the amount of input dsDNA (Fig. S11); conversely, for a given level of input, the response dynamics can be hard-coded into the system by altering the properties of the starting material. For example, pore size is expected to alter the mobility of macromolecules in polymer networks (24). Based on our macroscopic observations of programmed anchor hydrolysis (Fig. S12), we hypothesized that this could be used to further tune the relationship between dsDNA input and Cas12a-mediated response. By modulating the cross-linking density of a PEG-DNA hydrogel and measuring the rate of fluorophore release by Cas12a-gRNA, we established another strategy by which the behavior of the CRISPR-responsive material could be controlled (Fig. 1E and Figs. S13-S14).

In addition to controlling global dynamics of ssDNA cleavage through bulk material properties, we capitalized on the sequence-defined, addressable nature of the ssDNA linkers and the selectivity of the collateral cleavage activity of Cas12a for ssDNA over dsDNA (1, 2). We attached two different fluorophores (Cy3 and 6-FAM) into PEG hydrogels with distinct ssDNA linkers, and pre-programmed the differential sensitivity of one linker over the other to Cas12a collateral degradation by hybridizing it with a complementary blocking strand in situ. While the release of the unprotected fluorophore was unaffected, the speed of release of the hybridized reporter was significantly reduced (Fig. 1F and Fig. S15).

Collateral Cas12a activity alters the large scale mechanical properties of DNA-hydrogels

The high catalytic efficiency of dsDNA-activated Cas12a-gRNA ($k_{\text{cat}}/K_m \sim 1.7 \times 10^9 \text{ s}^{-1}\text{M}^{-1}$) (2) makes it well-suited for converting dsDNA signals into bulk material changes. To demonstrate this, we designed DNA cross-linked polyacrylamide (PA) hydrogels (9, 25) by separately incorporating two non-complementary oligonucleotides into polyacrylamide chains (Fig. S16). We then cross-linked the polyacrylamide-DNA (PA-DNA) precursors using an oligonucleotide strand that forms bridges between the PA-DNA chains. These cross-links contained single stranded, AT-rich Cas12a collateral cleavage sites (Fig. 2A). In these hydrogels, degradation of DNA cross-links physically disrupts the polymer networks (Fig. S1B) (24, 26).

The Cas12a-induced degradation of PA-based CRISPR-gels was initially evaluated with a DNA-intercalating dye to label bridge sequences in PA-DNA gels and track gel integrity. The bridges were degraded upon exposure to gRNA-Cas12a and trigger dsDNA, as revealed by the dissipation of gel fluorescence at rates dependent on trigger concentration (Fig. 2B). Compared to experiments performed in solution (Fig. S4), gel degradation appeared more robust to the introduction of sequence mismatches between the gRNA and dsDNA trigger (Fig. S17). Using FITC-dextran particles physically entrapped in the hydrogel, we also visualized the degradation of millimeter-scale PA-DNA hydrogels (Fig. S18).

Programmable degradation of PA-DNA hydrogels was assessed by testing 25 combinations of different gRNAs and dsDNA triggers. Consistent with the non-destructive cargo release experiments (Fig. 1E), PA-DNA hydrogel degradation occurred only when the gRNA and dsDNA sequences were complementary (Fig. 2C and Fig. S19), demonstrating Cas12a-gRNA's ability to discriminate between inputs.

Though biomolecules can be tethered to materials through well-defined, single linkers, physical entrapment in a polymer matrix represents a more general strategy to control the release of larger payloads. We tested the release of nanoparticles by encapsulating PEG-coated gold nanoparticles (AuNPs) (Fig. S16C and Fig. S20) in PA-DNA hydrogels. Loading gels with both Cas12a-gRNA and a dsDNA trigger led to total nanoparticle release via Cas12a activation and gel degradation, whereas gels loaded with a scrambled dsDNA trigger showed no significant release of AuNPs relative to a buffer-only background (Fig. 2D and Fig. S21-S22). This was consistent with the disruption of the percolated network upon cross-link cleavage (27, 28).

The complex interactions between cells and surrounding materials have implications for tissue engineering and other therapeutic applications. We reasoned that if Cas12a-gRNA would have the capacity to modify the extracellular matrix of cells encapsulated in DNA materials in response to pre-defined cues. We tested the reversible encapsulation of human primary peripheral blood mononuclear (PBMC) cells in PA-DNA hydrogels by exposing the gels to activated gRNA-Cas12a. Complete gel degradation and cell release were observed within 2 hours in the presence of 1 μ M dsDNA trigger (Fig. 2E and Fig. S23), without compromising cell viability (Fig. S24-S25). Conversely, gels exposed to a scrambled dsDNA control remained intact within the same timeframe. These results demonstrate that nanoparticles and live-cell payloads can be immobilized in biocompatible hydrogels and released upon addition of trigger dsDNA sequences without the need for hydrogel redesign to accommodate different input signals.

Conductive DNA-based materials act as Cas12a-actuated electronic fuses

We used Cas12a to modulate the attachment of a conductive DNA-based hydrogel to an electrode surface to act as an electrical fuse triggered by specific DNA sequences (Fig. 3A and Fig. S1C). A conductive, biologically responsive hydrogel may be desirable for a variety of sensing and diagnostic applications where the direct interface to electrical devices (e.g., analog circuits and microcontrollers) is required (29). These conductive, self-assembled materials consisted of ssDNA networks cross-linked with carbon-black (CB) conductive nanoparticles (CB-DNA gels). CB is composed of spherical particles (30) containing graphitic-like domains (31), and is widely used in industrial applications to impart electrical conductivity to polymers (32); here we used it as a conductive cross-linker in hydrogels. CB-DNA gels were synthesized through thermal melting of dsDNA followed by cooling in the presence of CB nanoparticles. This leads to the strong, non-covalent association of the aromatic DNA nucleotides with nearby CB graphitic surfaces (33) through hydrogen bonding and π - π stacking interactions (34-36). In these hydrogels, DNA behaves as the main structural component, linking carbon black particles together to form a three-dimensional network (34, 37).

We hypothesized that cleavage of the ssDNA at the electrode-material interface by Cas12a would disrupt the conductive path. To test this system, CB-DNA droplets were spotted onto printed interdigitated silver electrodes and lyophilized (Fig. 3A). Before Cas12a-mediated degradation, lyophilized CB-DNA hydrogels showed conductivities comparable to that reported for graphene-DNA gels of similar compositions (\sim 4 mS/cm) (34). After initial electrical testing, CB-DNA gels were incubated in a solution containing Cas12a-gRNA and dsDNA triggers. We visually monitored the CB-DNA hydrogels during Cas12a-mediated detachment (Fig. 3B), tested

for conductivity (Fig. 3C), and imaged the electrodes (Fig. 3D and Fig. S26A) with increasing concentrations of dsDNA inputs. Cas12a-gRNA with 500 nM dsDNA trigger was able to completely detach 60% of the hydrogels from electrodes in 10 hours, and 100% of hydrogels after 20 hours. Incubation with a higher dsDNA trigger concentration (1 μ M) led to CB-DNA detachment from 100% of electrodes within 10 hours. Complete detachment resulted in an opening of the circuit across the electrode, while partial detachment of the CD-DNA hydrogels at lower dsDNA trigger concentrations led to intermediate conductivities (Fig. 3C and D, and Fig. S26). Exposure of electrodes with CB-DNA gels to a ssDNA-specific nuclease resulted in a similar response, confirming that detachment was a consequence of Cas12a activation and ssDNA hydrolysis (Fig. S26D-E). This inexpensive CB-DNA gel formulation provides a direct link between dsDNA triggers and electrical outputs.

Cas12a-controlled hydrogel formation in a paper fluidic device enables diagnostic readouts

We used a tunable PA-DNA hydrogel to control the permeability and electrical readout of a paper-based microfluidic device (Fig. 4). Paper-based technologies have shown promise for point-of-care diagnostics as they are low cost, equipment-free, and easy to use (38, 39). Our device (Fig. 4A and Fig. S24) expands on the concept of paper fluidic chips (μ PADs) that rely on the capacity of hydrogels to obstruct flow through porous channels (40).

The layers of the device were folded to create a multilayered structure in which the hydrophilic regions are topologically aligned. Capillary-driven flow through the device terminated in a fifth layer where the output was measured (Fig. 4A and S27). In this system, an intermediary layer contains PA-DNA gel precursors (Ps-X and Ps-Y) that, when mixed with ssDNA cross-linker, form a hydrogel in the paper channels (41, 42). The extent of gel formation, and therefore the rate of buffer flow, is dependent on the extent of degradation of the ssDNA gel cross-linker during a pre-incubation step. The activation of Cas12a can be confirmed by adding a fluorescent ssDNA reporter during this step (Fig. S28). By degrading the cross-linker using Cas12a, we were able to couple the level of buffer flow to the concentration of dsDNA trigger added to a 4-hour incubated Cas12a reaction.

When nonspecific dsDNA trigger is present during pre-incubation, ssDNA cross-linkers are not cleaved, allowing for hydrogel assembly in the microchannel (Fig. 4A). Conversely, in the presence of a specific dsDNA trigger, unimpeded flow can be visually detected by adding dyes to the μ PAD channel. We found the rate of buffer flow through a μ PAD to be inversely related to the concentration of a MRSA dsDNA trigger. Using this visual output, we were able to detect dsDNA concentrations down to 400 pM (Fig. S29).


To optimize our CRISPR- μ PAD for field diagnostic applications, we used reverse transcription (RT) to expand the range of detectable biomarkers to RNA, and coupled the RT to an isothermal amplification (RPA) step to improve the limit of detection. We used RT-RPA followed by a μ PAD readout to detect synthetic Ebola genomic RNA (43) down to 11 aM (Fig. 4B), a sensitivity matching other state-of-the-art CRISPR-based diagnostics (Fig. S30) (2, 4, 5). This approach is promising for point-of-care diagnostics and has overall better performances in terms of sensitivity, portability and cost than other molecular diagnostics (Table S3).

Visual readouts of buffer flow are commonly used, yet they are difficult to couple to downstream hardware for data processing. To overcome this limitation, we modified the CRISPR-actuated fluidic system to read buffer flow as an electric signal: the microfluidic channel in the final layer was sandwiched between two electrodes and connected to an ohmmeter (Fig. 4A and Fig. S27B).

Electrical conductivity between the electrodes relied on electrolytes provided by the flowing buffer, and was directly correlated to the buffer penetration length in the μ PAD channel (Fig. S31A) (44). Using this approach, sub-nanomolar concentrations of dsDNA trigger were successfully detected at a 5-minute end-point, without DNA amplification, demonstrating the potential of the CRISPR μ PAD for embedded sensor applications (Fig. 4C). Non-specific dsDNA trigger did not activate Cas12a, thus leaving the electrical circuit open (Fig. 4C and Fig. S31). We were able to reduce the pre-incubation time required to observe a signal to 1 h by tuning the properties of the acrylamide precursors (Fig. S31B).

The wireless, decentralized logging of individual clinical tests during infectious disease outbreaks could address challenges with record keeping and logistics. To integrate CRISPR-Cas reactions with electronic monitoring systems through hydrogel actuation, we incorporated a wireless radio-frequency identification (RFID) module into the μ PAD. The original design was modified such that buffer flow would short-circuit an interdigitated silver electrode, thereby modulating the efficiency of signal transmission by a flexible RFID tag (Fig. 4D and Fig. S31). We then conducted an experimenter-blinded trial consisting of twelve samples (containing either 11 aM or 0 aM Ebola ssRNA amplified by RT-RPA) divided across three geographic locations (Fig. 4E and Fig. S32). The experimenter pre-incubated the samples with Cas12a and Ebola-specific gRNA for 4 h, and then recorded the RFID- μ PAD signals over the course of 2 minutes. Buffer flow through the μ PAD in Ebola-positive samples caused RFID tag antenna short-circuiting, which was detected in real-time as a change in the signal strength compared to an unmodified reference RFID tag (Fig. 4E). All positive and negative samples were correctly assigned using the RFID- μ PAD (Fig. S32).

We have demonstrated several strategies to interface biological signals with materials that combine the inherent programmability of CRISPR-associated enzymes with hydrogel systems. These strategies offer control over a variety of complex behaviors and properties, including the release of molecules, nanoparticles, and live cells, as well as bulk hydrogel degradation, electronic signal transduction, and microfluidic valve actuation. By exploiting the enzymatic properties of Cas12a, we have designed a platform that improves upon hydrogel programmability and versatility as only the gRNA molecule needs to be changed to allow hydrogel response to a user-defined DNA sequence. The catalytic activity of Cas12a improves sensitivity compared to DNA-responsive hydrogels requiring stoichiometric amounts of DNA triggers for material activation. Finally, we demonstrate various forms of output that expand the capabilities of CRISPR-responsive materials and enhance existing biomaterial-based approaches for tissue engineering, molecular diagnostics, and bioelectronic interfaces with programmable readouts.

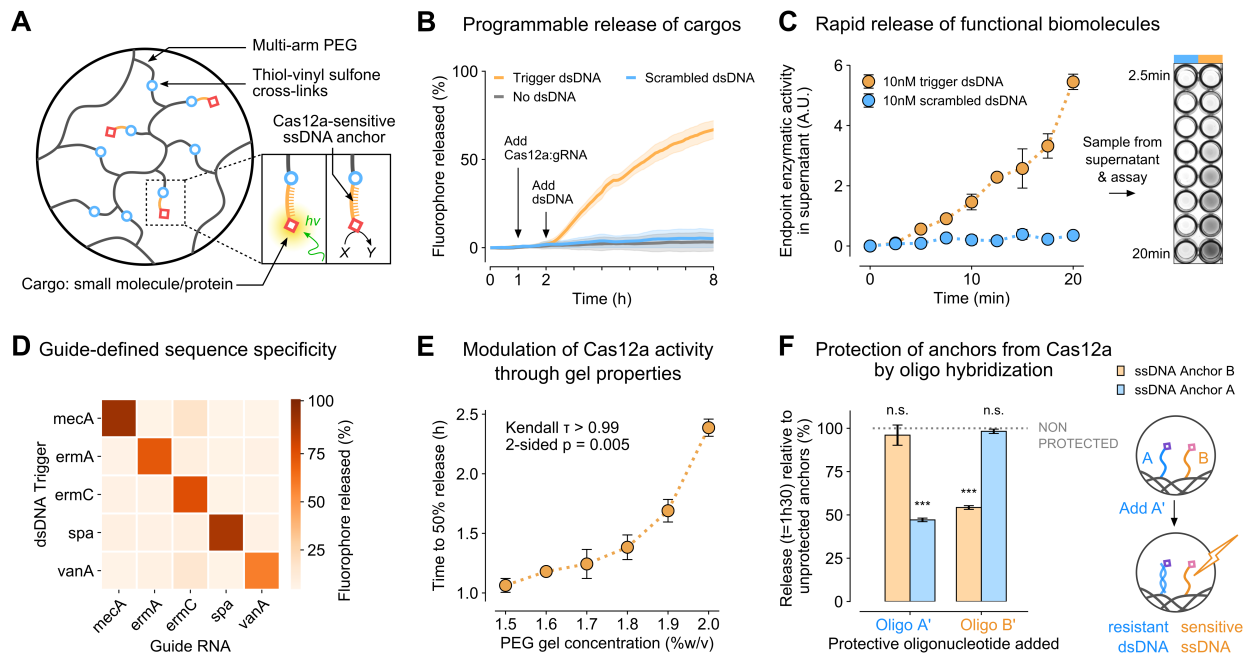

5 **Fig. 1. Cas12a mediated release of small molecules and enzymes from PEG hydrogels.** (A) ssDNA
 acts as a cleavable linker for attaching payloads to an inert PEG matrix. (B) Release of a tethered
 fluorophore by Cas12a is initiated only upon introduction of a specific dsDNA trigger, and not a
 10 scrambled dsDNA control sequence. (C) Functional enzymes can be anchored into the hydrogel, and
 released by Cas12a in sufficient quantities for visual detection in a horseradish peroxidase activity assay
 within minutes. (D) Activation of Cas12a and fluorophore release ($t = 8$ h) is defined by the
 complementarity between a dsDNA sequence and the gRNA of Cas12a. (E) The cross-linking density of
 the PEG hydrogels modulates the release rate of the cargo by Cas12a. The correlation was analyzed using
 a Kendall rank test. (F) Pre-hybridization of the ssDNA linkers with a matching oligonucleotide
 15 selectively reduces the release rate of molecules anchored in the gel (observed at $t = 1.5$ h). The means
 were compared to independent samples that were not pre-protected with oligonucleotides (grey).
 Differences in the means of the test conditions and the unprotected controls were analyzed using a t-test
 (Bonferroni adjusted $\alpha = 0.0125$, p-values: n.s. > 0.05 , *** < 0.0001). All plots show mean \pm SD for $n \geq$
 3 replicates.

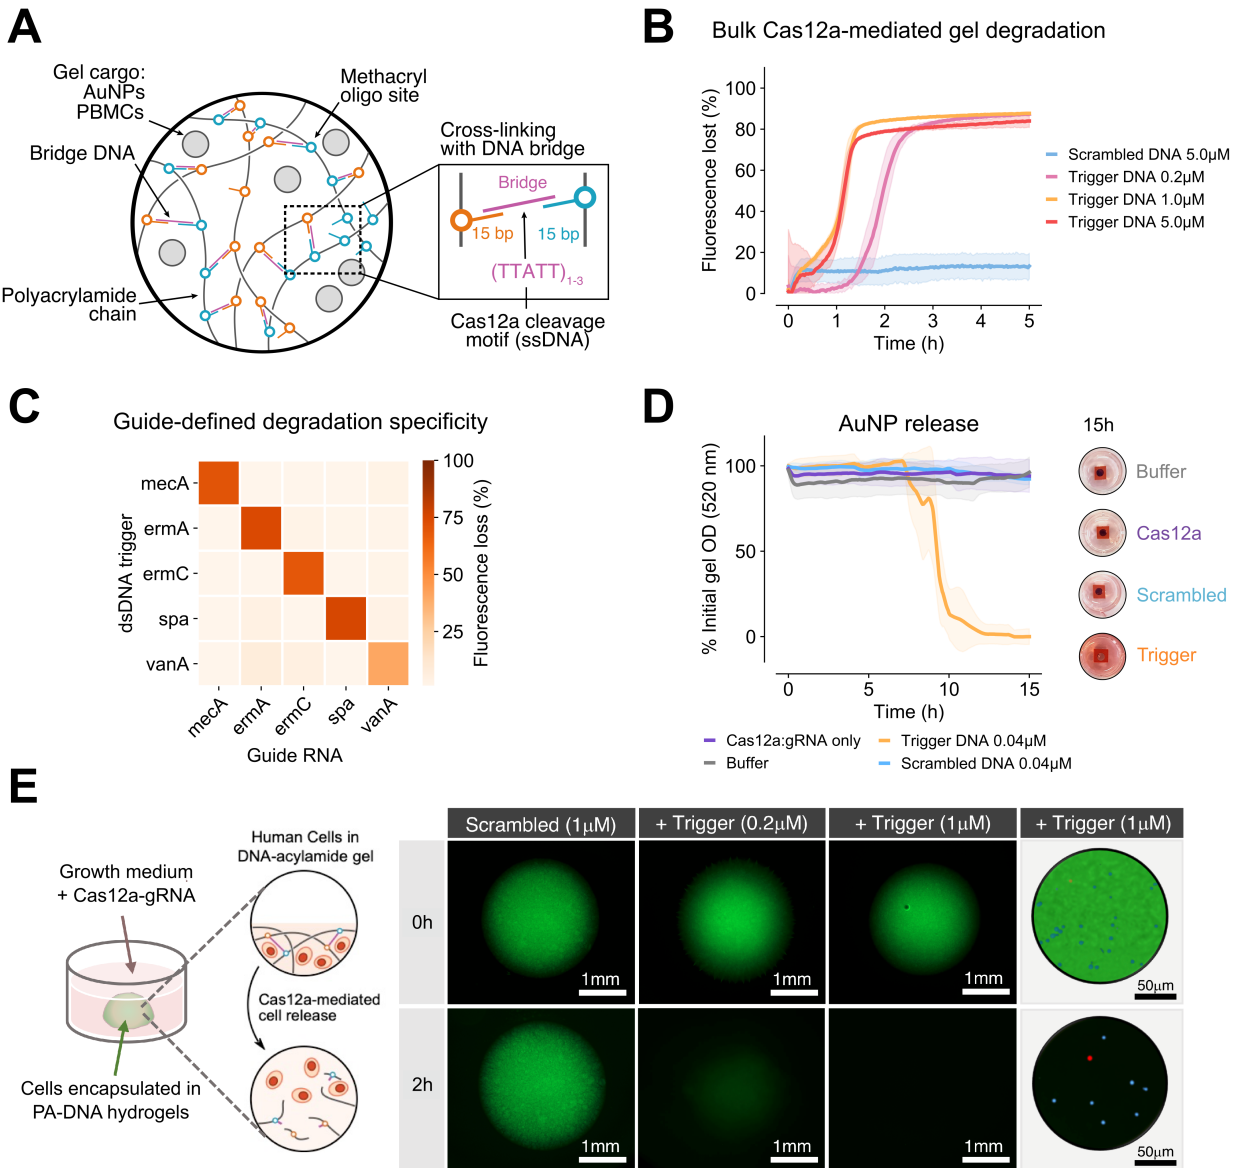


Fig. 2. Programmable release of nanoparticles and live cells from polyacrylamide-DNA hydrogels.

(A) ssDNA bridges lock DNA-functionalized polyacrylamide chains into a 3D network. (B) Cas12a-mediated degradation of PA-DNA gels stained with EvaGreen intercalating DNA dye. (C) Degradation of gel with 25 combinations of gRNAs and dsDNA triggers and comparison of signals after 12 h. (D) Release of AuNPs from 7% (w/v) PA-DNA gels using Cas12a collateral cleavage, tracked by measuring gel optical density. The Cas12a-gRNA and dsDNA trigger were encapsulated in the gel with the AuNPs (concentrations shown include supernatant volume). (E) Sequence-specific degradation of PA-DNA gels leads to the release of encapsulated non-adherent PBMCs. Cells were stained before encapsulation using Calcein blue-AM (blue) and ethidium homodimer (red) and gels were labelled with a fluorescein-functionalized ssDNA bridge. See Figs. S24-S25 for post-degradation live-dead staining. All plots show mean \pm SD for $n \geq 3$ replicates.

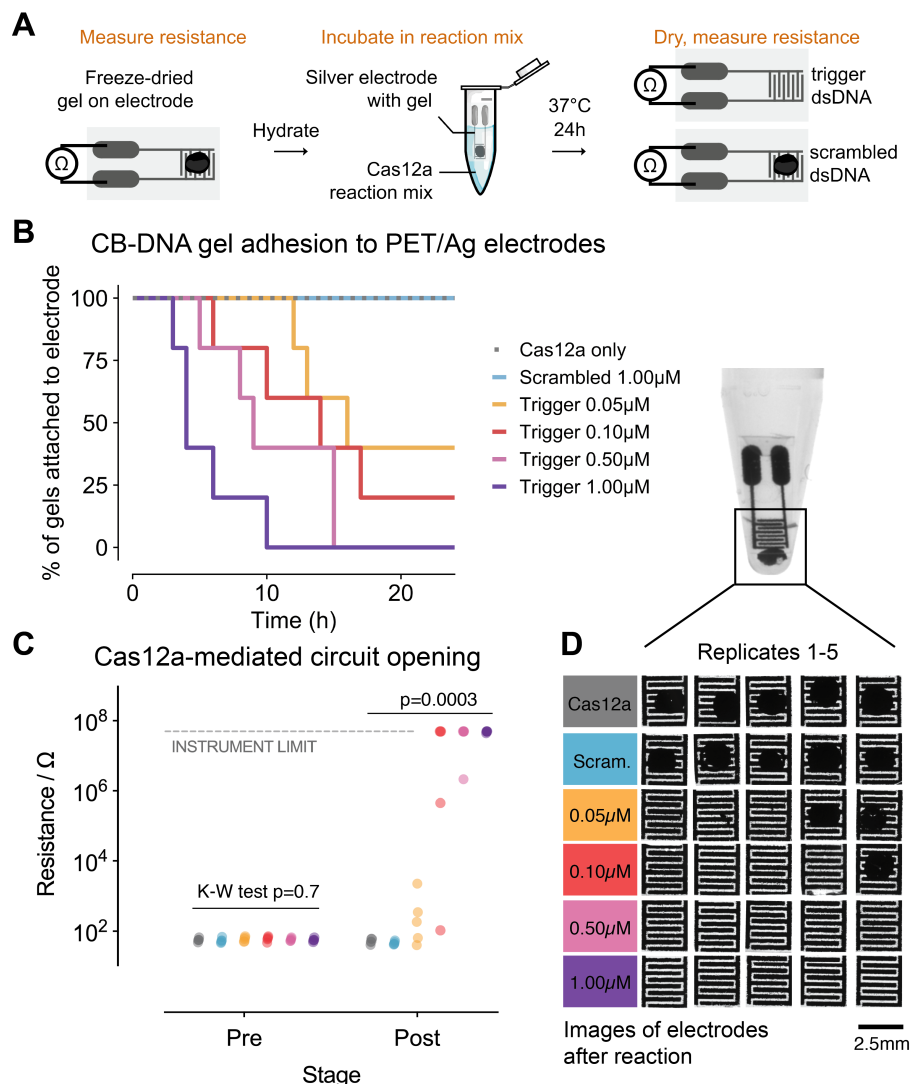


Fig. 3. Carbon black-DNA (CB-DNA) hydrogels can be used as Cas12a-actuated electrical fuses.

(A) Schematic of the experimental workflow. (B) Degradation kinetics of CB-DNA gels with increasing concentrations of DNA trigger ($n = 5$ per condition). We inspected replicates at hourly intervals to record detachment of gels from interdigitated electrodes (IDEs). (C) Electrical resistance across the IDEs in (B) after removal from the reaction upon detachment of the CB-DNA gel, or after 24 h if no detachment occurred. Measurements before and after reaction were compared using a Kruskal-Wallis test (before: $p = 0.7$, after: $p = 0.0003$) and Dunn's post-hoc test (before: all > 0.99 ; after: $p < 0.05$ for both 1.0 μM and 0.5 μM vs controls, $p > 0.05$ otherwise). (D) A representative image of a gel in the reaction mix detached from its IDE (top) and microscopy images of the IDEs in (B) after removal from the reaction (bottom). Images are quantified in Fig. S23A.

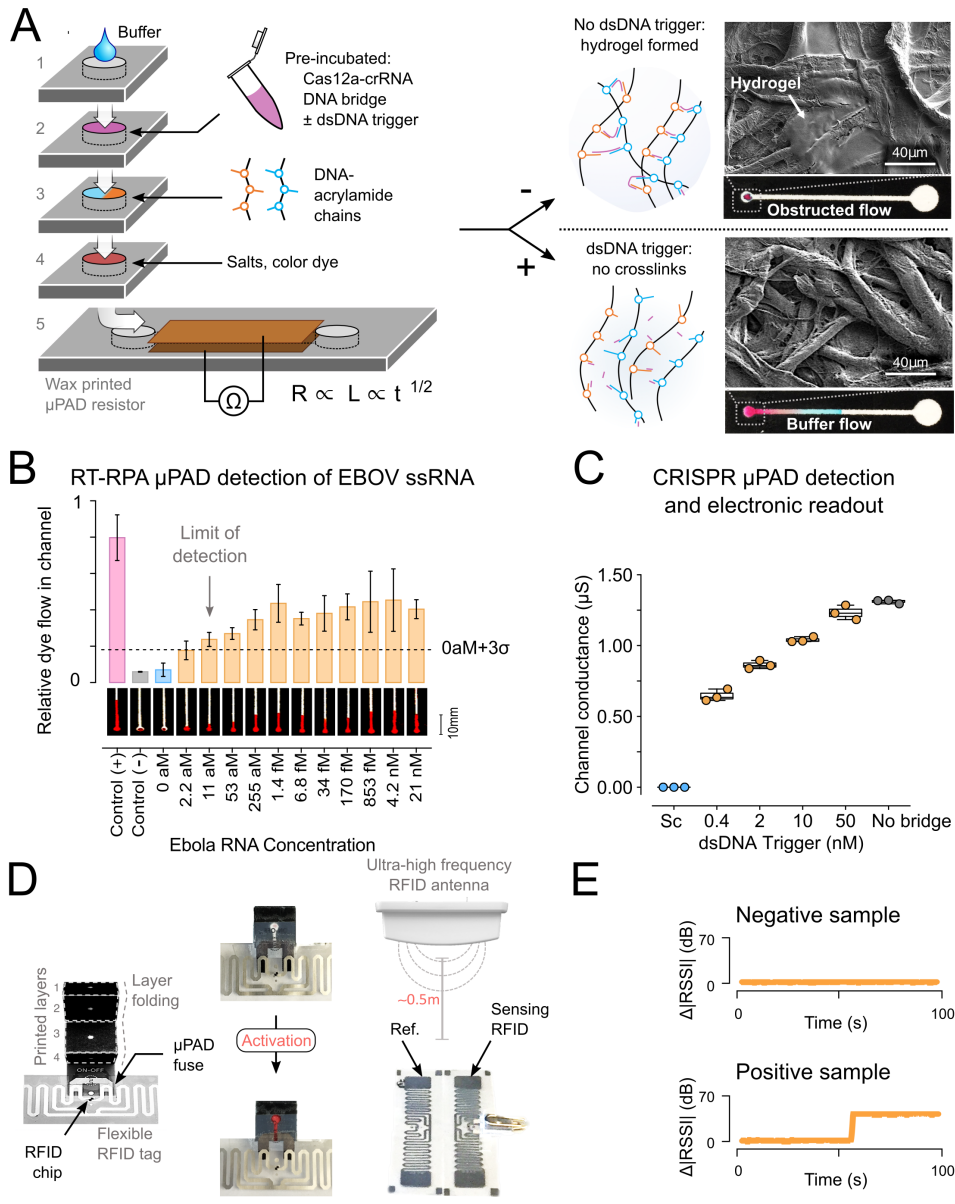


Fig. 4. Cas12a digestion of hydrogel precursors modulates permeability of a paper-based microfluidic device (μ PAD) with dual visual and electronic readouts for diagnostic applications. (A) Schematic of the stackable μ PAD design (40) modified for operation with CRISPR-gels and electrical readout. Layers 1-4 contain hydrophilic regions that form a continuous channel on folding, and feed into a lateral flow channel in layer 5. The channel in layer 5 was covered with conductive tape to measure conductivity as a function of buffer wicking. In the presence of target trigger, Cas12a cleaves the DNA linker, preventing hydrogel cross-linking in the channel and enabling flow. The inset shows SEM images of channels with (top) and without (bottom) cross-linked hydrogel. (B) Endpoint measurements ($t = 5$ min) of the colorimetric coupled reverse transcription-recombinase polymerase amplification (RT-RPA) μ PAD hydrogel detection system for different concentrations of ssRNA EBOV input (mean \pm SD, $n = 3$). Representative images of μ PAD channel flow are shown. The positive control corresponds to flow with no ssDNA bridging strand in the pre-incubation reaction, and the negative control corresponds to flow with an undigested ssDNA bridging strand. Student's t -test $p = 0.0057$ for differences in the means of the 0 and 11 aM ssRNA samples. (C) Endpoint measurements (5 min) of resistance across the channel for

different concentrations of dsDNA MRSA trigger input, after a 4 hour pre-digestion step. Sc = 50 nM scrambled dsDNA. (D) Schematic illustrating the integration of the paper-fluidic device with an RFID flexible tag. Cas12a activation in the pre-incubation step results in the short-circuiting of an interdigitated electrode arrangement in the loop RFID tag, thereby altering the received signal strength indicator (RSSI) compared to a reference tag. An increase in absolute RSSI difference between the tags is indicative of Cas12a activation by a dsDNA trigger. (E) Representative signal traces for positive and negative results in the experimenter-blinded trial of the RFID μ PAD device (full set in Fig. S29). Samples containing either 0 aM (negative) or 11aM (positive) EBOV ssRNA trigger were amplified by RT-RPA, incubated with the ssDNA gel bridging strand and Cas12a-gRNA for 4 h, and assayed on a μ PAD-RFID device.

References and Notes:

1. S. Y. Li *et al.*, CRISPR-Cas12a has both cis- and trans-cleavage activities on single-stranded DNA. *Cell Res.* **28**, 491-493 (2018).
2. J. S. Chen *et al.*, CRISPR-Cas12a target binding unleashes indiscriminate single-stranded DNase activity. *Science* **360**, 436-439 (2018).
3. G. J. Knott, J. A. Doudna, CRISPR-Cas guides the future of genetic engineering. *Science* **361**, 866-869 (2018).
4. J. S. Gootenberg *et al.*, Nucleic acid detection with CRISPR-Cas13a/C2c2. *Science* **356**, 438-442 (2017).
5. J. S. Gootenberg *et al.*, Multiplexed and portable nucleic acid detection platform with Cas13, Cas12a, and Csm6. *Science* **360**, 439-444 (2018).
6. N. Gjorevski *et al.*, Designer matrices for intestinal stem cell and organoid culture. *Nature* **539**, 560-564 (2016).
7. W. Na, D. Nam, H. Lee, S. Shin, Rapid molecular diagnosis of infectious viruses in microfluidics using DNA hydrogel formation. *Biosens. Bioelectron.* **108**, 9-13 (2018).
8. M. Qin *et al.*, Bioinspired hydrogel interferometer for adaptive coloration and chemical sensing. *Adv. Mater.* **30**, e1800468 (2018).
9. J. S. Kahn *et al.*, Integration of Switchable DNA-based hydrogels with surfaces by the hybridization chain reaction. *Nano Lett.* **15**, 7773-7778 (2015).
10. E. Heitzer, P. Ulz, J. B. Geigl, Circulating tumor DNA as a liquid biopsy for cancer. *Clin. Chem.* **61**, 112-123 (2015).
11. H. H. Yang, H. P. Liu, H. Z. Kang, W. H. Tan, Engineering target-responsive hydrogels based on aptamer-target interactions. *J. Am. Chem. Soc.* **130**, 6320-6321 (2008).
12. A. Cangialosi *et al.*, DNA sequence-directed shape change of photopatterned hydrogels via high-degree swelling. *Science* **357**, 1126-1129 (2017).
13. S. Sugimoto *et al.*, Broad impact of extracellular DNA on biofilm formation by clinically isolated Methicillin-resistant and -sensitive strains of *Staphylococcus aureus*. *Sci. Rep.* **8**, 2254 (2018).
14. Materials and methods are provided in the supplementary materials.
15. B. P. Kleinstiver *et al.*, Genome-wide specificities of CRISPR-Cas Cpf1 nucleases in human cells. *Nat. Biotechnol.* **34**, 869-874 (2016).
16. J. Y. Li, D. J. Mooney, Designing hydrogels for controlled drug delivery. *Nat. Rev. Mater.* **1**, 16071 (2016).
17. A. M. Rosales, K. S. Anseth, The design of reversible hydrogels to capture extracellular matrix dynamics. *Nat. Rev. Mater.* **1**, 15012 (2016).

18. B. P. Purcell *et al.*, Injectable and bioresponsive hydrogels for on-demand matrix metalloproteinase inhibition. *Nat. Mater.* **13**, 653-661 (2014).
19. M. M. Martino *et al.*, Growth factors engineered for super-affinity to the extracellular matrix enhance tissue healing. *Science* **343**, 885-888 (2014).
- 5 20. M. Arthur, C. Molinas, C. Mabilat, P. Courvalin, Detection of erythromycin resistance by the polymerase-chain reaction using primers in conserved regions of erm ribosomal-RNA methylase genes. *Antimicrob. Agents Ch.* **34**, 2024-2026 (1990).
21. B. Strommenger, C. Kettlitz, G. Werner, W. Witte, Multiplex PCR assay for simultaneous detection of nine clinically relevant antibiotic resistance genes in Staphylococcus aureus. *J. Clin. Microbiol.* **41**, 4089-4094 (2003).
- 10 22. C. E. Okolie, K. G. Wooldridge, D. P. J. Turner, A. Cockayne, R. James, Development of a heptaplex PCR assay for identification of Staphylococcus aureus and CoNS with simultaneous detection of virulence and antibiotic resistance genes. *BMC Microbiol.* **15**, 157 (2015).
- 15 23. N. K. Qureshi, S. H. Yin, S. Boyle-Vavra, The role of the staphylococcal VraTSR regulatory system on vancomycin resistance and vanA operon expression in vancomycin-resistant Staphylococcus aureus. *PLoS One* **9**, e85873 (2014).
24. K. W. Wang, T. Betancourt, C. K. Hall, Computational study of DNA-cross-linked hydrogel formation for drug delivery applications. *Macromolecules* **51**, 9758-9768 (2018).
- 20 25. D. C. Lin, B. Yurke, N. A. Langrana, Mechanical properties of a reversible, DNA-crosslinked polyacrylamide hydrogel. *J. Biomech. Eng.-T. ASME* **126**, 104-110 (2004).
26. B. Wei, I. Cheng, K. Q. Luo, Y. L. Mi, Capture and release of protein by a reversible DNA-induced sol-gel transition system. *Angew. Chem. Int. Edit.* **47**, 331-333 (2008).
- 25 27. K. Barker *et al.*, Biodegradable DNA-enabled poly(ethylene glycol) hydrogels prepared by copper-free click chemistry. *J. Biomat. Sci.-Polym. E.* **27**, 22-39 (2016).
28. Z. Zhu *et al.*, An aptamer cross-linked hydrogel as a colorimetric platform for visual detection. *Angew. Chem. Int. Edit.* **49**, 1052-1056 (2010).
29. R. Hajian *et al.*, Detection of unamplified target genes via CRISPR-Cas9 immobilized on a graphene field-effect transistor. *Nat. Biomed. Eng.* **3**, 427 – 437 (2019).
- 30 30. H. Parant *et al.*, Flowing suspensions of carbon black with high electronic conductivity for flow applications: Comparison between carbons black and exhibition of specific aggregation of carbon particles. *Carbon* **119**, 10-20 (2017).
31. M. Pawlyta, J. N. Rouzaud, S. Duber, Raman microspectroscopy characterization of carbon blacks: Spectral analysis and structural information. *Carbon* **84**, 479-490 (2015).
- 35 32. M. Spahr, R. Gilardi, D. Bonacchi, "Carbon black for electrically conductive polymer applications" in *Fillers for Polymer Applications*, R. Rother, Ed. (Polymers and Polymeric Composites: A Reference Series, Springer, Berlin, 2016).
33. C. H. Lu, H. H. Yang, C. L. Zhu, X. Chen, G. N. Chen, A graphene platform for sensing biomolecules. *Angew. Chem. Int. Edit.* **48**, 4785-4787 (2009).
- 40 34. Y. X. Xu, K. X. Sheng, C. Li, G. Q. Shi, Self-assembled graphene hydrogel via a one-step hydrothermal process. *ACS Nano* **4**, 4324-4330 (2010).
35. B. W. Liu, S. Salgado, V. Maheshwari, J. W. Liu, DNA adsorbed on graphene and graphene oxide: Fundamental interactions, desorption and applications. *Curr. Opin. Colloid In.* **26**, 41-49 (2016).
- 45

36. S. Manohar *et al.*, Peeling single-stranded DNA from graphite surface to determine oligonucleotide binding energy by force spectroscopy. *Nano Lett.* **8**, 4365-4372 (2008).
37. Y. X. Xu, Q. O. Wu, Y. Q. Sun, H. Bai, G. Q. Shi, Three-dimensional self-assembly of graphene oxide and DNA into multifunctional hydrogels. *ACS Nano* **4**, 7358-7362 (2010).
38. K. Pardee *et al.*, Rapid, low-cost detection of Zika virus using programmable biomolecular components. *Cell* **165**, 1255-1266 (2016).
39. K. Pardee *et al.*, Paper-based synthetic gene networks. *Cell* **159**, 940-954 (2014).
40. Y. He, Y. Wu, J. Z. Fu, W. B. Wu, Fabrication of paper-based microfluidic analysis devices: a review. *RSC Adv.* **5**, 78109-78127 (2015).
41. X. F. Wei *et al.*, Target-responsive DNA hydrogel mediated "stop-flow" microfluidic paper-based analytic device for rapid, portable and visual detection of multiple targets. *Anal. Chem.* **87**, 4275-4282 (2015).
42. A. K. Badu-Tawiah *et al.*, Polymerization-based signal amplification for paper-based immunoassays. *Lab Chip* **15**, 655-659 (2015).
43. L. Magro *et al.*, Paper-based RNA detection and multiplexed analysis for Ebola virus diagnostics. *Sci. Rep.* **7**, 1347 (2017).
44. E. Fu, B. Lutz, P. Kauffman, P. Yager, Controlled reagent transport in disposable 2D paper networks. *Lab Chip* **10**, 918-920 (2010).
45. L. Sun, S. S. Park, D. Sheberla, M. Dinca, Measuring and reporting electrical conductivity in metal organic frameworks: Cd-2(TTFTB) as a case study. *J. Am. Chem. Soc.* **138**, 14772-14782 (2016).
46. M. L. Previtiera, N. A. Langrana, Preparation of DNA-crosslinked polyacrylamide hydrogels. *JOVE-J. Vis. E.*, e51323 (2014).
47. J. Turkevich, P. C. Stevenson, J. Hillier, A study of the nucleation and growth processes in the synthesis of colloidal gold. *Discuss. Faraday Soc.* **11**, 55-75 (1951).
48. H. H. Lee, K. S. Chou, K. C. Huang, Inkjet printing of nanosized silver colloids. *Nanotechnology* **16**, 2436-2441 (2005).
49. W. Cai, S. B. Xie, J. Zhang, D. Y. Tang, Y. Tang, An electrochemical impedance biosensor for Hg²⁺ detection based on DNA hydrogel by coupling with DNAzyme-assisted target recycling and hybridization chain reaction. *Biosens. Bioelectron.* **98**, 466-472 (2017).
50. Y. Z. Xing *et al.*, Self-assembled DNA hydrogels with designable thermal and enzymatic responsiveness. *Adv. Mater.* **23**, 1117-1121 (2011).
51. X. Z. Ma *et al.*, Remote controlling DNA hydrogel by magnetic field. *ACS Appl. Mater. Inter.* **9**, 1995-2000 (2017).
52. S. Venkatesh, J. Wower, M. E. Byrne, Nucleic acid therapeutic carriers with on-demand triggered release. *Bioconjugate Chem.* **20**, 1773-1782 (2009).
53. Y. Y. Chang *et al.*, Homogeneous entropy catalytic-driven DNA hydrogel as strong signal blocker for highly sensitive electrochemical detection of platelet-derived growth factor. *Anal. Chem.* **90**, 8241-8247 (2018).
54. G. Sicilia *et al.*, Programmable polymer-DNA hydrogels with dual input and multiscale responses. *Biomater. Sci.* **2**, 203-211 (2014).
55. M. Gao, K. Gawel, B. T. Stokke, Toehold of dsDNA exchange affects the hydrogel swelling kinetics of a polymer-dsDNA hybrid hydrogel. *Soft Matter* **7**, 1741-1746 (2011).

56. S. H. Li, N. C. Chen, Z. Y. Zhang, Y. Wang, Endonuclease-responsive aptamer-functionalized hydrogel coating for sequential catch and release of cancer cells. *Biomaterials* **34**, 460-469 (2013).

5 **Acknowledgments:** We thank T. Ferrante for his support during the acquisition of confocal images, as well as C. Lin, D.B. Chou and F.A. Ran for supplying cells and media for cell-hydrogel release experiments. We thank T. Divoux for helpful discussions and advice relating to the carbon black-DNA gels. We thank S. Gobaa for helpful discussions regarding PEG hydrogel chemistry. We thank C. Escobedo for help and advice with cell culture in soft materials. We
10 thank members of the Collins Lab for helpful discussion during manuscript editing.

Funding: This work was supported by the Defense Threat Reduction Agency grant HDTRA1-14-1-0006, the Paul G. Allen Frontiers Group, and the Wyss Institute for Biologically Inspired Engineering, Harvard University (J.J.C, L.R.S., H.P., A.M.). L.R.S. was also supported by
15 CONACyT grant 342369 / 408970, and N.A.M. was supported by an MIT-TATA Center fellowship 2748460.

Author contributions: M.A.E., L.R.S., R.V.G., H.P. and A.S.M. designed and performed experiments, analyzed the data, and wrote the manuscript. N.A.M. and P.Q.N. performed
20 experiments and edited the manuscript. J.J.C. directed overall research and edited the manuscript.

Competing interests: M.A.E., L.R.S., R.V.G., H.P., N.A.M., P.Q.N., A.S.M. and J.J.C. are inventors on a U.S. Provisional Patent Application (No. 62/823,272) that covers CRISPR-
25 responsive materials. J.J.C. is a co-founder and director of Sherlock Biosciences.

Data and materials availability: All data needed to evaluate the conclusions in the paper can be found in the paper and/or the Supplementary Materials. Sequences used in this study are listed in
30 Table S4 of the Supplementary Materials. Correspondence and requests for materials should be addressed to J.J.C.

Supplementary Materials:

www.sciencemag.org/cgi/content/full/#####

Materials and Methods

35 Figures S1-S32

Tables S1-S4

References (45-56)