

MIT Open Access Articles

Temperature dependence of the Dzyaloshinskii-Moriya interaction in Pt/Co/Cu thin film heterostructures

The MIT Faculty has made this article openly available. **Please share** how this access benefits you. Your story matters.

As Published: 10.1063/1.5038353

Publisher: AIP Publishing

Persistent URL: <https://hdl.handle.net/1721.1/134744>

Version: Final published version: final published article, as it appeared in a journal, conference proceedings, or other formally published context

Terms of Use: Article is made available in accordance with the publisher's policy and may be subject to US copyright law. Please refer to the publisher's site for terms of use.



Temperature dependence of the Dzyaloshinskii-Moriya interaction in Pt/Co/Cu thin film heterostructures

Sarah Schlotter, Parnika Agrawal, and Geoffrey S. D. Beach

Citation: *Appl. Phys. Lett.* **113**, 092402 (2018); doi: 10.1063/1.5038353

View online: <https://doi.org/10.1063/1.5038353>

View Table of Contents: <http://aip.scitation.org/toc/apl/113/9>

Published by the [American Institute of Physics](#)

Articles you may be interested in

[Improving the magnetodynamical properties of NiFe/Pt bilayers through Hf dusting](#)
Applied Physics Letters **113**, 092401 (2018); 10.1063/1.5026232

[Anomalous spin Hall magnetoresistance in Pt/Co bilayers](#)
Applied Physics Letters **112**, 202405 (2018); 10.1063/1.5021510

[Temperature dependence of interlayer exchange coupling and Gilbert damping in synthetic antiferromagnetic trilayers investigated using broadband ferromagnetic resonance](#)
Applied Physics Letters **113**, 042401 (2018); 10.1063/1.5040666

[Interfacial coupling and negative spin Hall magnetoresistance in Pt/NiO/YIG](#)
Applied Physics Letters **113**, 072406 (2018); 10.1063/1.5041865

[Structural, magnetic, and transport properties of Fe_{1-x}Rh_x/MgO\(001\) films grown by molecular-beam epitaxy](#)
Applied Physics Letters **113**, 082403 (2018); 10.1063/1.5048303

[Study on measurement technique for magnetization dynamics of thin films](#)
Applied Physics Letters **112**, 252403 (2018); 10.1063/1.5032305

AIP | Conference Proceedings

Get **30% off** all
print proceedings!

Enter Promotion Code **PDF30** at checkout



Temperature dependence of the Dzyaloshinskii-Moriya interaction in Pt/Co/Cu thin film heterostructures

Sarah Schlotter,^{1,2} Parnika Agrawal,² and Geoffrey S. D. Beach^{2,a)}

¹John A. Paulson School of Engineering and Applied Sciences, Harvard University, Cambridge, Massachusetts 02138, USA

²Department of Materials Science and Engineering, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, USA

(Received 2 May 2018; accepted 16 August 2018; published online 30 August 2018)

Magnetic materials that exhibit chiral domain walls are of great interest for spintronic devices. In this work, we examine the temperature-dependent behavior of the Dzyaloshinskii-Moriya interaction (DMI) in Pt/Co/Cu thin film heterostructures. We extract the DMI strength, D , from static domain spacing analysis between 300 K and 500 K and compare its temperature dependence to that of the magnetic anisotropy, K_u , and saturation magnetization, M_s . Consistent with expected scaling in thin films, M_s exhibits Bloch-law temperature scaling and K_u scales as $M_s^{2.1 \pm 0.1}$. However, D varies more strongly with temperature than expected, scaling as $D \propto M_s^{4.9 \pm 0.7}$, indicating that interfacial DMI is more sensitive to thermal fluctuations than bulk magnetic properties. We suggest that this may be related to the temperature dependence of locally induced magnetic moments in the Pt underlayer and the $3d$ - $5d$ orbital interactions at the interface. While we observe stable domain widths in the studied temperature range, a strongly temperature dependent DMI may have significant consequences for potential devices based on the chiral domain wall or skyrmion motion. Published by AIP Publishing. <https://doi.org/10.1063/1.5038353>

Chiral magnetic thin film heterostructures have been of great interest in recent years for their potential for fast domain wall motion^{1,2} stabilized by the Dzyaloshinskii-Moriya interaction (DMI) as well as the possibility of hosting room temperature skyrmions in racetrack-based spintronic devices.^{3–5} The Dzyaloshinskii-Moriya interaction (DMI) is an anti-symmetric exchange interaction that promotes chiral spin textures in ferromagnetic materials.^{6,7} In bulk materials, it can arise from spin-orbit coupling (SOC) acting as a high-order perturbation of the direct exchange interaction,^{7,8} or it can result from exchange between two ferromagnetic atoms and a third nonmagnetic atom with large spin-orbit coupling, such as at heavy metal/ferromagnet interfaces.⁹ Clarifying the origins of DMI and its relation to other magnetic and environmental parameters is critically important for understanding and designing spin-orbitronic materials for potential applications.

Fundamentally, interfacial magnetic anisotropy (IMA) and DMI in ferromagnet/heavy metal systems both arise from broken inversion symmetry and interfacial spin-orbit coupling (SOC). However, few studies have examined the correlation between DMI and IMA in thin film heterostructures and their relative dependence on temperature, which could provide insights into their common origins. Recent work has suggested that the orbital moment anisotropy responsible for IMA¹⁰ plays a critical role in establishing DMI, based on a correlation between the temperature dependence of the former and latter.¹¹ While the temperature dependence of IMA has been well-studied theoretically and experimentally,^{12–14} much less is known in the case of DMI. Rózsa *et al.* derived the temperature dependence of DMI

using a Green's function formalism and found that it scales similarly to Heisenberg exchange.¹⁵ This result is consistent with experiments examining the temperature dependence of the wavelength of spin spirals in Mn on W(110).¹⁶ Barker and Tretiakov concluded a strongly temperature-dependent DMI based on a study of antiferromagnetic skyrmions,¹⁷ but a detailed analysis of the related micromagnetic parameters was lacking.

In this letter, we use static domain spacing analysis and conventional magnetometry to characterize the temperature dependence of DMI, anisotropy, and magnetization and identify the corresponding scaling laws. We find that in the studied heavy-metal ferromagnetic multilayers, the DMI varies significantly with temperature and scales much more strongly than a mean-field model would suggest. This is in contrast to the magnetization and anisotropy, which agree well with existing theory. Despite the strong temperature dependence of all micromagnetic parameters, we find that the domain spacing varies relatively weakly with temperature up to at least 500 K, which would be beneficial in devices in which the bit size and spacing should be robust to temperature variations. However, given the important role of DMI in stabilizing chiral domain walls and skyrmions and its influence on their dynamics,¹⁸ this temperature dependence may have significant consequences for devices dependent on domain wall motion.

We studied Ta(3 nm)/[Pt(2 nm)/Co(1.1 nm)/Cu(1 nm)]₁₅/Pt(2 nm) films [Fig. 1(a)] grown on thermally oxidized Si via DC magnetron sputtering. The base chamber pressure was 1.6×10^{-8} Torr, and samples were grown under an Ar pressure of 4 mTorr. Material growth rates were calibrated using *ex situ* X-ray reflectivity which was also used to confirm the final sample thickness and structure. The Pt layers were used

^{a)}Electronic mail: gbeach@mit.edu

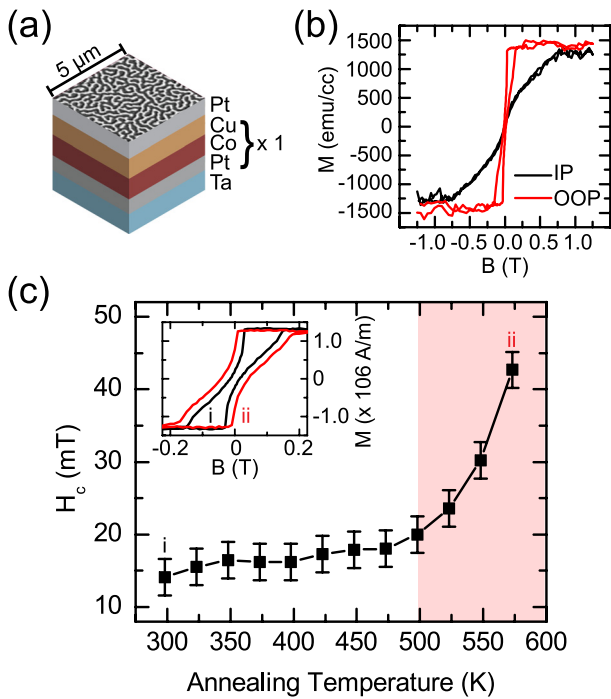


FIG. 1. (a) Schematic representation of the Ta (3)/[Pt (2)/Co (1.1)/Cu (1)]_{1.5}/Pt (2) sample (thicknesses in nm), with a room temperature magnetic force microscopy (MFM) image overlaid. (b) Out of plane (OOP) and in plane (IP) hysteresis loops taken by vibrating sample magnetometry (VSM). (c) Coercivity, H_c , as measured from OOP hysteresis loops after annealing at each temperature point for approximately 1 h. H_c begins to increase at approximately 500 K, which is the onset of annealing in this sample.

as a source of DMI and IMA, while the Cu layers were used to break inversion symmetry without contributing significantly to SOC-induced interfacial effects. We particularly chose to use Cu as a spacer layer because of its immiscibility with Co, which has previously been shown to prevent Co/Pt intermixing at the upper interface.¹⁹ Additionally, Cu has been shown to strengthen perpendicular magnetic anisotropy (PMA) in Pt/Co film systems.^{19–21} In-plane (IP) and out-of-plane (OOP) hysteresis loops measured using vibrating sample magnetometry (VSM) [Fig. 1(b)] confirm strong PMA in the film. The sheared OOP loop character with low remanence is characteristic of a multidomain demagnetized state,²² which is confirmed by magnetic force microscopy (MFM) in the inset of Fig. 1(a).

To determine the DMI constant D , we measured the domain width d in the labyrinth domain state and used a static domain spacing model based on the magnetostatic energies within the system. The analysis accounts for the competition between magnetostatic energy and domain wall energy, with the latter treated using an effective medium model which includes the transverse anisotropy of the domain wall, as proposed by Lemesh *et al.*²³ Similar experimental analysis has been presented by Meier *et al.*²⁴ From d , one can extract D with knowledge of the saturation magnetization M_s , uniaxial anisotropy constant K_u , and exchange stiffness, A .

Prior to performing temperature-dependent measurements, we determined the temperature threshold above which irreversible changes to the sample properties occur, due to processes such as crystallization or interdiffusion at the interfaces,^{25,26} as interfacial DMI is particularly sensitive to such structural changes.^{27–29} Figure 1(c) shows the

coercivity H_c as a function of annealing temperature (T) for an annealing time of 1 h. The data were obtained on a single sample subjected to sequentially increasing annealing temperatures and cooled back to 300 K between each step to measure an OOP hysteresis loop by VSM. H_c remains nearly constant up to approximately 500 K, beyond which a significant increase is observed. We hence restrict our measurements to temperatures below this threshold.

To measure $d(T)$, we performed MFM at variable temperatures using an Asylum MFP-3D with a sample heating stage (stability ± 0.5 K). Fourier transforms of the labyrinth domain images were used to extract d ; an example Fourier transform of an image taken at room temperature is shown in Fig. 2(a), and the corresponding Gaussian fit to the Fourier transform is shown in Fig. 2(b). Prior to acquisition of each image, an *in situ* AC demagnetization cycle was applied at temperature to ensure that the magnetic domains were in their true equilibrium width. The MFM tip was then allowed to reach thermal equilibrium with the sample before imaging for approximately 10 min. For each measurement, the heating, thermal equilibrating, and imaging cycle took approximately 1 h.

MFM was also used to verify that no irreversible structural changes were occurring as the sample was heated. Figure 2(c) shows a labyrinth domain image taken at 300 K after 8 h of imaging at temperatures up to 450 K. The initial value of d at 300 K is 161 ± 2 nm, while after annealing, it is 167 ± 2 nm. The lack of significant variation of d after annealing indicates that the likelihood of large structural changes occurring is low.

Figure 2(d) shows a subset of images taken at several temperatures, and Fig. 2(e) shows the measured $d(T)$. The spike in $d(T)$ at 425 K appears to be an anomaly. As the value of d is carried through to D , this point does not follow the general trend of the entire dataset. For this reason, we believe that there may have been an issue with the AC demagnetization cycle for this data point, resulting in domain widths that were not at equilibria.

M_s and K_u were measured versus T using VSM. Rise times were at a maximum 5 min, and the sample equilibrated at temperature for another 5 min before the measurement cycle. M_s was determined from saturation in the OOP loops, measured to a maximum field of 1.25 T. The area between OOP and IP hysteresis loops was used to determine the effective magnetic anisotropy, $K_{eff} = K_u - \mu_0 M_s^2 / 2$, which then provides K_u . As shown in Fig. 3(a), M_s is well-fitted in the measured temperature range by Bloch's law, $M_s = M_s(0)(1 - (T/T_C)^x)$, with $x = 2.06$, $M_s(0) = 1.44 \times 10^6$ A/m, and $T_C = 1150$ K. The deviation of x from the expected value of 3/2 can be attributed to the granular nature of sputtered films.³⁰ Both M_s and K_u vary markedly with T between 300 K and 500 K [Fig. 3(b)], whereas the domain spacing varies rather weakly [Fig. 2(e)], implying that the exchange energies must vary in such a way as to keep the balance between magnetostatic and domain wall energies nearly constant.

The exchange stiffness, A , and its temperature dependence were estimated from the literature. Micromagnetic simulations often take A to be approximately $1.3\text{--}1.5 \times 10^{-11}$ J/m (Ref. 31) or $2.2\text{--}2.5 \times 10^{-11}$ J/m,^{32,33} while experimentally Brillouin light scattering experiments have reported values of

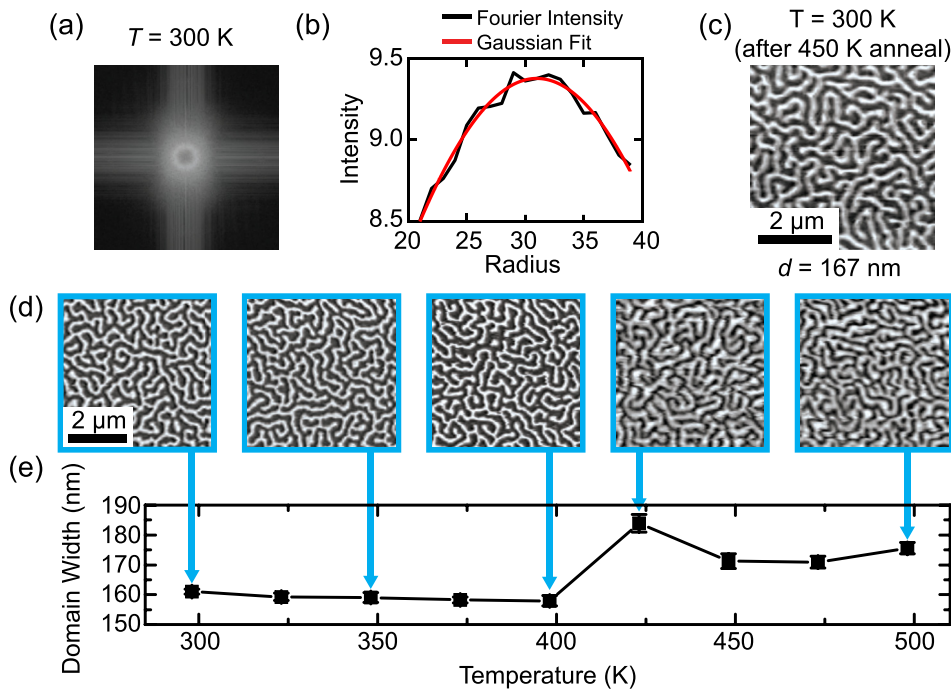


FIG. 2. (a) A sample Fourier transform of an MFM domain image taken at 300 K and (b) the corresponding Gaussian fit to the radial average peak intensity of the Fourier transform. (c) An MFM image taken at 300 K after imaging at temperature steps up to 450 K (roughly 8 h of imaging), with $d = 167 \pm 2 \text{ nm}$, comparable to the starting value of $d = 161 \pm 2 \text{ nm}$. (d) A selection of images taken at 300, 350, 400, 425, and 500 K while (e) shows calculated domain widths using Fourier transforms of the MFM images.

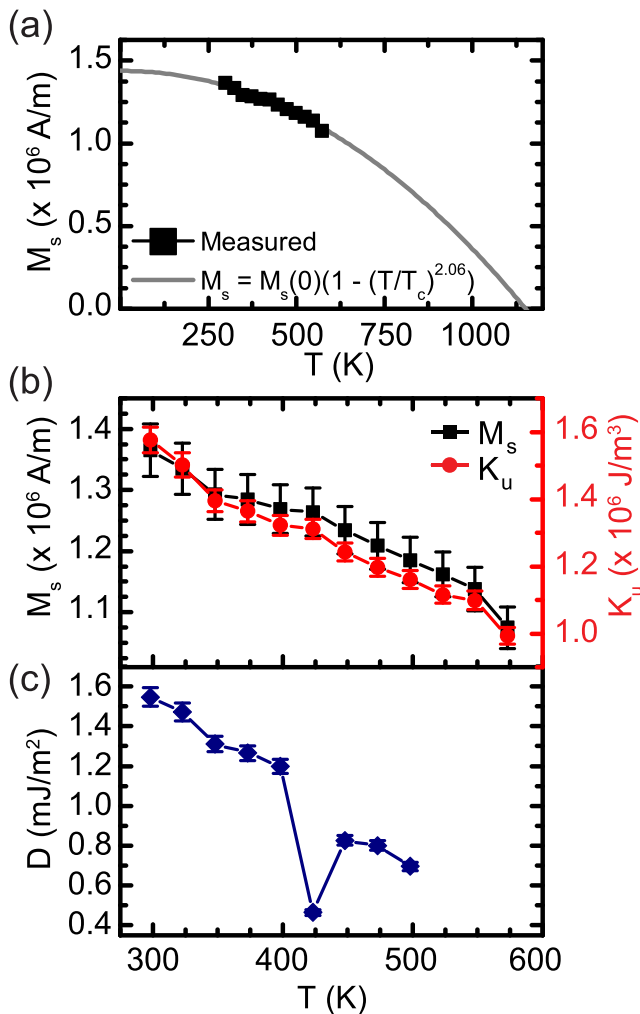


FIG. 3. (a) Measured saturation magnetization, M_s , taken between 300 and 575 K via vibrating sample magnetometry up to 1.25 T. $M_s(T)$ fits well to the Bloch law, such that $M_s(T) = M_s(0)(1 - (T/T_c)^{2.06})$. (b) Magnetocrystalline anisotropy, K_u , overlaid on the previous M_s data and (c) the Dzyaloshinskii-Moriya interaction strength, D .

$2.5 \times 10^{-11} \text{ J/m}$ or $3.6 \times 10^{-11} \text{ J/m}$, respectively.^{34,35} For simplicity, we assumed that $A(300 \text{ K}) = 2.0 \times 10^{-11} \text{ J/m}$. Additionally, we model $A(T)$ in accordance with work by Moreno *et al.*,³⁶ which indicated that in bulk Co, $A(T) \propto M_s^{1.8}$, rather than $\propto M_s^2$ as reported elsewhere.^{37,38} We find that the analysis carried out below of $D(T)$ does not depend strongly on the choice of the assumed scaling exponent for $A(T)$, since the latter enters the domain wall energy through its square root, $\sigma = 4\sqrt{AK}$.²³

From the measured K_u and M_s and the above assumption about $A(T)$, we extracted the DMI strength D from the measured domain spacing d . Here, we used the total energy expression $\sigma(d, A, K_u, M_s, D)$ for the multidomain state that was derived in Eq. (31) of Ref. 23 using an effective medium treatment of the multilayer. D was determined by numerical minimization of σ with respect to d , and the extracted $D(T)$ data are shown in Fig. 3(c). We evaluate this behavior and that of K_u by considering their scaling with M_s . Per Callen and Callen, $K \propto M^{l(l+1)/2}$, which over most temperature ranges results in $K \propto M^3$.¹² We find a best fit, however, with $K_u(T) \propto M_s(T)^{2.2 \pm 0.1}$, shown in Fig. 4(a). As these films are thin enough to support PMA, interfacial strain effects are likely contributing to the temperature dependence of anisotropy and changing its temperature scaling with M_s .^{39,40} Additionally, given evidence that DMI induces some anisotropy in heavy metal/ferromagnet interfaces,¹⁵ their interrelation may influence the net $K_u(T)$.

Neglecting Callen-like fluctuation corrections, one expects $D \propto M_s^2$ in a mean-field approximation similar to the mean-field scaling $A \propto M_s^2$.^{15,41} Rather, we find that $D(T) \propto M_s(T)^{4.9 \pm 0.7}$, as shown in Fig. 4(b), indicating that DMI is substantially more sensitive to temperature than bulk magnetic properties. This may be due to the 2-dimensional nature of interfacial DMI, as it has been shown that DMI in these types of thin film systems is a truly interfacial effect.⁴²⁻⁴⁴ We expect that lattice strains at material interfaces are playing a role in the behavior of $D(T)$. Thermal

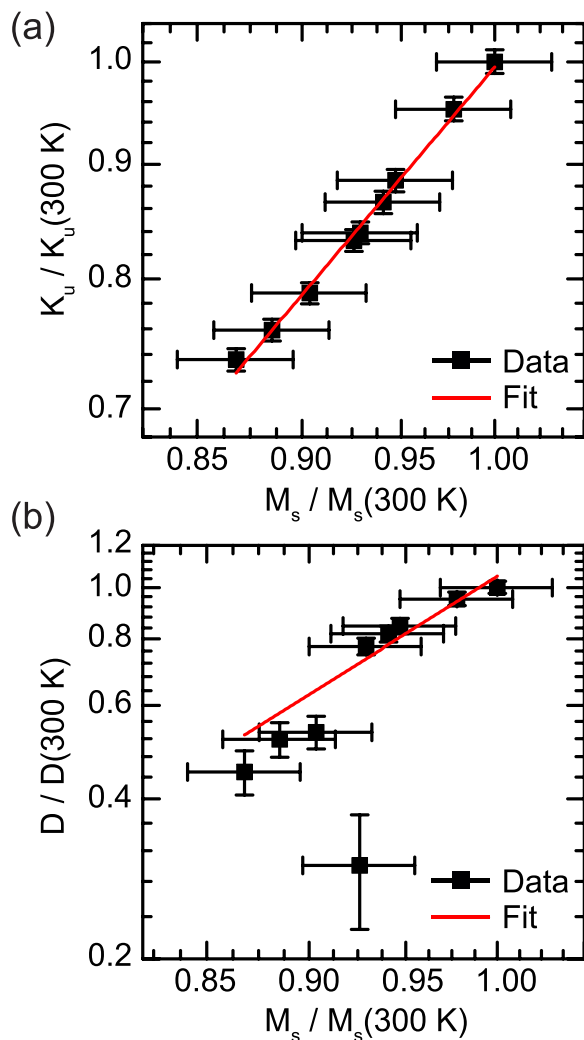


FIG. 4. (a) Log-log plot of the normalized $K_u/K_u(300 \text{ K})$ versus $M_s/M_s(300 \text{ K})$ fit with $K_u \propto M_s^{2.2 \pm 0.1}$ and (b) a log-log plot of the normalized $D/D(300 \text{ K})$ versus $M_s/M_s(300 \text{ K})$ fit with $D \propto M_s^{4.9 \pm 0.7}$. Fits were weighted in both x and y, and the fit in (b) excluded the anomalous point at 425 K.

lattice expansion is a primary source of temperature dependence of Heisenberg exchange,⁴⁵ and it has been shown that even 5% strain can significantly affect $d-d$ hybridization.⁴⁶ Disentangling structural changes such as atomic diffusion and lattice strain from the underlying physics of DMI will be essential in future work.

Assuming that the crystal structure was stable during our measurements, we suggest several possible sources for the physical origin of the observed behavior. According to Kim *et al.*,¹¹ electron hopping occurs between orbitals in noncentrosymmetric systems. The resulting electron-phonon interactions and magnetization fluctuations cause a broadening of the Fermi energy.¹¹ Our results thus indirectly suggest a correlation between the electron hopping due to inversion symmetry breaking and DMI and additionally with the Rashba field.⁴⁷

We further posit that the strong temperature dependence of the DMI may be indicative of the role of proximity-induced magnetic moments in Pt and the corresponding interaction of the $3d$ and $5d$ orbitals at the Pt/Co interface. Computational work by Belabbes *et al.* has shown that the

strength and sign of DMI in $3d-5d$ films are highly dependent on the hybridization of the $3d$ and $5d$ orbitals near the Fermi level.⁴⁸ Additionally, the locally induced magnetic moments of $5d$ metals in $3d/5d$ systems are strongly affected by temperature, an effect which has been shown to influence the temperature dependent behavior of K in $3d-5d$ alloys⁴⁹ and which we can similarly expect to influence the temperature dependence of DMI.

In summary, we measured the temperature dependence of the Dzyaloshinskii-Moriya interaction in Pt/Co/Cu thin film heterostructures using vibrating sample magnetometry and magnetic force microscopy and determined DMI via magnetostatic energy minimization. We find that domain spacing shows only a weak temperature dependence at elevated T , which could be a useful attribute for domain wall or skyrmion devices. Further, we found that the behavior of the magnetocrystalline anisotropy deviated from the expected relation, $K_u \propto M_s^3$, but was consistent with similar measurements in the literature. However, DMI scales more strongly with M_s than either A or K_u . This work raises questions about the specific sources of the temperature dependence of interfacial DMI, the impact of structural changes on the behavior of DMI, and the relation of the behavior of DMI to that of Heisenberg exchange.

This work was supported by the U.S. Department of Energy (DOE), Office of Science, Basic Energy Sciences (BES) under Award No. de-sc0012371 (sample fabrication and magnetic properties characterization) and performed in part at the Center for Nanoscale Systems (CNS), a member of the National Nanotechnology Coordinated Infrastructure Network (NNCI), which was supported by the National Science Foundation under NSF Award No. 1541959. S.S. acknowledges the National Science Foundation Graduate Research Fellowship under Grant No. DGE1144152 and thanks Felix Büttner for his feedback.

¹S. Emori, U. Bauer, S.-M. Ahn, E. Martinez, and G. S. D. Beach, "Current-driven dynamics of chiral ferromagnetic domain walls," *Nat. Mater.* **12**, 611–616 (2013).

²S. G. Je, D. H. Kim, S. C. Yoo, B. C. Min, K. J. Lee, and S. B. Choe, "Asymmetric magnetic domain-wall motion by the Dzyaloshinskii-Moriya interaction," *Phys. Rev. B* **88**, 214401 (2013).

³R. Tomasello, E. Martinez, R. Zivieri, L. Torres, M. Carpentieri, and G. Finocchio, "A strategy for the design of skyrmion racetrack memories," *Sci. Rep.* **4**, 6784 (2014).

⁴A. Fert, V. Cros, and J. Sampaio, "Skyrmions on the track," *Nat. Nanotechnol.* **8**, 152–156 (2013).

⁵F. Büttner, I. Lemes, M. Schneider, B. Pfau, C. M. Günther, P. Hession, J. Geilhufe, L. Caretta, D. Engel, B. Krüger, J. Viehhaus, S. Eisebitt, and G. S. Beach, "Field-free deterministic ultrafast creation of magnetic skyrmions by spin-orbit torques," *Nat. Nanotechnol.* **12**, 1040–1044 (2017). 1705.01927.

⁶I. Dzyaloshinsky, "A thermodynamic theory of 'weak' ferromagnetism of antiferromagnetics," *J. Phys. Chem. Solids* **4**, 241–255 (1958).

⁷T. Moriya, "Anisotropic superexchange interaction and weak ferromagnetism," *Phys. Rev.* **120**, 91–98 (1960).

⁸F. Keffer, "Moriya interaction and the problem of the spin arrangements in βmnS ," *Phys. Rev.* **126**, 896–900 (1962).

⁹A. Fert and P. M. Levy, "Role of anisotropic exchange interactions in determining the properties of spin-glasses," *Phys. Rev. Lett.* **44**, 1538–1541 (1980).

¹⁰P. Bruno, "Tight-binding approach to the orbital magnetic moment and magnetocrystalline anisotropy of transition-metal monolayers," *Phys. Rev. B* **39**, 865–868 (1989).

- ¹¹S. Kim, K. Ueda, G. Go, P. H. Jang, K. J. Lee, A. Belabbes, A. Manchon, M. Suzuki, Y. Kotani, T. Nakamura, K. Nakamura, T. Koyama, D. Chiba, K. T. Yamada, D. H. Kim, T. Moriyama, K. J. Kim, and T. Ono, "Correlation of the Dzyaloshinskii-Moriya interaction with Heisenberg exchange and orbital asphericity," *Nat. Commun.* **9**, 1648 (2018).
- ¹²H. B. Callen and E. Callen, "The present status of the temperature dependence of magnetocrystalline anisotropy, and the $1/(l+1)^2$ power law," *J. Phys. Chem. Solids* **27**, 1271–1285 (1966).
- ¹³J. B. Staunton, S. Ostanin, S. S. A. Razee, B. L. Gyorffy, L. Szunyogh, B. Ginatempo, and E. Bruno, "Temperature dependent magnetic anisotropy in metallic magnets from an *ab initio* electronic structure theory: L10-ordered FePt," *Phys. Rev. Lett.* **93**, 257204 (2004).
- ¹⁴N. N. Phuoc and C. K. Ong, "Anomalous temperature dependence of magnetic anisotropy in gradient-composition sputtered thin films," *Adv. Mater.* **25**, 980–984 (2013).
- ¹⁵L. Rózsa, U. Atxitia, and U. Nowak, "Temperature scaling of the Dzyaloshinsky-Moriya interaction in the spin wave spectrum," *Phys. Rev. B* **96**, 094436 (2017).
- ¹⁶G. Hasselberg, R. Yanes, D. Hinzke, P. Sessi, M. Bode, L. Szunyogh, and U. Nowak, "Thermal properties of a spin spiral: Manganese on tungsten(110)," *Phys. Rev. B* **91**, 064402 (2015).
- ¹⁷J. Barker and O. A. Tretiakov, "Static and dynamical properties of antiferromagnetic skyrmions in the presence of applied current and temperature," *Phys. Rev. Lett.* **116**, 147203 (2016).
- ¹⁸J. Torrejon, E. Martinez, and M. Hayashi, "Tunable inertia of chiral magnetic domain walls," *Nat. Commun.* **7**, 13533 (2016).
- ¹⁹S. Bandiera, R. C. Sousa, B. Rodmacq, L. Lechevallier, and B. Dieny, "Effect of a Cu spacer between Co and Pt layers on the structural and magnetic properties in (Co/Cu/Pt)₅/Pt type multilayers," *J. Phys. D: Appl. Phys.* **46**, 485003 (2013).
- ²⁰S. Bandiera, R. C. Sousa, B. Rodmacq, and B. Dieny, "Enhancement of perpendicular magnetic anisotropy through reduction of Co-Pt interdiffusion in (Co/Pt) multilayers," *Appl. Phys. Lett.* **100**, 142410 (2012).
- ²¹N. H. Kim, J. Cho, J. Jung, D. S. Han, Y. Yin, J. S. Kim, H. J. Swagten, K. Lee, M. H. Jung, and C. Y. You, "Role of top and bottom interfaces of a Pt/Co/AlOx system in Dzyaloshinskii-Moriya interaction, interface perpendicular magnetic anisotropy, and magneto-optical Kerr effect," *AIP Adv.* **7**, 035213 (2017).
- ²²H. J. G. Draaisma and W. J. M. De Jonge, "Magnetization curves of Pd/Co multilayers with perpendicular anisotropy," *J. Appl. Phys.* **62**, 3318–3322 (1987).
- ²³I. Lemesch, F. Büttner, and G. S. Beach, "Accurate model of the stripe domain phase of perpendicularly magnetized multilayers," *Phys. Rev. B* **95**, 174423 (2017).
- ²⁴T. N. G. Meier, M. Kronseder, and C. H. Back, "Domain-width model for perpendicularly magnetized systems with Dzyaloshinskii-Moriya interaction," *Phys. Rev. B* **96**, 144408 (2017).
- ²⁵P. F. Carcia, "Perpendicular magnetic anisotropy in Pd/Co and Pt/Co thin-film layered structures," *J. Appl. Phys.* **63**, 5066–5073 (1988).
- ²⁶F. J. A. Den Broeder, D. Kuiper, A. P. Van De Mosselaer, and W. Hoving, "Perpendicular magnetic anisotropy of Co-Au multilayers induced by interface sharpening," *Phys. Rev. Lett.* **60**, 2769–2772 (1988).
- ²⁷A. Hrabec, N. A. Porter, A. Wells, M. J. Benítez, G. Burnell, S. McVitie, D. McGrouther, T. A. Moore, and C. H. Marrows, "Measuring and tailoring the Dzyaloshinskii-Moriya interaction in perpendicularly magnetized thin films," *Phys. Rev. B* **90**, 020402 (2014).
- ²⁸R. A. Khan, P. M. Shepley, A. Hrabec, A. W. Wells, B. Ocker, C. H. Marrows, and T. A. Moore, "Effect of annealing on the interfacial Dzyaloshinskii-Moriya interaction in Ta/CoFeB/MgO trilayers," *Appl. Phys. Lett.* **109**, 132404 (2016).
- ²⁹A. W. Wells, P. M. Shepley, C. H. Marrows, and T. A. Moore, "Effect of interfacial intermixing on the Dzyaloshinskii-Moriya interaction in Pt/Co/Pt," *Phys. Rev. B* **95**, 054428 (2017).
- ³⁰P. V. Hendriksen, S. Linderöth, and P. A. Lindgård, "Finite-size modifications of the magnetic properties of clusters," *Phys. Rev. B* **48**, 7259–7273 (1993).
- ³¹H. F. Ding, W. Wulfhekel, and J. Kirschner, "Ultra sharp domain walls in the closure domain pattern of Co(0001)," *Europhys. Lett.* **57**, 100–106 (2002).
- ³²K. J. Lee, A. Deac, O. Redon, J. P. Nozières, and B. Dieny, "Excitations of incoherent spin-waves due to spin-transfer torque," *Nat. Mater.* **3**, 877–881 (2004).
- ³³H. F. Ding, A. K. Schmid, D. Li, K. Y. Guslienko, and S. D. Bader, "Magnetic bistability of Co nanodots," *Phys. Rev. Lett.* **94**, 157202 (2005).
- ³⁴S. P. Vernon, S. M. Lindsay, and M. B. Stearns, "Brillouin scattering from thermal magnons in a thin Co film," *Phys. Rev. B* **29**, 4439–4442 (1984).
- ³⁵M. Grimsditch, E. Fullerton, and R. Stamps, "Exchange and anisotropy effects on spin waves in epitaxial Co films," *Phys. Rev. B* **56**, 2617–2622 (1997).
- ³⁶R. Moreno, R. F. Evans, S. Khmelevskiy, M. C. Muñoz, R. W. Chantrell, and O. Chubykalo-Fesenko, "Temperature-dependent exchange stiffness and domain wall width in Co," *Phys. Rev. B* **94**, 104433 (2016).
- ³⁷L. de Broeckere and J. Vennik, "The temperature dependence of magnetic bubble parameters," *Phys. Status Solidi* **61**, 455–461 (1980).
- ³⁸F. Heider and W. Williams, "Note on temperature dependence of exchange constant in magnetite," *Geophys. Res. Lett.* **15**, 184–187, <https://doi.org/10.1029/GL015i002p00184> (1988).
- ³⁹W. J. Carr, Jr., "Temperature dependence of ferromagnetic anisotropy," *Phys. Rev.* **109**, 1971–1976 (1958).
- ⁴⁰K. M. Lee, J. W. Choi, J. Sok, and B. C. Min, "Temperature dependence of the interfacial magnetic anisotropy in W/CoFeB/MgO," *AIP Adv.* **7**, 065107 (2017).
- ⁴¹U. Atxitia, D. Hinzke, O. Chubykalo-Fesenko, U. Nowak, H. Kachkachi, O. N. Mryasov, R. F. Evans, and R. W. Chantrell, "Multiscale modeling of magnetic materials: Temperature dependence of the exchange stiffness," *Phys. Rev. B* **82**, 134440 (2010).
- ⁴²K. Di, V. L. Zhang, H. S. Lim, S. C. Ng, M. H. Kuok, J. Yu, J. Yoon, X. Qiu, and H. Yang, "Direct observation of the Dzyaloshinskii-Moriya interaction in a Pt/Co/Ni film," *Phys. Rev. Lett.* **114**, 047201 (2015).
- ⁴³K. Di, V. L. Zhang, H. S. Lim, S. C. Ng, M. H. Kuok, X. Qiu, and H. Yang, "Asymmetric spin-wave dispersion due to Dzyaloshinskii-Moriya interaction in an ultrathin Pt/CoFeB film," *Appl. Phys. Lett.* **106**, 052403 (2015).
- ⁴⁴J. Cho, N. H. Kim, S. Lee, J. S. Kim, R. Lavrijsen, A. Solignac, Y. Yin, D. S. Han, N. J. Van Hoof, H. J. Swagten, B. Koopmans, and C. Y. You, "Thickness dependence of the interfacial Dzyaloshinskii-Moriya interaction in inversion symmetry broken systems," *Nat. Commun.* **6**, 7635 (2015).
- ⁴⁵S. T. Bramwell, "Temperature dependence of the isotropic exchange constant," *J. Phys.: Condens. Matter* **2**, 7527–7536 (1990).
- ⁴⁶K. Kyuno, J.-G. Ha, R. Yamamoto, and S. Asano, "The effect of crystal orientation on the magnetic anisotropy of Pd/Co metallic multilayers," *J. Phys.: Condens. Matter* **8**, 3297–3303 (1996).
- ⁴⁷A. Kundu and S. Zhang, "Dzyaloshinskii-Moriya interaction mediated by spin-polarized band with Rashba spin-orbit coupling," *Phys. Rev. B: Condens. Matter Mater. Phys.* **92**, 094434 (2015).
- ⁴⁸A. Belabbes, G. Bihlmayer, F. Bechstedt, S. Blügel, and A. Manchon, "Hund's rule-driven Dzyaloshinskii-Moriya interaction at 3d-5d interfaces," *Phys. Rev. Lett.* **117**, 247202 (2016).
- ⁴⁹O. N. Mryasov, U. Nowak, K. Y. Guslienko, and R. W. Chantrell, "Temperature-dependent magnetic properties of FePt: Effective spin Hamiltonian model," *Europhys. Lett.* **69**, 805–811 (2005).